



Universiteit
Leiden
The Netherlands

Effect of bonding of a CO molecule on the conductance of atomic metal wires

Kiguchi, M.; Djukic, D.; Ruitenbeek, J.M. van

Citation

Kiguchi, M., Djukic, D., & Ruitenbeek, J. M. van. (2007). Effect of bonding of a CO molecule on the conductance of atomic metal wires. *Nanotechnology*, 18(3), 035205.
doi:10.1088/0957-4484/18/3/035205

Version: Not Applicable (or Unknown)

License: [Leiden University Non-exclusive license](#)

Downloaded from: <https://hdl.handle.net/1887/62504>

Note: To cite this publication please use the final published version (if applicable).

Effect of bonding of a CO molecule on the conductance of atomic metal wires

M. Kiguchi, D. Djukic, and J.M. van Ruitenbeek

Kamerlingh Onnes Laboratorium, Universiteit Leiden, Postbus 9504, NL - 2300 RA Leiden, The Netherlands
(November 12, 2017)

We have measured the effect of bonding of a CO molecule on the conductance of Au, Cu, Pt, and Ni atomic contacts at 4.2 K. When CO gas is admitted to the metal nano contacts, a conductance feature appears in the conductance histogram near 0.5 of the quantum unit of conductance, for all metals. For Au, the intensity of this fractional conductance feature can be tuned with the bias voltage, and it disappears at high bias voltage (above ~ 200 mV). The bonding of CO to Au appears to be weakest, and associated with monatomic Au wire formation.

I. INTRODUCTION

Fabrication and characterization of nano structures have attracted wide attention because of its potential application in atomic scale electronic devices. The development of fabrication methods such as mechanically controllable break junctions (MCBJ) and a scanning tunnelling microscopy, has made it possible to fabricate even monatomic metal wires [1,2]. The properties of the nano wires have been studied in detail by various methods [3]. On the basis of the understanding of the metal nano wire, the influence of molecules binding to the metal nano contacts has been discussed in recent years [4–12]. Li et al. reported a change in the conductance of metal nano wires due to adsorbates. The change was attributed to adsorbate scattering and rearrangement in the atomic configuration of the nano wire induced by adsorption [4]. Under specific circumstances a single molecule can be made to form a bridge between metal electrodes just after breaking the nano contact. The first conductance measurement of a single molecule was performed by Reed et al. who investigated 1,4 benzendithiol [5]. Conductance measurements of single molecules have been studied by several experimental techniques, including MCBJ and electromigration break junctions [9], and various interesting phenomena have been observed [6,9]. Although these results are promising there are large discrepancies between experimental results obtained by different groups, and between experiments and theory. One of the reasons for these discrepancies is uncertainty regarding the configuration of the molecule and the nature of the molecule-metal interface. The molecules selected for these studies are usually composed of several carbo-hydrate rings and are anchored to gold metal leads by sulphur groups. In view of the difficulties, it seems natural to step back and focus on even simpler system, such as H₂ and CO.

For H₂ on Pt nano contacts detailed studies have been performed by Pt conductance measurement and point contact spectroscopy. It was found that the conductance of a single H₂ molecule anchored between Pt leads is slightly below 1 G_0 , where $G_0 = 2e^2/h$ is the quantum conductance unit. The configuration of the H₂ molecule

in the junction and the number of conductance channels were determined by combined experimental and theoretical studies [7,8]. The effect of H₂ on metal nano contacts was also studied for Au, Fe, Co, Ni, and Pd [10–12]. Going beyond the simplest molecule, H₂, we concentrate here on CO for the follows reasons. First, CO is one of the simplest molecules for which atomic and electronic structures for bonding to metal surfaces are well determined. CO on the metal surfaces can be studied by conventional surface analysis methods, including Auger electron spectroscopy (AES) [13] and low energy electron diffraction (LEED) [14], while H₂ is hard to detect by these methods [15]. We can discuss the results for the metal nano contacts based on the understanding obtained for flat metal surfaces. Second, both electron donation and back donation from the CO molecule occur at the same time, which are important charge transfer mechanisms for the understanding of chemical interactions between a molecule and a metal. In case of CO, the 5σ orbital (which is the highest occupied molecular orbital: HOMO) and $2\pi^*$ orbital (lowest unoccupied molecular orbital: LUMO) stay near the Fermi level of the metal, involving electron donation from the 5σ orbital to the metal, and back donation from the metal d band to the $2\pi^*$ orbital. Third, CO is a poisonous gas. If the conductance of the metal nano contact is changed in a specific way by CO, it may be applicable as CO gas sensors.

The effect of CO on the Pt nano contacts is discussed in more detail elsewhere [11,16]. The CO single molecule anchored between Pt leads was characterized by conductance measurement and point contact spectroscopy. In the present study, we report on the effect of CO on Ni, Cu, Pt, and Au nano contacts. While Au and Cu are noble metals, Ni and Pt are transition metals, for which the Fermi level lays inside the metal d band and back donation from the metal to the CO $2\pi^*$ orbital should play an important role. Reflecting the change in the chemical interaction the adsorption energy of CO on Ni, Pt, Cu, and Au flat surfaces decreases in that order [15]. We discuss the relationship between this adsorption character on macroscopic metal surfaces and the conductance behaviour of metal nano contacts. For Au nano contacts

we present a more detailed analysis of the conductance histograms and conductance traces.

II. EXPERIMENTAL

The measurements have been performed using the mechanically controllable break junction technique [3]. A small notch was cut at the middle of Ni, Cu, Pt, and Au wires in order to fix the breaking point. The wires used were 0.1 mm in diameter, about 1 cm long. The wire was glued on top of a bending beam and mounted in a three-point bending configuration inside a vacuum chamber. Once under vacuum and cooled to 4.2 K the wire was broken by mechanical bending of the substrate. Clean fracture surfaces are exposed by breaking and these remain clean for days in the cryogenic vacuum. The bending can be relaxed to form atomic-sized contacts between the wire ends using a piezo element for fine adjustment. CO was admitted via a home made capillary equipped with a heater wire running along the capillary that prevents premature condensation of the CO gas. After admitting a small amount of CO gas in the sample chamber we waited some time for the gas to diffuse to the end of the insert. About 3000 digitized conductance traces were used to build each conductance histogram in the present study.

III. RESULTS

Figure 1 shows the conductance histograms for Ni, Cu, Pt, and Au nano contacts before and after admitting CO. The conductance histograms are observed to change by admitting CO, most dramatically for Pt and Ni. For Pt, two new peaks appear in the conductance histogram, one near $0.5 G_0$ and one near $1 G_0$, in agreement with our previous studies [11,16]. A peak appears in the conductance histogram near $0.5 G_0$ for Ni. In both cases the peak for the clean metal that represents a single metal atom contact (at $1.6 G_0$ for Pt and $1.4 G_0$ for Ni) is suppressed after admission of CO. Weak features near $0.5 G_0$ also appear in the conductance histograms for Au and Cu, although the change is much smaller than for Pt and Ni.

For Pt, the $0.5 G_0$ feature is likely due to the conductance of a single CO molecule anchored between Pt electrodes [16,17]. For Ni, Cu, and Au, it is not clear whether the new feature near $0.5 G_0$ is due to the conductance of a single CO molecule, or whether it is due to the conductance of the metal nano wire whose surface is covered by CO. In both cases the conductance of the contact should vary with the type of metal because the electronic structure of the CO-metal bond depends strongly on the metal. Therefore, it is interesting to ob-

serve that a conductance feature near $0.5 G_0$ is found for all metals.

The importance of the changes in the conductance histograms for Ni, Pt, Cu, and Au decreases in that order. This order agrees with the adsorption properties of CO molecules on metal surfaces [15]. On transition metal (Ni, Pt) surfaces, the electron donation from the 5σ orbital to the metal and the back donation from the metal to the $2\pi^*$ orbital occur simultaneously, and a strong chemical bond is formed between the CO molecule and the metals. The present results show that the adsorption properties on macroscopic surfaces reflect the adsorption properties on atomic-scale metal nano structures. On the other hand, there is a difference in the adsorption properties between the macroscopic surface and the atomic scale nano structure. While a CO molecule does not adsorb chemically on macroscopic Au surfaces, CO molecules appear to coordinate to Au nano contacts judging from the change in the conductance histogram (Fig. 1(a)). Indeed, novel catalytic properties have been reported for Au nano particles [18]. Theoretical calculations support the idea that the Au nano contact is chemically active, with strong chemisorption of O_2 and CO [19].

For Au nano contacts we observed systematic changes in the conductance behaviour and reproducible conductance traces, characteristic of Au nano contacts in the presence of CO. For this reason we concentrate on Au nano contacts in the following. The conductance histogram changes with bias voltage, and the change is continuous and reversible (Fig. 2). The fractional conductance feature is clearly observed at low bias voltage, and its intensity decreases with bias voltage. Figure 3 shows the intensity of the fractional feature normalized to the intensity of the peak at $1 G_0$, plotted as a function of the bias voltage. The fractional conductance feature gradually decreases and disappears at a bias voltage of about 200 mV, indicating that the structure having a fractional conductance is unstable at high bias voltage, suggesting that the interaction between the CO molecule and the Au nano contact is weak. It is noteworthy that the fractional conductance feature appears at low bias voltage, even after it first disappeared at high bias voltage. This indicates that the CO molecule is not blown off the surface but remains bound to one of the two electrodes at high bias voltage.

In order to find evidence as to how the CO molecule is adsorbed on, or incorporated into the Au nano wire, we have analysed the conductance traces. Figure 4 shows typical breaking and return traces for Au after admitting CO. The stretching length was calibrated with the length histogram of the last conductance plateau for clean Au [20]. There are three characteristics in the conductance traces. The last plateau, by which we mean the part having a conductance near $1 G_0$, extends to quite long length; the conductance drops abruptly just before breaking to about $0.5 G_0$; and the conductance smoothly increases

with further stretching on this fractional conductance plateau. These characteristics are observed reproducibly and they are typical for Au nano contact in the presence of CO. In the following these characters are discussed.

First, we discuss the length of the Au nano contact. Figure 5 shows the length histogram of the last conductance plateau for Au after admitting CO. The length of the last plateau is taken here as the distance between the points at which the conductance drops below $1.2 G_0$ and $0.2 G_0$, respectively. A conductance at $1 G_0$ corresponds to a clean Au monatomic contact or chain of Au atoms. The $1G_0$ -plateau was observed to stretch up to 1 nm in length. Figure 6 shows the average of the return distance as a function of the length of the last plateau. Apart from an offset of 0.5nm due to the elastic response of the banks [2], the relation is approximately 1:1, suggesting that a fragile structure is formed with a length corresponding to that of the last plateau, which is unable to support itself when it breaks and collapses onto the banks on either side. The long plateaux of over 1 nm length and the 1:1 relation were also observed for clean Au monatomic wires [2], supporting the formation of the monatomic wire in the present case. While clean Au forms a monatomic wire under UHV at low temperature the results show that Au monatomic wires also form in the presence of CO.

Second, we discuss the change in conductance during the breaking process. The conductance drops abruptly down to about $0.5 G_0$ just before breaking the contact, which produces a fractional feature in the conductance histogram. This conductance drop should be caused by the adsorption of CO on the Au nano wire or incorporation of CO into the Au wire because it is not observed for clean Au. It should be noticed that the wire breaks once the conductance has dropped to about $0.5 G_0$. For Pt in the presence of H_2 and Ag in the presence of O_2 , the conductance decreases stepwise after the conductance drops from $1 G_0$, and the contact can be stretched further [21,22]. This indicates that CO adsorption or incorporation destabilized the Au nano wire.

The destabilization mechanism of the Au nano wire by CO we will now discuss in terms of the charge transfer between the CO molecule and Au, and in relation to the stabilization mechanism of the Au monatomic wire. The Au d band is located below the Fermi level, and thus, the electron back donation from the Au d band to $2\pi^*$ orbital of CO does not play an important role. The donation from the 5σ orbital of CO to the metal is dominant, and the electron would be transferred from CO to Au. The charge transfer between CO and Au was studied for Au nano particles deposited on TiO_2 , which showed novel catalytic properties [23]. Adsorption of CO on Au particles induces charge transfer from Au to TiO_2 , suggesting that the electron is transferred from CO to Au. A monatomic wire is formed only for 5d metal as a result of the following mechanism. For 5 d metals, the s oc-

cupation increases at the expense of the d electrons due to relativistic effects in electronic structure. Since the top of the d band consists of states with anti-bonding character that are now partially depleted, the d bond becomes stronger. While the d electrons tend to compress the lattice, the s electrons exert an opposing Fermi pressure. At the surface, the spill out of the s electron cloud into the vacuum relieves some of the s electron pressure, and allows a strengthening of the bonds at the surface. The monatomic wire geometry allows for an even larger s pressure relief. Therefore, the bond in the wire is much stronger than the bond in the bulk, and monatomic wires are formed for 5d metals, Ir, Pt and Au [3,24]. When CO adsorbs on the surface of the Au monatomic wire, spill out of the s electron cloud into the vacuum will be inhibited. Furthermore, the density of states (DOS) near the Fermi level with anti-bonding character will increase due to the charge transfer from CO to Au. These mechanisms will decrease the bond strength of the Au in the wire, and the Au monatomic wire will be destabilized by CO adsorption or incorporation.

Third, we discuss the increase in conductance with the stretch length after the conductance drops down to near $0.5 G_0$. A similar increase in the conductance with elongation is observed for Al nano contacts [25], and for Au nano contacts in the presence of H_2 [26]. The former is explained by the change in DOS at Fermi level. The elongation of the Al contact induces a narrowing the s_{pz} band, leading to an increase in the DOS at the Fermi level, and a concomitant increase in the conductance. The latter (the effect for Au+ H_2) was explained as due to a gradual change in the molecular orientation. Barnett et al. used density functional theory (DFT) to calculate the conductance of the various atomic configurations, including a system having a H_2 molecule incorporated into a Au monatomic wire. The conductance of the perpendicular configuration, for which the molecular axis is perpendicular to the contact axis, was calculated to be about $0.1 G_0$, and the conductance of the parallel configuration increased up to $0.25 G_0$ [27]. Based on these calculation results the increase in conductance was explained by the change in configuration of hydrogen molecule. The H_2 molecule incorporates into the Au wire in the perpendicular configuration and the molecule turns toward an orientation parallel to the contact axis, which shows up as an increasing conductance as the electrodes are pulled apart. The present results may be explained by both a change in the DOS or a changing orientation of the CO molecule. Recent DFT calculation results for Pt nano contacts in the presence of CO show a slight increase in the conductance with the elongation [17], and this mechanism may also apply to Au in the presence of CO.

IV. CONCLUSIONS

We have studied the conductance of Ni, Cu, Pt, and Au nano contacts in the presence of CO. In all cases a fractional conductance feature appears in the conductance histogram near $0.5 G_0$ after admitting CO. The change in the conductance histogram for Ni, Pt, Cu, and Au decreases in that order, in agreement with the adsorption properties on macroscopic metal surfaces. For Au, the intensity of the fractional conductance feature continuously and reversibly changes with the bias voltage. The feature disappears at a bias voltage of 200 mV, indicating that the CO-Au bond is weak. The results give evidence that Au atomic chain formation persists in the presence of CO, but bonding of a CO molecule weakens the chain and gives rise to a drop of the conductance to about $0.5 G_0$.

ACKNOWLEDGMENTS

This work is part of the research program of the Stichting voor Fundamenteel Onderzoek der Materie (FOM), which is financially supported by NOW..MK has been supported by the Yamada Science Foundation.

[1] Ohnishi H, Kondo Y and Takayanagi K 1998 Nature **395** 780
 [2] Yanson A I, Bollinger G R, van den Brom H E, Agrait N and van Ruitenbeek J M 1998 Nature **395** 783
 [3] Agrait N, Levy Yeyati A and van Ruitenbeek J M 2003 Phys. Rep. **377** 81
 [4] Li C Z, He H X, Bogozi A, Bunch J S and Tao N J 2000 Appl. Phys. Lett. **76** 1333
 [5] Reed M A, Zhou C, Muller C J, Burgin T P and Tour J M 1997 Science **278** 252
 [6] For example, van Ruitenbeek J M, Scheer E and Weber H 2005 Introducing Molecular Electronics ed G Cuniberti, G Fagas and K Richter (Heidelberg: Springer) p253
 [7] Smit R H M, Noat Y, Untiedt C, Lang N D, van Hemert M C and van Ruitenbeek J M 2002 Nature **419** 906
 [8] Djukic D, Thygesen K S, Untiedt C, Smit R H M, Jacobsen K W and van Ruitenbeek J M 2005 Phys. Rev. B **71** 161402; Djukic D and van Ruitenbeek J M 2006 Nano Lett. **6** 789
 [9] Park, J.; Pasupathy, A. N.; Goldsmith, J. I.; Chang, C.; Yaish, Y.; Petta, J. R.; Rinkoski, M.; Sethna, J. P.; Abruna, H. D.; McEuen, D. Nature 2002, **417**, 722?725; Liang, W.; Shores, M.P.; Bockrath, M.; Long, J. R.; Park, H. Nature 2002, **417**, 725?729.
 [10] Csonka Sz, Halbritter A, Mihaly G, Jurdik E, Shklyarevskii O I, Speller S and van Kempen H 2003 Phys. Rev. Lett. **90** 116803

[11] Untiedt C, Dekker D M T, Djukic D and van Ruitenbeek J M 2004 Phys. Rev. B **69** 081401
 [12] Csonka Sz, Halbritter A, Mihaly G, Shklyarevskii O I, Speller S, and van Kempen H 2004 Phys. Rev. Lett. **93** 16802
 [13] Carlson T A 1975 Photoelectron and Auger spectroscopy (New York: Plenum)
 [14] van Hove M A and Tong S Y 1979 Surface Crystallography by LEED (Heidelberg: Springer)
 [15] Zangwill A 1988 Physics at Surfaces (Cambridge: Cambridge University Press)
 [16] Djukic D et al. in preparation.
 [17] Strange M, Thygesen K S and Jacobsen K W 2006 Phys. Rev. B **73** 125424
 [18] Haruta M 2003 Chem. Record **3** 75
 [19] Bahn S R, Lopez N, Norskov J K and Jacobsen K W 2002 Phys. Rev. B **66** 81405
 [20] . The conductance traces are obtained as a function of piezo voltage. It is reported in [2] that the length histogram of the last conductance plateau for clean Au, which is defined as having a conductance between $1.3 G_0$ and $0.7 G_0$, shows a number of equidistant maxima, at multiples of 0.257 nm [3]. We use this to determine the ratio between the relative change in piezo voltage with respect to the stretch length, assuming that the inter-peak distance is 0.26 nm in the length histogram for clean Au. The stretch length was calibrated in this way with clean Au before each measurement of the Au in the presence of CO.
 [21] Thijssen W H A, Marjenburgh D, Bremmer R H, and van Ruitenbeek J M 2006 Phys. Rev. Lett. **96** 026806
 [22] Kiguchi M et al. unpublished results
 [23] Toyoshima I and Somorjai G A 1979 Cat. Rev. Sci. Eng. **19** 105
 [24] Smit R H M, Untiedt C, Yanson A I and van Ruitenbeek J M 2001 Phys. Rev. Lett. **87** 266102
 [25] Cuevas J C, Levy Yeyati A, Martin-Rodero A, Rubio Bollinger G, Untiedt C and Agrait N 1998 Phys. Rev. Lett. **81** 2990
 [26] Csonka Sz, Halbritter A and Mihaly G 2006 Phys. Rev. B **73** 075405
 [27] Barnett R N, Hakkinen H, Scherbakov A G and Landman U 2004 Nano Lett. **4** 1845

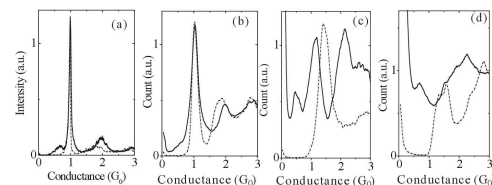


FIG. 1. Conductance histograms for (a) Au, (b) Cu, (c) Pt and (d) Ni atomic-size contacts before (dotted-line) and after (thick line) admitting CO. The bias voltage is (a) 0.03 V, (b) 0.05 V, (c) 0.15 V and (d) 0.2 V.

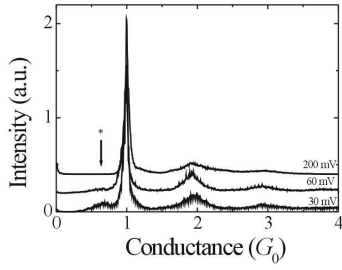


FIG. 2. Bias voltage dependence of conductance histograms for Au atomic-size contacts after admitting CO for various values of the bias voltage.

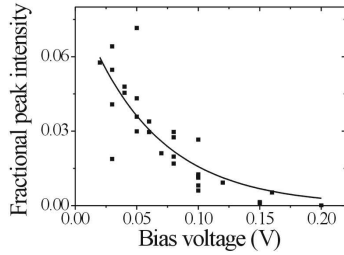


FIG. 3. Intensity of the fractional feature in the histograms normalized to the intensity of the peak at $1 G_0$, plotted as a function of bias voltage for Au atomic-size contacts after admitting CO.

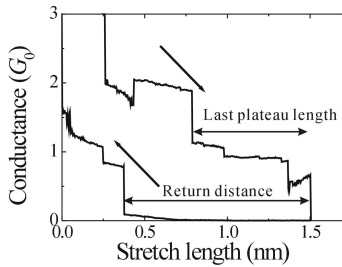


FIG. 4. Typical breaking and return traces for Au after admitting CO recorded at a bias voltage of 100 mV. The length of the last plateau is defined as the distance between the points at which the conductance drops below $1.2 G_0$ and $0.2 G_0$, respectively.

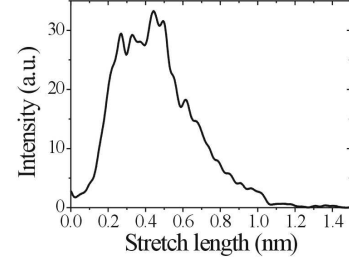


FIG. 5. The length histogram of the last conductance plateau as defined in Fig. 4. The histogram is obtained from 3000 experiments recorded at a bias voltage of 100 mV.

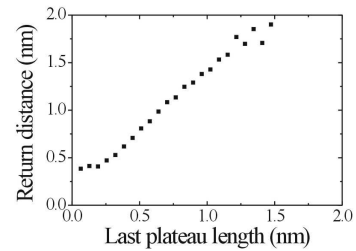


FIG. 6. The average of the return distance as a function of the length of the last plateau as defined in Fig. 4 recorded at a bias voltage of 100 mV.