



Universiteit
Leiden
The Netherlands

Valley-momentum locking in a graphene superlattice with Y-shaped Kekulé bond texture

Gamayun, O.; Ostroukh, V.; Gnezdilov, N.; Adagideli, I.; Beenakker, C.W.J.

Citation

Gamayun, O., Ostroukh, V., Gnezdilov, N., Adagideli, I., & Beenakker, C. W. J. (2018). Valley-momentum locking in a graphene superlattice with Y-shaped Kekulé bond texture. *New Journal Of Physics*, 20, 023016. doi:10.1088/1367-2630/aaa7e5

Version: Not Applicable (or Unknown)

License: [Leiden University Non-exclusive license](#)

Downloaded from: <https://hdl.handle.net/1887/68667>

Note: To cite this publication please use the final published version (if applicable).

PAPER • OPEN ACCESS

Valley-momentum locking in a graphene superlattice with Y-shaped Kekulé bond texture

To cite this article: O V Gamayun *et al* 2018 *New J. Phys.* **20** 023016

View the [article online](#) for updates and enhancements.

Recent citations

- [Opening a band gap in graphene by C–C bond alternation: a tight binding approach](#)
Doan Q Khoa *et al*
- [Generation of valley pump currents in silicene](#)
John Tombe Jada Marcellino *et al*
- [Topological magnon insulator with a Kekulé bond modulation](#)
Pierre A Pantaleón *et al*



IOP | ebooks™

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.



PAPER

Valley-momentum locking in a graphene superlattice with Y-shaped Kekulé bond texture

OPEN ACCESS

RECEIVED

11 October 2017

REVISED

12 January 2018

ACCEPTED FOR PUBLICATION

15 January 2018

PUBLISHED

7 February 2018

Original content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/4.0/).

Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

O V Gamayun^{1,3}, V P Ostroukh¹, N V Gnezdilov¹, İ Adagideli² and C W J Beenakker¹ ¹ Instituut-Lorentz, Universiteit Leiden, PO Box 9506, 2300 RA Leiden, The Netherlands² Faculty of Engineering and Natural Sciences, Sabanci University, Orhanli-Tuzla, 34956 Istanbul, Turkey³ Author to whom any correspondence should be addressed.E-mail: o.gamayun@uva.nl**Keywords:** graphene, Kekule distortion, valley-momentum locking, massless Dirac fermions**Abstract**

Recent experiments by Gutiérrez *et al* (2016 *Nat. Phys.* **12** 950) on a graphene–copper superlattice have revealed an unusual Kekulé bond texture in the honeycomb lattice—a Y-shaped modulation of weak and strong bonds with a wave vector connecting two Dirac points. We show that this so-called ‘Kek-Y’ texture produces two species of massless Dirac fermions, with valley isospin locked parallel or antiparallel to the direction of motion. In a magnetic field B , the valley degeneracy of the B -dependent Landau levels is removed by the valley-momentum locking but a B -independent and valley-degenerate zero-mode remains.


1. Introduction

The coupling of orbital and spin degrees of freedom is a promising new direction in nano-electronics, referred to as ‘spin-orbitronics’, that aims at non-magnetic control of information carried by charge-neutral spin currents [1–3]. Graphene offers a rich platform for this research [4, 5], because the conduction electrons have three distinct spin quantum numbers: in addition to the spin magnetic moment $s = \pm 1/2$, there is the sublattice pseudospin $\sigma = A, B$ and the valley isospin $\tau = K, K'$. While the coupling of the electron spin s to its momentum p is a relativistic effect, and very weak in graphene, the coupling of σ to p is so strong that one has a pseudospin-momentum locking: the pseudospin points in the direction of motion, as a result of the helicity operator $\mathbf{p} \cdot \boldsymbol{\sigma} \equiv p_x \sigma_x + p_y \sigma_y$ in the Dirac Hamiltonian of graphene.

The purpose of this paper is to propose a way to obtain a similar handle on the valley isospin, by adding a term $\mathbf{p} \cdot \boldsymbol{\tau}$ to the Dirac Hamiltonian, which commutes with the pseudospin helicity and locks the valley to the direction of motion. We find that this valley-momentum locking should appear in a superlattice that has recently been realized experimentally by Gutiérrez *et al* [6, 7]: a superlattice of graphene grown epitaxially onto Cu(111), with the copper atoms in registry with the carbon atoms. One of six carbon atoms in each superlattice unit cell ($\sqrt{3} \times \sqrt{3}$ larger than the original graphene unit cell) have no copper atoms below them and acquire a shorter nearest-neighbor bond. The resulting Y-shaped periodic alternation of weak and strong bonds (see figure 1) is called a Kekulé-Y (Kek-Y) ordering, with reference to the Kekulé dimerization in a benzene ring (called Kek-O in this context) [7].

The Kek-O and Kek-Y superlattices have the same Brillouin zone, with the K and K' valleys of graphene folded on top of each other. The Kek-O ordering couples the valleys by opening a gap in the Dirac cone [8–12], and it was assumed by Gutiérrez *et al* that the same applies to the Kek-Y ordering [6, 7]. While it is certainly possible that the graphene layer in the experiment is gapped by the epitaxial substrate (for example, by a sublattice-symmetry breaking ionic potential [13–15]), we find that the Y-shaped Kekulé bond ordering by itself does not impose a mass on the Dirac fermions⁴. Instead, the valley degeneracy is broken by the helicity operator

⁴ That the Kek-Y bond ordering by itself preserves the massless nature of the Dirac fermions in graphene could already have been deduced from [15] (it is a limiting case of their equation (4)), although it was not noticed in the experiment [6]. We thank Dr Gutiérrez for pointing this out to us.

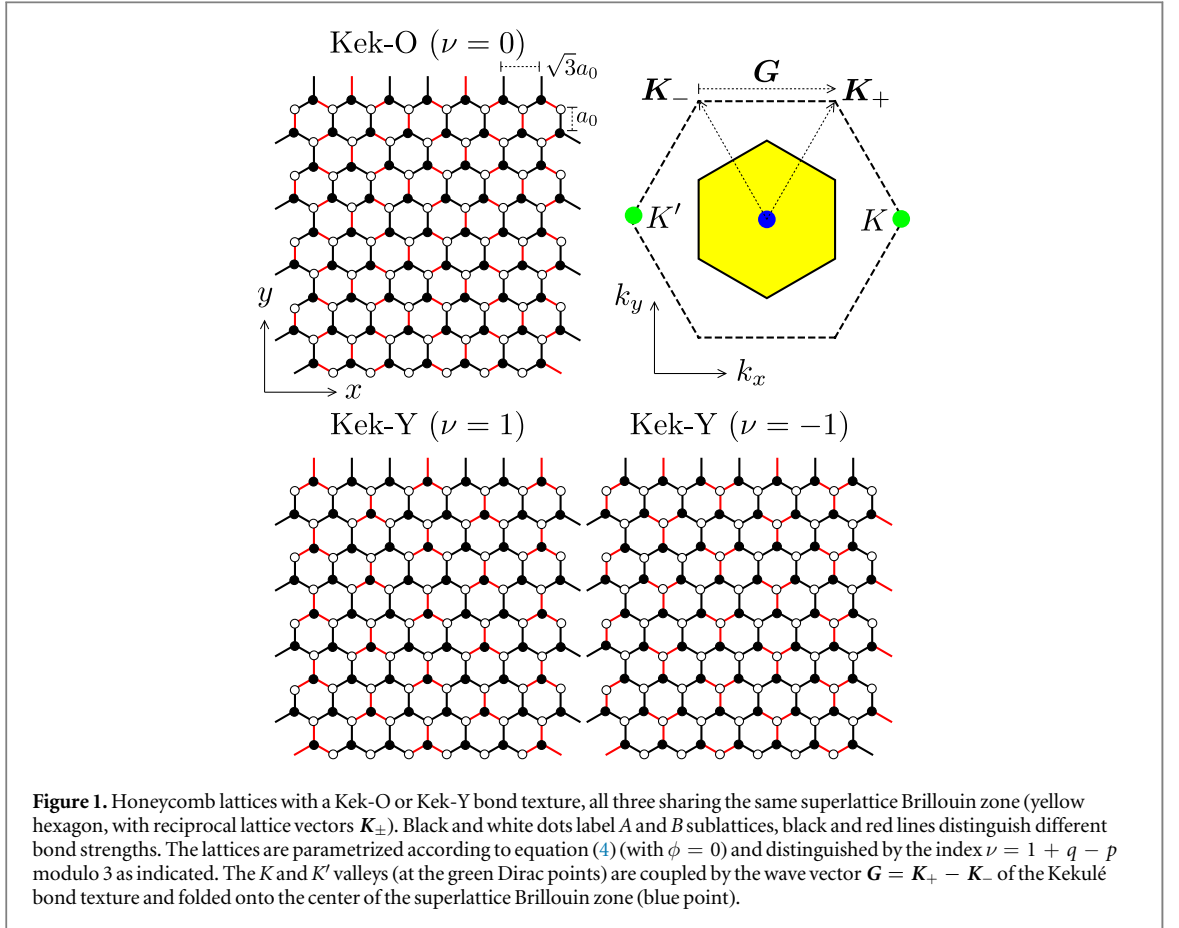

$\mathbf{p} \cdot \boldsymbol{\tau}$, which preserves the gapless Dirac point while locking the valley degree of freedom to the momentum. In a magnetic field the valley-momentum locking splits all Landau levels except for the zeroth Landau level, which remains pinned to zero energy.

2. Tight-binding model

2.1. Real-space formulation

A monolayer of carbon atoms has the tight-binding Hamiltonian

$$H = -\sum_{\mathbf{r}} \sum_{\ell=1}^3 t_{r,\ell} a_{\mathbf{r}}^{\dagger} b_{\mathbf{r}+\mathbf{s}_{\ell}} + \text{H.c.}, \quad (1)$$

describing the hopping with amplitude $t_{r,\ell}$ between an atom at site $\mathbf{r} = n\mathbf{a}_1 + m\mathbf{a}_2$ ($n, m \in \mathbb{Z}$) on the A sublattice (annihilation operator $a_{\mathbf{r}}$) and each of its three nearest neighbors at $\mathbf{r} + \mathbf{s}_{\ell}$ on the B sublattice (annihilation operator $b_{\mathbf{r}+\mathbf{s}_{\ell}}$). The lattice vectors are defined by $\mathbf{s}_1 = \frac{1}{2}(\sqrt{3}, -1)$, $\mathbf{s}_2 = -\frac{1}{2}(\sqrt{3}, 1)$, $\mathbf{s}_3 = (0, 1)$, $\mathbf{a}_1 = \mathbf{s}_3 - \mathbf{s}_1$, $\mathbf{a}_2 = \mathbf{s}_3 - \mathbf{s}_2$. All lengths are measured in units of the unperturbed C-C bond length $a_0 \equiv 1$.

For the uniform lattice, with $t_{r,\ell} \equiv t_0$, the band structure is given by [16]

$$E(\mathbf{k}) = \pm|\varepsilon(\mathbf{k})|, \quad \varepsilon(\mathbf{k}) = t_0 \sum_{\ell=1}^3 e^{i\mathbf{k}\cdot\mathbf{s}_{\ell}}. \quad (2)$$

There is a conical singularity at the Dirac points $\mathbf{K}_{\pm} = \frac{2}{9}\pi\sqrt{3}(\pm 1, \sqrt{3})$, where $E(\mathbf{K}_{\pm}) = 0$. For later use we note the identities

$$\varepsilon(\mathbf{k}) = \varepsilon(\mathbf{k} + 3\mathbf{K}_{\pm}) = e^{2\pi i/3}\varepsilon(\mathbf{k} + \mathbf{K}_+ + \mathbf{K}_-). \quad (3)$$

The bond-density wave that describes the Kek-O and Kek-Y textures has the form

$$\begin{aligned} t_{r,\ell}/t_0 &= 1 + 2 \operatorname{Re} [\Delta e^{i(p\mathbf{K}_+ + q\mathbf{K}_-) \cdot \mathbf{s}_\ell + i\mathbf{G} \cdot \mathbf{r}}] \\ &= 1 + 2\Delta_0 \cos \left[\phi + \frac{2}{3}\pi(m - n + N_\ell) \right], \end{aligned} \quad (4a)$$

$$N_1 = -q, \quad N_2 = -p, \quad N_3 = p + q, \quad p, q \in \mathbb{Z}_3. \quad (4b)$$

The Kekulé wave vector

$$\mathbf{G} \equiv \mathbf{K}_+ - \mathbf{K}_- = \frac{4}{9}\pi\sqrt{3}(1, 0) \quad (5)$$

ouples the Dirac points. The coupling amplitude $\Delta = \Delta_0 e^{i\phi}$ may be complex, but the hopping amplitudes $t_{r,\ell}$ are real in order to preserve time-reversal symmetry. (We note that our definition of Δ differs by a factor 3 from that of [8].)

As illustrated in figure 1, the index

$$\nu = 1 + q - p \pmod{3} \quad (6)$$

distinguishes the Kek-O texture ($\nu = 0$) from the Kek-Y texture ($\nu = \pm 1$). Each Kekulé superlattice has a $2\pi/3$ rotational symmetry, reduced from the $2\pi/6$ symmetry of the graphene lattice. The two $\nu = \pm 1$ Kek-Y textures are each others mirror image⁵.

2.2. Transformation to momentum space

The Kek-O and Kek-Y superlattices have the same hexagonal Brillouin zone, with reciprocal lattice vectors \mathbf{K}_\pm —smaller by a factor $1/\sqrt{3}$ and rotated over 30° with respect to the original Brillouin zone of graphene (see figure 1). The Dirac points of unperturbed graphene are folded from the corner to the center of the Brillouin zone and coupled by the bond-density wave.

To study the coupling we Fourier transform the tight-binding Hamiltonian (1),

$$\begin{aligned} H(\mathbf{k}) &= -\varepsilon(\mathbf{k})a_k^\dagger b_k - \Delta\varepsilon(\mathbf{k} + p\mathbf{K}_+ + q\mathbf{K}_-)a_{\mathbf{k}+\mathbf{G}}^\dagger b_k \\ &\quad - \Delta^*\varepsilon(\mathbf{k} - p\mathbf{K}_+ - q\mathbf{K}_-)a_{\mathbf{k}-\mathbf{G}}^\dagger b_k + \text{H.c.} \end{aligned} \quad (7)$$

The momentum \mathbf{k} still varies over the original Brillouin zone. In order to restrict it to the superlattice Brillouin zone we collect the annihilation operators at \mathbf{k} and $\mathbf{k} \pm \mathbf{G}$ in the column vector $c_k = (a_k, a_{\mathbf{k}-\mathbf{G}}, a_{\mathbf{k}+\mathbf{G}}, b_k, b_{\mathbf{k}-\mathbf{G}}, b_{\mathbf{k}+\mathbf{G}})$ and write the Hamiltonian in a 6×6 matrix form:

$$H(\mathbf{k}) = -c_k^\dagger \begin{pmatrix} 0 & \mathcal{E}_\nu(\mathbf{k}) \\ \mathcal{E}_\nu^\dagger(\mathbf{k}) & 0 \end{pmatrix} c_k, \quad (8a)$$

$$\mathcal{E}_\nu = \begin{pmatrix} \varepsilon_0 & \tilde{\Delta}\varepsilon_{\nu+1} & \tilde{\Delta}^*\varepsilon_{-\nu-1} \\ \tilde{\Delta}^*\varepsilon_{1-\nu} & \varepsilon_{-1} & \tilde{\Delta}\varepsilon_\nu \\ \tilde{\Delta}\varepsilon_{\nu-1} & \tilde{\Delta}^*\varepsilon_{-\nu} & \varepsilon_1 \end{pmatrix}, \quad (8b)$$

$$\tilde{\Delta} = e^{2\pi i(p+q)/3}\Delta, \quad \varepsilon_n = \varepsilon(\mathbf{k} + n\mathbf{G}), \quad (8c)$$

where we used equation (3).

3. Low-energy Hamiltonian


3.1. Gapless spectrum

The low-energy spectrum is governed by the four modes $u_k = (a_{\mathbf{k}-\mathbf{G}}, a_{\mathbf{k}+\mathbf{G}}, b_{\mathbf{k}-\mathbf{G}}, b_{\mathbf{k}+\mathbf{G}})$, which for small \mathbf{k} lie near the Dirac points at $\pm\mathbf{G}$. (We identify the K valley with $+\mathbf{G}$ and the K' valley with $-\mathbf{G}$.) Projection onto this subspace reduces the six-band Hamiltonian (8) to an effective four-band Hamiltonian,

$$H_{\text{eff}} = -u_k^\dagger \begin{pmatrix} 0 & h_\nu \\ h_\nu^\dagger & 0 \end{pmatrix} u_k, \quad h_\nu = \begin{pmatrix} \varepsilon_{-1} & \tilde{\Delta}\varepsilon_\nu \\ \tilde{\Delta}^*\varepsilon_{-\nu} & \varepsilon_1 \end{pmatrix}. \quad (9)$$

Corrections to the low-energy spectrum from virtual transitions to the higher bands are of order Δ_0^2 . We will include these corrections later, but for now assume $\Delta_0 \ll 1$ and neglect them.

⁵ There are three sets of integers $p, q \in \mathbb{Z}_3$ for a given index $\nu = 1 + q - p \pmod{3}$, corresponding to textures on the honeycomb lattice that are translated by one hexagon, or equivalently related by a $\pm 2\pi/3$ phase shift of Δ .

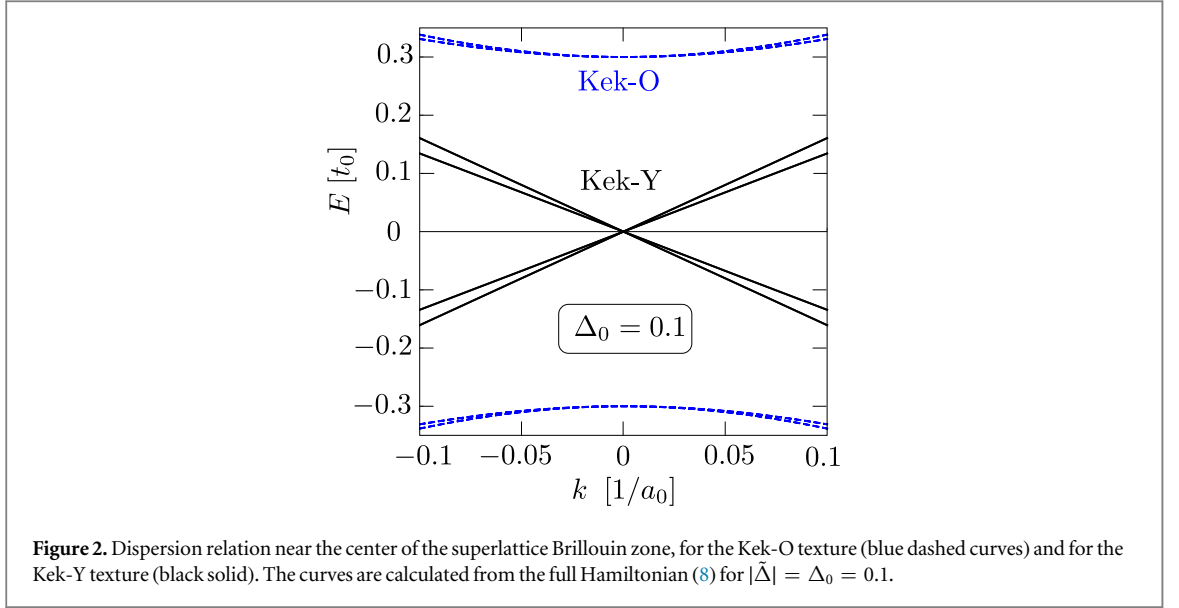

The \mathbf{k} -dependence of ε_n may be linearized near $\mathbf{k} = 0$,

$$\varepsilon_0 = 3t_0, \quad \varepsilon_{\pm 1} = \hbar v_0(\mp k_x + i k_y) + \text{order}(k^2), \quad (10)$$

with Fermi velocity $v_0 = \frac{3}{2}t_0 a_0 / \hbar$. The corresponding 4-component Dirac equation has the form

$$\mathcal{H} \begin{pmatrix} \Psi_{K'} \\ \Psi_K \end{pmatrix} = E \begin{pmatrix} \Psi_{K'} \\ \Psi_K \end{pmatrix}, \quad \mathcal{H} = \begin{pmatrix} v_0 \mathbf{p} \cdot \boldsymbol{\sigma} & \tilde{\Delta} Q_\nu \\ \tilde{\Delta}^* Q_\nu^\dagger & v_0 \mathbf{p} \cdot \boldsymbol{\sigma} \end{pmatrix}, \quad (11a)$$

$$\Psi_{K'} = \begin{pmatrix} -\psi_{B,K'} \\ \psi_{A,K'} \end{pmatrix}, \quad \Psi_K = \begin{pmatrix} \psi_{A,K} \\ \psi_{B,K} \end{pmatrix}, \quad (11b)$$

$$Q_\nu = \begin{pmatrix} \varepsilon_{-\nu}^* & 0 \\ 0 & -\varepsilon_\nu \end{pmatrix} = \begin{cases} 3t_0 \sigma_z & \text{if } \nu = 0, \\ v_0(\nu p_x - i p_y) \sigma_0 & \text{if } |\nu| = 1. \end{cases} \quad (11c)$$

The spinor Ψ_K contains the wave amplitudes on the A and B sublattices in valley K and similarly $\Psi_{K'}$ for valley K' , but note the different ordering of the components [17]⁶. We have defined the momentum operator $\mathbf{p} = -i\hbar \partial / \partial \mathbf{r}$, with $\mathbf{p} \cdot \boldsymbol{\sigma} = p_x \sigma_x + p_y \sigma_y$. The Pauli matrices $\sigma_x, \sigma_y, \sigma_z$, with σ_0 the unit matrix, act on the sublattice degree of freedom.

For the Kek-O texture we recover the gapped spectrum of Kekulé dimerized graphene [8],

$$E^2 = v_0^2 |\mathbf{p}|^2 + (3t_0 \Delta_0)^2 \quad \text{for } \nu = 0. \quad (12)$$

The Kek-Y texture, instead, has a gapless spectrum,

$$E_\pm^2 = v_0^2 (1 \pm \Delta_0)^2 |\mathbf{p}|^2, \quad \text{for } |\nu| = 1, \quad (13)$$

consisting of a pair of linearly dispersing modes with different velocities $v_0(1 \pm \Delta_0)$. The two qualitatively different dispersions are contrasted in figure 2.

3.2. Valley-momentum locking


The two gapless modes in the Kek-Y superlattice are helical, with both the sublattice pseudospin and the valley isospin locked to the direction of motion. To see this, we consider the $\nu = 1$ Kek-Y texture with a real $\tilde{\Delta} = \Delta_0$. (Complex $\tilde{\Delta}$ and $\nu = -1$ are equivalent upon a unitary transformation.) The Dirac Hamiltonian (11) can be written in the compact form

$$\mathcal{H} = v_\sigma (\mathbf{p} \cdot \boldsymbol{\sigma}) \otimes \tau_0 + v_\tau \sigma_0 \otimes (\mathbf{p} \cdot \boldsymbol{\tau}), \quad (14)$$

with the help of a second set of Pauli matrices τ_x, τ_y, τ_z and unit matrix τ_0 acting on the valley degree of freedom⁷. The two velocities are defined by $v_\sigma = v_0$ and $v_\tau = v_0 \Delta_0$.

⁶ The ordering of the spinor components in equation (11b) is the so-called valley-isotropic representation of Dirac fermions.

⁷ For reference, we note that the unitary transformation from $\Psi = (-\psi_{B,K'}, \psi_{A,K'}, \psi_{A,K}, \psi_{B,K})$ to $\Psi' = (\psi_{B,K'}, \psi_{A,K'}, \psi_{A,K}, \psi_{B,K})$ transforms $H = v_\sigma (\mathbf{p} \cdot \boldsymbol{\sigma}) \otimes \tau_0 + v_\tau \sigma_0 \otimes (\mathbf{p} \cdot \boldsymbol{\tau})$ into $\mathcal{H} = -v_\sigma (\mathbf{p} \cdot \boldsymbol{\sigma}) \otimes \tau_z + v_\tau \sigma_z \otimes (\mathbf{p} \cdot \boldsymbol{\tau})$.

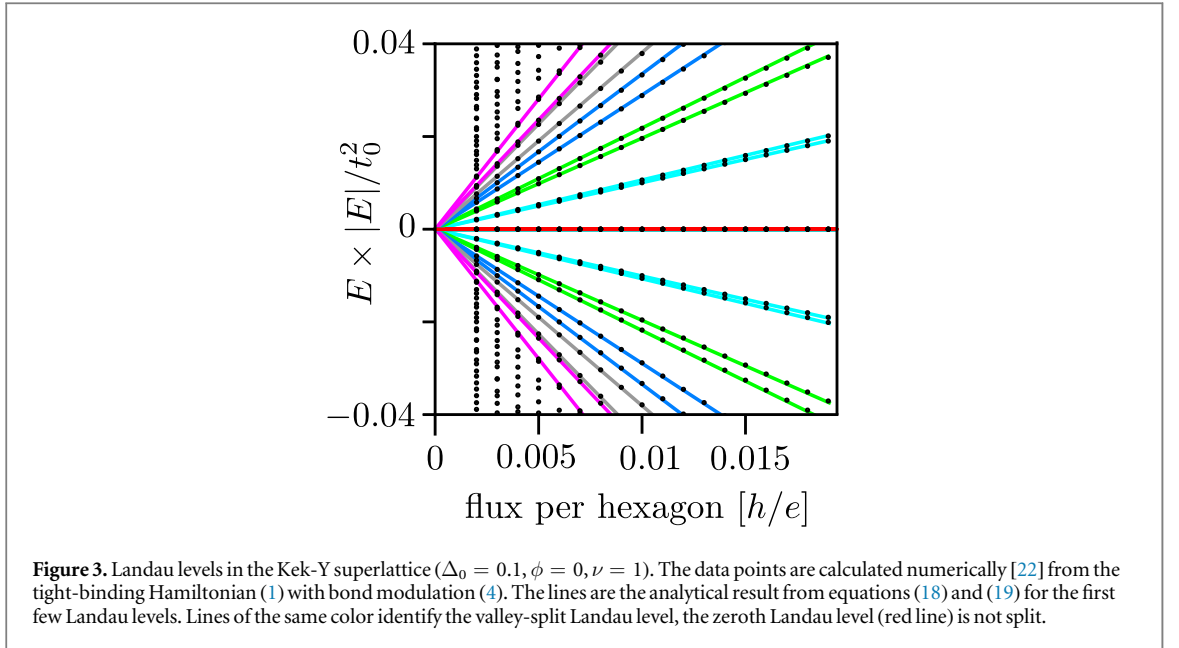

An eigenstate of the current operator

$$j_\alpha = \partial \mathcal{H} / \partial p_\alpha = v_\sigma \sigma_\alpha \otimes \tau_0 + v_\tau \sigma_0 \otimes \tau_\alpha \quad (15)$$

with eigenvalue $v_\sigma \pm v_\tau$ is an eigenstate of σ_α with eigenvalue ± 1 and an eigenstate of τ_α with eigenvalue ± 1 . (The two Pauli matrices act on different degrees of freedom, so they commute and can be diagonalized independently.) This valley-momentum locking does not violate time-reversal symmetry, since the time-reversal operation in the superlattice inverts all three vectors \mathbf{p} , $\boldsymbol{\sigma}$, and $\boldsymbol{\tau}$, and hence leaves \mathcal{H} unaffected⁸:

$$(\sigma_y \otimes \tau_y) \mathcal{H}^* (\sigma_y \otimes \tau_y) = \mathcal{H}. \quad (16)$$

The valley-momentum locking does break the sublattice symmetry, since \mathcal{H} no longer anticommutes with σ_z , but another chiral symmetry involving both sublattice and valley degrees of freedom remains:

$$(\sigma_z \otimes \tau_z) \mathcal{H} = -\mathcal{H} (\sigma_z \otimes \tau_z). \quad (17)$$

3.3. Landau level quantization

A perpendicular magnetic field B in the z -direction (vector potential \mathbf{A} in the x - y plane), breaks the time-reversal symmetry (16) via the substitution $\mathbf{p} \mapsto -i\hbar \partial / \partial \mathbf{r} + e\mathbf{A}(\mathbf{r}) \equiv \boldsymbol{\Pi}$. The chiral symmetry (17) is preserved, so the Landau levels are still symmetrically arranged around $E = 0$, as in unperturbed graphene. Because the two helicity operators $\boldsymbol{\Pi} \cdot \boldsymbol{\sigma}$ and $\boldsymbol{\Pi} \cdot \boldsymbol{\tau}$ do not commute for $\mathbf{A} \neq 0$, they can no longer be diagonalized independently. In particular, this means the Landau level spectrum is not simply a superposition of two spectra of Dirac fermions with different velocities.

It is still possible to calculate the spectrum analytically (see appendix A). We find Landau levels at energies $E_n^+, E_n^-, -E_n^+, -E_n^-, n = 0, 1, 2, \dots$, given by

$$E_n^\pm = E_B [2n + 1 \pm \sqrt{1 + n(n+1)(4v_\sigma v_\tau)^2 \bar{v}^{-4}}]^{1/2}, \quad (18)$$

with the definitions $\bar{v} = \sqrt{v_\sigma^2 + v_\tau^2}$ and $E_B = \bar{v} \sqrt{\hbar e B}$.

In unperturbed graphene all Landau levels have a twofold valley degeneracy⁹: $E_n^+ = E_{n+1}^-$ for $v_\tau = 0$. This includes the zeroth Landau level: $E_0^- = 0 = -E_0^+$. A nonzero v_τ breaks the valley degeneracy of all Landau levels at $E \neq 0$, but a valley-degenerate zero-mode $E_0^- = 0$ remains, see figure 3.

The absence of a splitting of the zeroth Landau level can be understood as a topological protection in the context of an index theorem [18–21], which requires that either $\Pi_+ \equiv \Pi_x + i\Pi_y$ or $\Pi_- \equiv \Pi_x - i\Pi_y$ has a zero-mode. If we decompose $\mathcal{H} = \Pi_+ S_- + \Pi_- S_+$, with $S_\pm = v_\sigma (\sigma_x \pm i\sigma_y) + v_\tau (\tau_x \pm i\tau_y)$, we see that both S_+ and

⁸ The time-reversal operation $\mathcal{T} = (\sigma_y \otimes \tau_y) \mathcal{C}$ from equation (16) (with \mathcal{C} complex conjugation) squares to $+1$ because the electron spin is not explicitly included. If we do include it, we would have $\mathcal{T} = (s_y \otimes \sigma_y \otimes \tau_y) \mathcal{C}$, which squares to -1 as expected for a fermionic quasiparticle. The combination of the time-reversal symmetry (16) and the chiral symmetry (17) places the superlattice in the BDI symmetry classification of topological states of matter.

⁹ The Landau levels also have a twofold spin degeneracy, which could be resolved by the Zeeman energy but is not considered here.

S_- have a rank-two null space¹⁰, spanned by the spinors $\psi_{\pm}^{(1)}$ and $\psi_{\pm}^{(2)}$. So if $\Pi_{\pm} f_{\pm} = 0$, a twofold degenerate zero-mode of \mathcal{H} is formed by the states $f_{\pm} \psi_{\mp}^{(1)}$ and $f_{\pm} \psi_{\mp}^{(2)}$.

All of this is distinctive for the Kek-Y bond order: for the Kek-O texture it is the other way around—the Landau levels have a twofold valley degeneracy except for the nondegenerate Landau level at the edge of the band gap¹¹.

4. Effect of virtual transitions to higher bands

So far we have assumed $\Delta_0 \ll 1$, and one might ask how robust our findings are to finite- Δ_0 corrections, involving virtual transitions from the $\varepsilon_{\pm 1}$ bands near $E = 0$ to the ε_0 band near $E = 3t_0$. We have been able to include these to all orders in Δ_0 (see appendix B), and find that the entire effect is a renormalization of the velocities v_{σ} and v_{τ} in the Hamiltonian (14), which retains its form as a sum of two helicity operators. For real $\Delta = \Delta_0$ the renormalization is given by $v_{\sigma} = v_0 \rho_+$, $v_{\tau} = v_0 \rho_-$ with

$$\rho_{\pm} = \frac{1}{2}(1 - \Delta_0) \left(\frac{1 + 2\Delta_0}{\sqrt{1 + 2\Delta_0^2}} \pm 1 \right). \quad (19)$$

For complex $\Delta = \Delta_0 e^{i\phi}$ the nonlinear renormalization introduces a dependence on the phase ϕ modulo $2\pi/3$.

What this renormalization shows is that, as expected for a topological protection, the robustness of the zeroth Landau level to the Kek-Y texture is not limited to perturbation theory—also strong modulations of the bond strength cannot split it away from $E = 0$.

5. Pseudospin-valley coupling

In zero magnetic field the low-energy Hamiltonian (14) does not couple the pseudospin σ and valley τ degrees of freedom. A $\sigma \otimes \tau$ coupling is introduced in the Kek-Y superlattice by an ionic potential μ_Y on the carbon atoms that line up with the carbon vacancies—the atoms located at each center of a red Y in figure 1. We consider this effect for the $\nu = 1$ Kek-Y texture with a real $\tilde{\Delta} = \Delta_0$.

The ionic potential acts on one-third of the A sublattice sites, labeled r_Y . (For $\nu = -1$ it would act on one-third of the B sublattice sites.) Fourier transformation of the on-site contribution $\mu_Y \sum_{r_Y} a_{r_Y}^{\dagger} a_{r_Y}$ to the tight-binding Hamiltonian (1) gives with the help of the lattice sum

$$\sum_{r_Y} e^{ik \cdot r_Y} \propto \delta(\mathbf{k}) + \delta(\mathbf{k} - \mathbf{G}) + \delta(\mathbf{k} + \mathbf{G}) \quad (20)$$

the momentum-space Hamiltonian

$$H(\mathbf{k}) = -c_k^{\dagger} \begin{pmatrix} M_Y & \mathcal{E}_1(\mathbf{k}) \\ \mathcal{E}_1^{\dagger}(\mathbf{k}) & 0 \end{pmatrix} c_k, \quad (21a)$$

$$M_Y = -\mu_Y \begin{pmatrix} 1 & 1 & 1 \\ 1 & 1 & 1 \\ 1 & 1 & 1 \end{pmatrix}. \quad (21b)$$

The \mathcal{E}_1 block is still given by equation (8). The additional M_Y -block breaks the chiral symmetry.

Projection onto the subspace spanned by $u_{\mathbf{k}} = (a_{\mathbf{k}-\mathbf{G}}, a_{\mathbf{k}+\mathbf{G}}, b_{\mathbf{k}-\mathbf{G}}, b_{\mathbf{k}+\mathbf{G}})$ gives the effective Hamiltonian



$$H_{\text{eff}} = -u_{\mathbf{k}}^{\dagger} \begin{pmatrix} m_Y & h_1 \\ h_1^{\dagger} & 0 \end{pmatrix} u_{\mathbf{k}}, \quad m_Y = -\mu_Y \begin{pmatrix} 1 & 1 \\ 1 & 1 \end{pmatrix}. \quad (22)$$

The corresponding Dirac Hamiltonian has the form (11) with an additional $\sigma \otimes \tau$ coupling,

$$\begin{aligned} \mathcal{H} = & v_{\sigma} (\mathbf{p} \cdot \boldsymbol{\sigma}) \otimes \tau_0 + v_{\tau} \sigma_0 \otimes (\mathbf{p} \cdot \boldsymbol{\tau}) + \frac{1}{2} \mu_Y \\ & + \frac{1}{2} \mu_Y (\sigma_x \otimes \tau_x + \sigma_y \otimes \tau_y - \sigma_z \otimes \tau_z). \end{aligned} \quad (23)$$

¹⁰ If we define the eigenstates $|\alpha, \beta\rangle$ by $\sigma_z |\alpha, \beta\rangle = \alpha |\alpha, \beta\rangle$, $\tau_z |\alpha, \beta\rangle = \beta |\alpha, \beta\rangle$, then S_+ annihilates $\psi_+^{(1)} = |1, 1\rangle$ and $\psi_+^{(2)} = v_r |-1, 1\rangle - v_l |1, -1\rangle$, while S_- annihilates $\psi_-^{(1)} = |-1, -1\rangle$ and $\psi_-^{(2)} = v_r |1, -1\rangle - v_l |-1, 1\rangle$.

¹¹ In a Kek-O superlattice the Landau levels are given by $E_n^2 = (3t_0 \Delta_0)^2 + 2n\hbar v_0^2$, $n = 0, 1, 2, \dots$, with a twofold valley degeneracy for $n \geq 1$ and a nondegenerate zeroth Landau level at $\pm 3t_0 \Delta_0$.

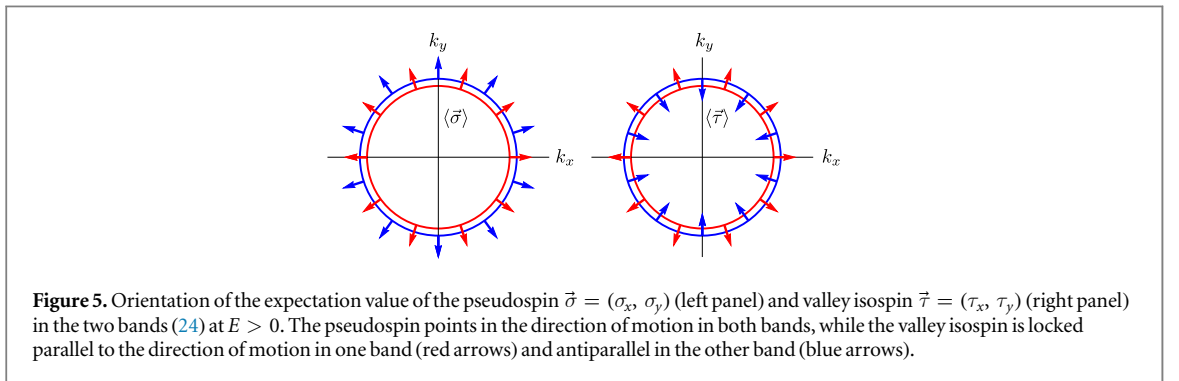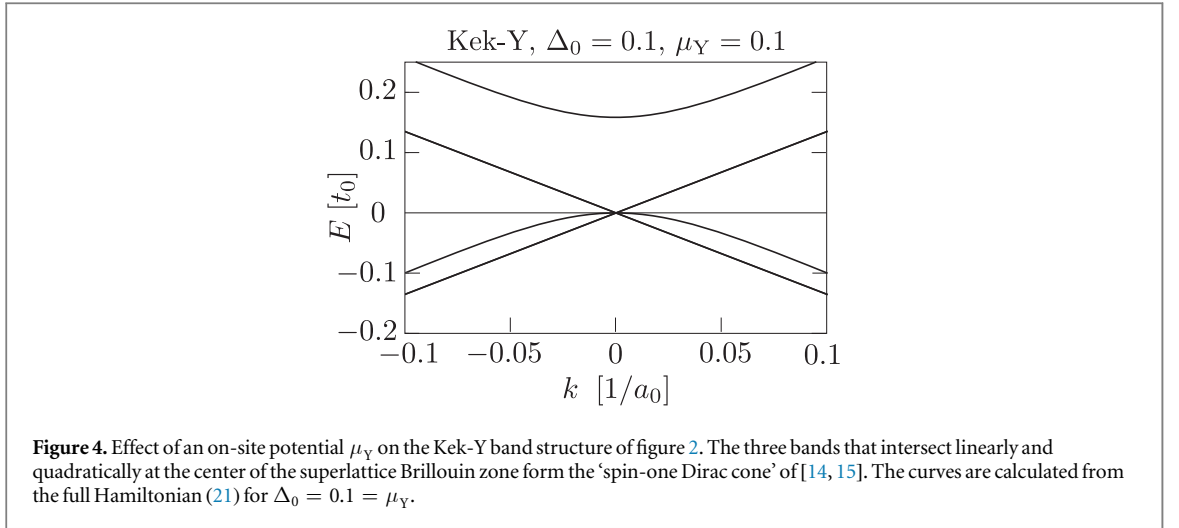

The energy spectrum,

$$\begin{aligned} E_{\pm}^{(1)} &= \pm(v_{\sigma} - v_{\tau})|\mathbf{p}|, \\ E_{\pm}^{(2)} &= \mu_Y \pm \sqrt{(v_{\sigma} + v_{\tau})^2|\mathbf{p}|^2 + \mu_Y^2}, \end{aligned} \quad (24)$$

has two bands that cross linearly in p at $E = 0$, while the other two bands have a quadratic p -dependence (see figure 4). The pseudospin and valley isospin orientation for the two bands is illustrated in figure 5.

The three bands $E_{+}^{(1)}$, $E_{-}^{(1)}$, $E_{-}^{(2)}$ that intersect at $p = 0$ are reminiscent of a spin-one Dirac one. Such a dispersion is a known feature of a potential modulation that involves only one-third of the atoms on one sublattice [14, 15]. The spectrum remains gapless even though the chiral symmetry is broken. This is in contrast to the usual staggered potential between A and B sublattices, which opens a gap via a $\sigma_z \otimes \tau_z$ term [16].

6. Discussion

In summary, we have shown that the Y-shaped Kekulé bond texture (Kek-Y superlattice) in graphene preserves the massless character of the Dirac fermions. This is fundamentally different from the gapped band structure resulting from the original Kekulé dimerization [8–11] (Kek-O superlattice), and contrary to expectations from its experimental realization [6, 7].

The gapless low-energy Hamiltonian $\mathcal{H} = v_{\sigma}\mathbf{p} \cdot \boldsymbol{\sigma} + v_{\tau}\mathbf{p} \cdot \boldsymbol{\tau}$ is the sum of two helicity operators, with the momentum \mathbf{p} coupled independently to both the sublattice pseudospin $\boldsymbol{\sigma}$ and the valley isospin $\boldsymbol{\tau}$. This valley-momentum locking is distinct from the coupling of the valley to a pseudo-magnetic field that has been explored as an enabler for valleytronics [23], and offers a way for a momentum-controlled valley precession. The broken valley degeneracy would also remove a major obstacle for spin qubits in graphene [24].

A key experimental test of our theoretical predictions would be a confirmation that the Kek-Y superlattice has a gapless spectrum, in stark contrast to the gapped Kek-O spectrum. In the experiment by Gutiérrez *et al* on a graphene/Cu heterostructure the Kek-Y superlattice is formed by copper vacancies that are in registry with one out of six carbon atoms [6, 7]. These introduce the Y-shaped hopping modulations shown in figure 1, but in addition will modify the ionic potential felt by the carbon atom at the center of the Y. Unlike the usual staggered

potential between A and B sublattices, this potential modulation in an enlarged unit cell does not open a gap [14, 15]. We have also checked that the Dirac cone remains gapless if we include hoppings beyond nearest neighbor. All of this gives confidence that the gapless spectrum will survive in a realistic situation.

Further research in other directions could involve the Landau level spectrum, to search for the unique feature of a broken valley degeneracy coexisting with a valley-degenerate zero-mode. The graphene analogs in optics and acoustics [25] could also provide an interesting platform for a Kek-Y superlattice with a much stronger amplitude modulation than can be realized with electrons.

Acknowledgments

We have benefited from discussions with A Akhmerov, V Cheianov, J Hutasoit, P Silvestrov, and D Varjas. This research was supported by the Netherlands Organization for Scientific Research (NWO/OCW) and an ERC Synergy Grant.

Appendix A. Calculation of the Landau level spectrum in a Kek-Y superlattice

We calculate the spectrum in a perpendicular magnetic field of a graphene sheet with a Kekulé-Y bond texture. We start by rewriting the Hamiltonian (14), with $\mathbf{\Pi} = \mathbf{p} + e\mathbf{A}$, in the form

$$\mathcal{H} = \frac{1}{2}\Pi_+S_- + \frac{1}{2}\Pi_-S_+ + \mu\sigma_z \otimes \tau_z, \quad (\text{A1})$$

in terms of the raising and lowering operators

$$\begin{aligned} \Pi_{\pm} &= \Pi_x \pm i\Pi_y, \quad \sigma_{\pm} = \sigma_x \pm i\sigma_y, \quad \tau_{\pm} = \tau_x \pm i\tau_y, \\ S_{\pm} &= v_{\sigma} \sigma_{\pm} \otimes \tau_0 + v_{\tau} \sigma_0 \otimes \tau_{\pm}. \end{aligned} \quad (\text{A2})$$

The chiral-symmetry breaking term $\mu\sigma_z \otimes \tau_z$ that we have added will serve a purpose later on.

We know that the Hermitian operator $\Omega = \Pi_+\Pi_-$ has eigenvalues $\omega_n = 2n\hbar eB$, $n = 0, 1, 2, \dots$, in view of the commutator $[\Pi_-, \Pi_+] = 2\hbar eB$. So the strategy is to express the secular equation $\det(E - \mathcal{H}) = 0$ in a form that involves only the mixed products $\Pi_+\Pi_-$, and no Π_+^2 or Π_-^2 . This is achieved by means of a unitary transformation, as follows.

We define the unitary matrix

$$U = \exp\left[\frac{1}{4}i\pi(\sigma_0 + \sigma_z) \otimes \tau_y\right] \quad (\text{A3})$$

and reduce the determinant of a 4×4 matrix to that of a 2×2 matrix:

$$\begin{aligned} \det(\mathcal{H} - E) &= \det U^\dagger(\mathcal{H} - E)U \\ &= \det \begin{pmatrix} -E + \mu & R^\dagger \\ R & -E - \mu \end{pmatrix} \\ &= \begin{cases} \det(E^2 - \mu^2 - RR^\dagger) & \text{if } E \neq \mu, \\ \det(E^2 - \mu^2 - R^\dagger R) & \text{if } E \neq -\mu, \end{cases} \end{aligned} \quad (\text{A4})$$

$$\text{with } R = \begin{pmatrix} -v_{\tau}\Pi_- & v_{\sigma}\Pi_- \\ -v_{\sigma}\Pi_+ & v_{\tau}\Pi_+ \end{pmatrix}. \quad (\text{A5})$$

The matrix product RR^\dagger is not of the desired form, but $R^\dagger R$ is,

$$R^\dagger R = \begin{pmatrix} v_{\sigma}^2\Pi_-\Pi_+ + v_{\tau}^2\Pi_+\Pi_- & -v_{\sigma}v_{\tau}(\Pi_-\Pi_+ + \Pi_+\Pi_-) \\ -v_{\sigma}v_{\tau}(\Pi_-\Pi_+ + \Pi_+\Pi_-) & v_{\sigma}^2\Pi_+\Pi_- + v_{\tau}^2\Pi_-\Pi_+ \end{pmatrix}, \quad (\text{A6})$$

involving only $\Pi_+\Pi_- = \Omega$ and $\Pi_-\Pi_+ = \Omega + \omega_1$. Hence the determinant is readily evaluated for $E \neq -\mu$,

$$\det(\mathcal{H} - E) = \det(E^2 - \mu^2 - R^\dagger R) = \prod_{n=0}^{\infty} \det \begin{pmatrix} E^2 - \mu^2 - \bar{v}^2\omega_n - v_{\sigma}^2\omega_1 & v_{\sigma}v_{\tau}(2\omega_n + \omega_1) \\ v_{\sigma}v_{\tau}(2\omega_n + \omega_1) & E^2 - \mu^2 - \bar{v}^2\omega_n - v_{\tau}^2\omega_1 \end{pmatrix}, \quad (\text{A7})$$

where we have abbreviated $\bar{v} = \sqrt{v_{\sigma}^2 + v_{\tau}^2}$.

Equating the determinant to zero and solving for E we find four sets of energy eigenvalues E_n^+ , E_n^- , $-E_n^+$, $-E_n^-$, given by

$$(E_n^\pm)^2 - \mu^2 = \left(\omega_n + \frac{1}{2}\omega_1\right)\bar{v}^2 \pm \frac{1}{2}\sqrt{\omega_1^2\bar{v}^4 + (4v_\sigma v_\tau)^2\omega_n\omega_{n+1}} = E_B^2[2n + 1 \pm \sqrt{1 + n(n+1)(4v_\sigma v_\tau)^2\bar{v}^{-4}}]. \quad (\text{A8})$$

In the second equation we introduced the energy scale $E_B = \hbar\bar{v}/l_m$, with $l_m = \sqrt{\hbar/eB}$ the magnetic length. The B -independent level $E_0^- = \mu$ becomes a zero-mode in the limit $\mu \rightarrow 0$.

As a check on the calculation, we note that for $\mu = 0$, $v_\tau = 0$ we recover the valley-degenerate Landau level spectrum of graphene [16],

$$E_n^- = (\hbar v_\sigma/l_m)\sqrt{2n}, \quad E_n^+ = E_{n+1}^-. \quad (\text{A9})$$

Another special case of interest is $\mu = 0$, $v_\sigma = v_\tau \equiv v_0$, when the two modes of Dirac fermions have velocities $v_\sigma \pm v_\tau$ equal to 0 and $2v_0$. From equation (A8) we find the Landau level spectrum

$$E_n^- = 0, \quad E_n^+ = 2(\hbar v_0/l_m)\sqrt{2n+1}. \quad (\text{A10})$$

The mode with zero velocity remains B -independent, while the mode with velocity $2v_0$ produces a sequence of Landau levels with a $1/2$ offset in the n -dependence.

Appendix B. Calculation of the low-energy Hamiltonian to all orders in the Kek-Y bond modulation

We seek to reduce the six-band Hamiltonian (8) to an effective 4×4 Hamiltonian that describes the low-energy spectrum near $\mathbf{k} = 0$. For $\Delta_0 \ll 1$ we can simply project onto the 2×2 lower-right subblock of \mathcal{E}_ν , which for the $|\nu| = 1$ Kek-Y bond modulation vanishes linearly in \mathbf{k} . This subblock is coupled to the ε_0 band near $E = 3t_0$ by matrix elements of order Δ_0 , so virtual transitions to this higher band contribute to the low-energy spectrum in order Δ_0^2 . We will now show how to include these effects to all order in Δ_0 .

One complication when we go beyond the small- Δ_0 regime is that the phase ϕ of the modulation amplitude can no longer be removed by a unitary transformation. As we will see, the low-energy Hamiltonian depends on ϕ modulo $2\pi/3$ —so we do not need to distinguish between the phase of $\tilde{\Delta} = e^{2\pi i(p+q)/3}\Delta$ and the phase of Δ . The choice between $\nu = \pm 1$ still does not matter, the two Kek-Y modulations being related by a mirror symmetry. For definiteness we take $\nu = +1$.

We define the unitary matrix

$$V = \begin{pmatrix} \Phi & 0 \\ 0 & \Phi \end{pmatrix} \begin{pmatrix} \mathcal{V} & 0 \\ 0 & \mathbf{1} \end{pmatrix}, \quad \Phi = \begin{pmatrix} 1 & 0 & 0 \\ 0 & e^{-i\phi} & 0 \\ 0 & 0 & e^{i\phi} \end{pmatrix}, \quad (\text{B1a})$$

$$\mathcal{V} = \frac{1}{2D_0} \begin{pmatrix} 2 & -2\Delta_0 & -2\Delta_0 \\ 2\Delta_0 & 1 + D_0 & 1 - D_0 \\ 2\Delta_0 & 1 - D_0 & 1 + D_0 \end{pmatrix}, \quad (\text{B1b})$$

with $D_0 = \sqrt{1 + 2\Delta_0^2}$ and evaluate

$$V^\dagger \begin{pmatrix} 0 & \mathcal{E}_1 \\ \mathcal{E}_1^\dagger & 0 \end{pmatrix} V = \begin{pmatrix} 0 & \tilde{\mathcal{E}}_1 \\ \tilde{\mathcal{E}}_1^\dagger & 0 \end{pmatrix}, \quad (\text{B2a})$$

$$\tilde{\mathcal{E}}_1 = \mathcal{V}^\dagger \mathcal{E}_1 = \begin{pmatrix} D_0\varepsilon_0 & \rho_0^*\varepsilon_{-1} & \rho_0\varepsilon_1 \\ 0 & \rho_+\varepsilon_{-1} & \rho_-^*\varepsilon_1 \\ 0 & \rho_-\varepsilon_{-1} & \rho_+^*\varepsilon_1 \end{pmatrix}, \quad (\text{B2b})$$

$$\rho_\pm = \frac{1}{2D_0}[1 - 2\Delta_0^2 \pm D_0 + e^{-3i\phi}\Delta_0(1 \mp D_0)], \quad (\text{B2c})$$



$$\rho_0 = \frac{\Delta_0}{D_0}(2 + e^{3i\phi}\Delta_0). \quad (\text{B2d})$$

The matrix elements that couple the lower-right 2×2 subblock of $\tilde{\mathcal{E}}_1$ to ε_0 are now of order k , so the effect on the low-energy spectrum is of order k^2 and can be neglected—to all orders in Δ_0 .

The resulting effective low-energy Hamiltonian has the 4×4 form (9), with h_1 replaced by

$$h_1 = \begin{pmatrix} \rho_+\varepsilon_{-1} & \rho_-^*\varepsilon_1 \\ \rho_-\varepsilon_{-1} & \rho_+^*\varepsilon_1 \end{pmatrix}. \quad (\text{B3})$$

The phases of $\rho_\pm = |\rho_\pm|e^{i\theta_\pm}$ can be eliminated by one more unitary transformation, with the 4×4 diagonal matrix

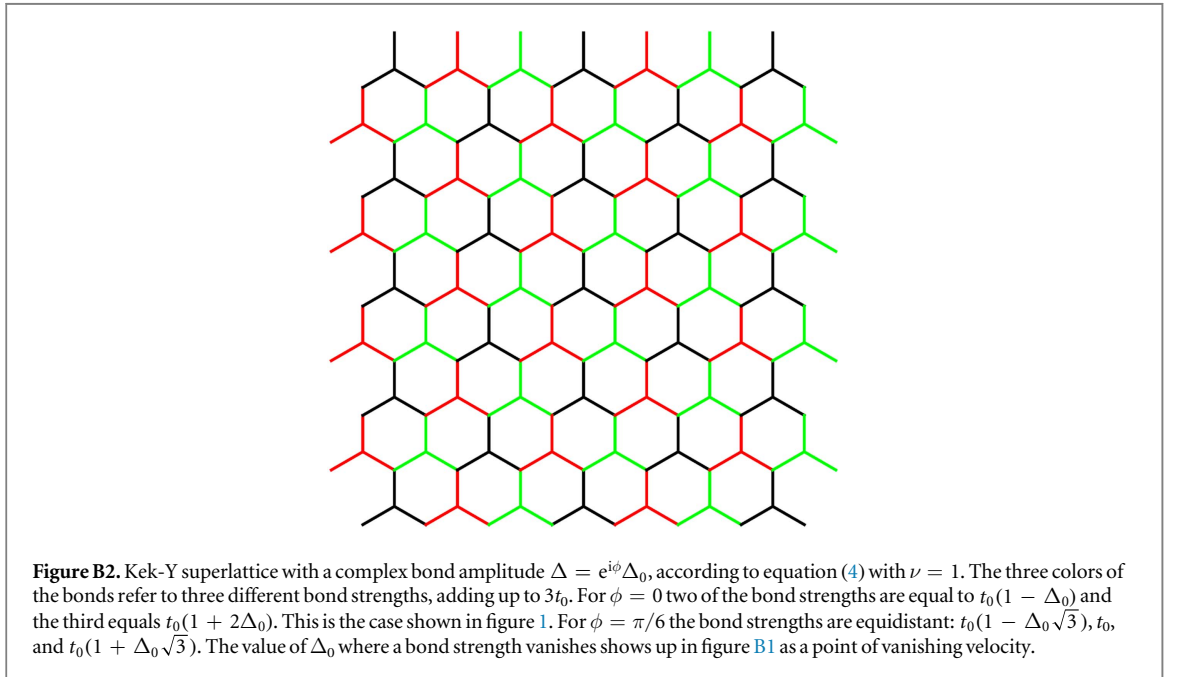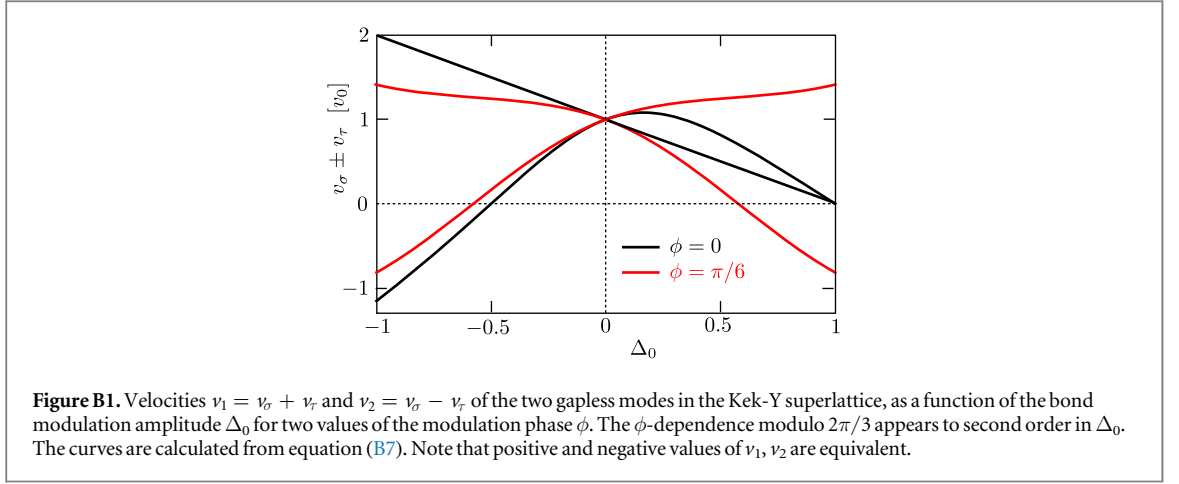

$$\Theta = \text{diag}(e^{i\theta_-}, e^{i\theta_+}, e^{i\theta_+ + i\theta_-}, 1), \quad (\text{B4})$$

which results in

$$\Theta^\dagger \begin{pmatrix} 0 & h_1 \\ \tilde{h}_1^\dagger & 0 \end{pmatrix} \Theta = \begin{pmatrix} 0 & \tilde{h}_1 \\ \tilde{h}_1^\dagger & 0 \end{pmatrix}, \quad \tilde{h}_1 = \begin{pmatrix} |\rho_+|\varepsilon_{-1} & |\rho_-|\varepsilon_1 \\ |\rho_-|\varepsilon_{-1} & |\rho_+|\varepsilon_1 \end{pmatrix}. \quad (\text{B5})$$

Finally, we arrive at the effective Hamiltonian (14), with renormalized velocities:

$$\mathcal{H} = v_\sigma(\mathbf{p} \cdot \boldsymbol{\sigma}) \otimes \tau_0 + v_\tau \sigma_0 \otimes (\mathbf{p} \cdot \boldsymbol{\tau}), \quad v_\sigma = |\rho_+|v_0, \quad v_\tau = |\rho_-|v_0, \quad (\text{B6})$$

$$|\rho_\pm|^2 = \frac{1}{2D_0^2}(1 + 3\Delta_0^4 \pm D_0(1 - 3\Delta_0^2) + 2\Delta_0^3(\pm D_0 - 2)\cos 3\phi). \quad (\text{B7})$$

To third order in Δ_0 we have

$$v_\sigma/v_0 = 1 - \frac{3}{2}\Delta_0^2 - \frac{1}{2}\Delta_0^3 \cos 3\phi, \quad v_\tau/v_0 = \Delta_0 - \frac{3}{2}\Delta_0^2 \cos 3\phi + \frac{1}{16}\Delta_0^3(1 - 9\cos 6\phi) + \mathcal{O}(\Delta_0^4). \quad (\text{B8})$$

For real Δ , when $\phi = 0$ and ρ_{\pm} is real, equation (B7) simplifies to

$$\rho_{\pm} = \frac{1}{2}(1 - \Delta_0) \left(\frac{1 + 2\Delta_0}{\sqrt{1 + 2\Delta_0^2}} \pm 1 \right). \quad (\text{B9})$$

The velocities of the two Dirac modes are then given by

$$\begin{aligned} v_1 &= v_{\sigma} + v_{\tau} = v_0 \frac{(1 - \Delta_0)(1 + 2\Delta_0)}{\sqrt{1 + 2\Delta_0^2}}, \\ v_2 &= v_{\sigma} - v_{\tau} = v_0(1 - \Delta_0). \end{aligned} \quad (\text{B10})$$

More generally, for complex $\Delta = \Delta_0 e^{i\phi}$ both v_1 and v_2 become ϕ -dependent to second order in Δ_0 , see figure B1.

Note that the asymmetry in $\pm\Delta_0$ vanishes for $\phi = \pi/6$. For this phase the superlattice has three different bond strengths (see figure B2) that are symmetrically arranged around the unperturbed value t_0 .

ORCID iDs

C W J Beenakker  <https://orcid.org/0000-0003-4748-4412>

References

- [1] Fert A 2008 Origin, development, and future of spintronics *Angew. Chem., Int. Ed. Engl.* **47** 5956
- [2] Awschalom D and Samarth N 2009 Spintronics without magnetism *Physics* **2** 50
- [3] Kuschel T and Reiss G 2015 Spin orbitronics: charges ride the spin wave *Nat. Nanotechnol.* **10** 22
- [4] Recher P and Trauzettel B 2011 A defect controls transport in graphene *Physics* **4** 25
- [5] Pesin D and MacDonald A H 2012 Spintronics and pseudospintronics in graphene and topological insulators *Nat. Mater.* **11** 409
- [6] Gutiérrez C, Kim C-J, Brown L, Schiros T, Nordlund D, Lochocki E B, Shen K M, Park J and Pasupathy A N 2016 Imaging chiral symmetry breaking from Kekulé bond order in graphene *Nat. Phys.* **12** 950
Commentary by Mudry C 2016 Heavy going *Nat. Phys.* **12** 895
- [7] Gutiérrez C 2015 Visualizing ordered electronic states in epitaxial graphene *PhD Thesis* Columbia University Academic Commons
- [8] Chamon C 2000 Solitons in carbon nanotubes *Phys. Rev. B* **62** 2806
- [9] Hou C-Y, Chamon C and Mudry C 2007 Electron fractionalization in two-dimensional graphenelike structures *Phys. Rev. Lett.* **98** 186809
- [10] Cheianov V V, Fal'ko V I, Syljuåsen O and Altshuler B L 2009 Hidden Kekulé ordering of adatoms on graphene *Solid State Commun.* **149** 1499
- [11] Cheianov V V, Syljuåsen O, Altshuler B L and Fal'ko V 2009 Ordered states of adatoms on graphene *Phys. Rev. B* **80** 233409
- [12] Gomes K K, Mar W, Ko W, Guinea F and Manoharan H C 2012 Designer Dirac fermions and topological phases in molecular graphene *Nature* **483** 306
- [13] Giovannetti G, Khomyakov P A, Brocks G, Kelly P J and van den Brink J 2007 Substrate-induced bandgap in graphene on hexagonal boron nitride *Phys. Rev. B* **76** 073103
- [14] Giovannetti G, Capone M, van den Brink J and Ortix C 2015 Kekulé textures, pseudo-spin one Dirac cones and quadratic band crossings in a graphene-hexagonal indium chalcogenide bilayer *Phys. Rev. B* **91** 121417
- [15] Ren Y, Deng X, Qiao Z, Li C, Jung J, Zeng C, Zhang Z and Niu Q 2015 Single-valley engineering in graphene superlattices *Phys. Rev. B* **91** 245415
- [16] Castro Neto A H, Guinea F, Peres N M R, Novoselov K S and Geim A K 2009 The electronic properties of graphene *Rev. Mod. Phys.* **81** 109
- [17] See Beenakker C W J 2008 Andreev reflection and Klein tunneling in graphene *Rev. Mod. Phys.* **80** 1337
- [18] Aharonov Y and Casher A 1979 Ground state of a spin-1/2 charged particle in a two-dimensional magnetic field *Phys. Rev. A* **19** 2461
- [19] Wen X G and Zee A 1989 Winding number, family index theorem, and electron hopping in a magnetic field *Nucl. Phys. B* **316** 641
- [20] Katsnelson M I and Prokhorova M F 2008 Zero-energy states in corrugated bilayer graphene *Phys. Rev. B* **77** 205424
- [21] Kailasvuori J 2009 Pedestrian index theorem à la Aharonov–Casher for bulk threshold modes in corrugated multilayer graphene *Europhys. Lett.* **87** 47008
- [22] Groth C W, Wimmer M, Akhmerov A R and Waintal X 2014 Kwant: a software package for quantum transport *New J. Phys.* **16** 063065
- [23] Wang S K and Wang J 2015 Valley precession in graphene superlattices *Phys. Rev. B* **92** 075419
- [24] Trauzettel B, Bulaev D V, Loss D and Burkard G 2007 Spin qubits in graphene quantum dots *Nat. Phys.* **3** 192
- [25] Polini M, Guinea F, Lewenstein M, Manoharan H C and Pellegrini V 2013 Artificial honeycomb lattices for electrons, atoms and photons *Nat. Nanotechnol.* **8** 625