

Cover Page



Universiteit Leiden



The handle <http://hdl.handle.net/1887/36422> holds various files of this Leiden University dissertation.

Author: Díaz Morales, Oscar Alfonso

Title: Catalysis of the electrochemical water oxidation to oxygen

Issue Date: 2015-11-19

Chapter 3

Electrochemical and spectroelectrochemical characterization of an iridium-based molecular catalyst for oxygen evolution: turnover frequencies, stability and electrolyte effects

ABSTRACT

We present a systematic electrochemical and spectroelectrochemical study of the catalytic activity for water oxidation of an iridium-N-dimethylimidazolin-2-ylidene (Ir-NHC-Me₂) complex adsorbed on a polycrystalline gold electrode. The work aims to understand the effect of the electrolyte properties (anions and acidity) on the activity of the molecular catalyst and check its stability towards decomposition. Our results show that the iridium complex displays a very strong dependence on the electrolyte properties such that large enhancements in catalytic activity may be obtained by adequately choosing pH and anions in the electrolyte. The stability of the adsorbed compound was investigated *in situ* by Surface Enhanced Raman Spectroscopy and Online Electrochemical Mass Spectrometry showing that the catalyst exhibits good stability under anodic conditions, with no observable evidence for the decomposition to iridium oxide.

This chapter has been published in: Diaz-Morales, O.; Hersbach, T. J. P., Hettler, D., G. H.; Reek, J. N. H and Koper M.T.M. *J. Am. Chem. Soc.* **2014**, 136, 10432-10439.

3.1. Introduction

Since the discovery of the ruthenium blue dimer system by Meyer¹, many molecular water oxidation catalysts have been published in literature²⁻⁴. Especially ruthenium based systems have been extensively studied,⁵⁻²⁰ but also manganese,²¹⁻²³ iron,^{24,25} cobalt,²⁶⁻²⁸ copper²⁹⁻³¹ and iridium³²⁻⁴² catalysts have been addressed. The catalytic activity of these systems for water oxidation is usually studied using sacrificial stoichiometric reagents.⁴³ Detailed (spectro-)electrochemical studies of dissolved or immobilized catalytic complexes for water oxidation are still rare. The use of sacrificial oxidants makes difficult to properly define the thermodynamic driving force for the water oxidation reaction. An unequivocal comparison between different systems is often hampered by varying reaction conditions and the associated lack of a clearly defined oxidation potential. The importance of controlling the oxidation potential in evaluating charge transfer rates follows from the Marcus theory for electron transfer reactions, in which the thermodynamic driving force η features prominently.⁴⁴ Knowing the reaction rate or Turnover Frequency (TOF) at a well-specified overpotential is also mandatory for assessing the suitability and efficiency of the catalyst in relation to its application in a future device.

In homogeneous catalysis studies of the water oxidation reaction, Cerium Ammonium Nitrate (CAN) is frequently used as a chemical oxidant, and its corresponding oxidation potential follows from the Nernst equation:

$$E_{eq} = E^0 + \frac{RT}{nF} \ln \left(\frac{[Ce^{4+}]}{[Ce^{3+}]} \right) \quad (1)$$

where E^0 is the standard redox potential of the couple Ce^{3+}/Ce^{4+} , *i.e.* 1.72 V vs. SHE,⁴⁵ R the gas constant, T temperature, $n=1$ the number of electrons transferred, F the Faraday constant and $[Ce^{4+}]$, $[Ce^{3+}]$ are, respectively, the activities of Ce^{4+} and Ce^{3+} in solution. Experiments are usually performed by adding solutions of cerium(IV) so that the initial concentration of cerium(III) is zero, under which conditions the oxidation potential is poorly defined (theoretically, it is infinitely high). Moreover, the oxidation potential will

actually change (*i.e.*, lower) as the reaction progresses, since Ce^{4+} is converted into Ce^{3+} so that their concentrations change in time.

An additional complication of using CAN is that, since the nitrate coordinating to cerium(IV) is partly displaced by water, the actual structure of CAN is poorly defined and very acidic conditions are employed as the Ce^{4+} coordinated aqua ligands readily deprotonate.⁴⁶ DFT calculations have shown that the resulting cerium hydroxide is best described as a Ce(III) complex with a hydroxyl radical coordinated.¹⁷ This can possibly lead to undesirable pathways involving transfer of hydroxyl radicals that are not relevant to water oxidation. Furthermore, Berlinguette and coworkers showed that part of the dioxygen evolved during ruthenium mediated water oxidation with CAN, contains oxygen atoms that are derived from nitrate rather than from water.⁴⁶ Another popular oxidant is periodate, which is stable at milder conditions compared to CAN^{43} ; however, it contains atomic oxygen that undergoes fast exchange equilibrium with water. For that reason, O-atom labeling studies cannot confirm whether the dioxygen produced derives from water or periodate.⁴⁷ In a recent theoretical study, we showed that atomic oxygen transfer from periodate to the iridium catalyst under study is very facile, and by *in situ*-MS spectroscopy we identified catalytic species that point to the occurrence of such non relevant elementary steps⁴⁸.

In addition to the sometimes poorly understood identity of the chemical oxidant under reactive conditions, identification of the active catalyst can be an issue. This has almost exclusively been carried out using sacrificial reagents. On basis of electrochemical experiments, it was claimed by the groups of De Groot and Lin that iridium complexes bearing cyclopentadienyl ligands may be stable, as no time dependence of the observed catalytic activity was observed.^{49,50} On the other hand, Crabtree and coworkers reported the complete deterioration of $[\text{IrC}_p^*(\text{OH}_2)_3]^{2+}$ (C_p^* = pentamethylcyclopentadienyl), leading to the formation of an amorphous phase of iridium oxide on the electrode.⁵¹⁻⁵³ In agreement with the former studies, our group⁵⁴ as well as others⁵⁵ showed using DFT calculations that iridium catalysts bearing the C_p^* ligand can be active for catalytic water oxidation and those catalyst would be sufficiently stable. Crabtree and coworkers published that the C_p^*

ligand is readily lost and that binuclear molecular complexes bearing the remaining organic ligands are the true active species, using sacrificial periodate as a chemical oxidant⁵⁶. Others have shown that complete deterioration of molecular systems leading to formation of iridium oxide nanoparticles can take place,^{32,57,58} yet this seems to be a relative sluggish reaction³³ which is strongly dependent on the iridium concentration employed. It was also shown that these nanoparticles contain significant amounts of cerium. It is not clear to which extent these phenomena are dependent on the chemical oxidants used, and whether this chemistry can actually be translated meaningfully to the electrochemically driven dioxygen evolution reaction.

In contrast to catalytic oxidation by stoichiometric oxidants, oxidation by electrochemical techniques allows for better defined reaction conditions. The relevant oxidation potential is directly related to the applied electrode potential, leaving no doubt about the thermodynamic driving force. Provided that the electrode material used to apply the oxidizing potential is stable under the conditions of water oxidation, there are no negative or unknown side effects of chemically unstable oxidants. Furthermore, if the molecular catalyst is immobilized on the inert electrode surface, mass transport of the catalyst may be ignored and the identity and stability of the immobilized catalyst may be probed by surface sensitive spectro-electrochemical techniques. Such studies are also more meaningful in relation to real application of water oxidation catalysis in the production of solar fuels.

In this work, we perform an electrochemical and spectro-electrochemical study of the water oxidation reaction using the recently introduced IrCp*-N-dimethylimidazolin-2-ylidene catalyst, immobilized on polycrystalline gold electrodes. We use steady state voltammetry to demonstrate the significant influence of the electrolyte composition in terms of pH and anion identity on the TOF of the catalyst. We show *in situ* Surface Enhanced Raman Spectroscopy (SERS) evidences that the adsorbed catalyst does not form IrO_x nanoparticles. Moreover, we show by the combination of electrochemical experiments with on-line electrochemical mass spectroscopy (OLEMS) that the adsorbed catalyst

produces only O_2 under reactive conditions, and no CO_2 , testifying to the stability of the organic ligands.

3.2. Experimental Section

All glassware was thoroughly cleaned before starting experiments by boiling in a 1:3 mixture of concentrated HNO_3 /concentrated H_2SO_4 to remove organic contaminations after which it was boiled five times in water. The water used for cleaning glassware and preparing solutions was demineralized and ultrafiltrated by a Millipore Milli-Q system (resistivity $> 18.2 \text{ M}\Omega \text{ cm}$ and $TOC < 5 \text{ ppb}$). When not in use, the glassware was stored in an aqueous solution of $0.5 \text{ M } H_2SO_4$ and $1 \text{ g/L } KMnO_4$. To clean the glassware from permanganate solution, it was rinsed thoroughly with water and then immersed in a solution 1:1 of concentrated H_2SO_4 and 30% H_2O_2 to remove all particles of MnO_2 , after which it was rinsed with water again and boiled five times in water.

Electrolyte solutions were prepared with high quality chemicals, $HClO_4$ (VWR, Normatom), H_2SO_4 (Merck, Ultrapur), HNO_3 (Merck, Suprapur), H_3PO_4 (Merck, Suprapur), NaH_2PO_4 (Merck, Suprapur), $NaClO_4$ (Merck, Emsure) and $NaOH$ (Sigma-Aldrich, trace metals). Dissolved oxygen in solutions was removed prior to measurements by purging with argon (purity grade 5.0) for at least 30 min, and the argon was kept flowing above the solution during experiments. Experiments with ^{18}O enriched water were performed with 98% ^{18}O water (GMP standard, from CMR) and experiments in deuterated media used D_2O (Sigma-Aldrich, 99.9 atom % D).

Electrochemical measurements were carried out in a home-made three-electrode and two compartment cell with the reference electrode separated by a Luggin capillary. The working electrode was a homemade gold rotating disk electrode RDE ($\phi = 4.6 \text{ mm}$), a gold wire was used as counter electrode and a reversible hydrogen electrode (RHE) was used as a reference; a platinum wire was connected to the reference electrode through a capacitor of $10 \mu\text{F}$, acting as a low-pass filter to reduce the noise in the low current measurements. All experiments were performed in hydrodynamic conditions at 1500 RPM, using a home-made rotator. Electrochemical measurements were performed with a potentiostat

PGSTAT12 (Metrohm- Autolab). Before and between measurements, the RDE electrode was first polished with 0.3 μm and 0.05 μm alumina paste (Buehler Limited). Subsequently the electrode was ultrasonicated for 5 minutes to remove polishing particles.

The molecular catalyst used in this work is iridium-N-dimethylimidazolin-2-ylidene, which was synthesized by Hettler and Reek,³² with the structure shown in Figure 1. This compound was dissolved in water to give a solution with nominal concentration of 1×10^{-3} M (catalyst solution). Na-exchanged Nafion solution was prepared by mixing one part of Nafion (5% wt., Sigma-Aldrich) with one part of NaOH 0.05 M. The solution to drop cast on the electrode was prepared by mixing one part of catalyst solution with one part of Na-exchanged Nafion; 5 μL of this solution was drop casted on the gold working electrodes and dried under vacuum conditions. Currents in this work will be reported as $I_{\text{Normalized}}$, which is the measured current divided by the amount (in μmol) of catalyst drop casted on the electrode, considering the nominal concentration of solution used and volume added.

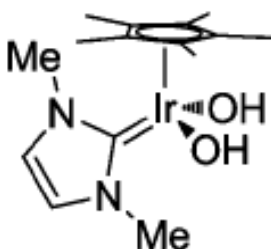


Figure 1. Structure of the iridium-N-dimethylimidazolin-2-ylidene complex.³²

In situ Surface Enhanced Raman Spectroscopy (SERS) was performed with a confocal Raman microscope (LabRam HR, Horiba Yobin Yvon) with a 50X objective. A He/Ne laser (633 nm) was used as excitation source. Backscattered light was filtered by a 633 nm edge filter, directed to the spectrograph and to the detector. Details of the setup can be found in references 59 and 60. Electrochemical SERS experiments were made with a

μ Autolab Type III potentiostat/galvanostat (Metrohm-Autolab), using a home-made electrochemical cell with a small electrolyte volume necessary for the H_2^{18}O experiments. The electrochemical cell has one compartment and three electrodes, a gold wire as counter electrode, Ag/AgCl (sat. KCl) as reference electrode (potentials were recalculated and reported versus RHE) and a roughened gold surface as working electrode. Prior to each measurement, the working electrode was mechanically polished to mirror finish using aqueous diamond pastes (Buehler Limited) with different grain sizes to $0.25\ \mu\text{m}$, rinsed with Milli-Q water and ultrasonicated during 5 min to remove all residuals of mechanical polishing. Next the gold electrode was electrochemically roughened by 25 oxidation-reduction cycles (ORC) in a 0.1 M solution of KCl. The ORC were performed between -0.30 and 1.20 V vs. SCE, during which the potential was held for 30 seconds at the negative limit and for 1.3 seconds at the positive limit, a method reported to give a brownish surface that is SERS active.⁶¹ SERS measurements were carried out drop casting the iridium complex without Na-exchanged Nafion, to avoid the appearance of strong signals in the spectrum, signals related to R- HSO_3 groups in Nafion.

Online Electrochemical Mass Spectrometry (OLEMS) experiments were performed using an EvoLution mass spectrometer system (European Spectrometry systems Ltd). The setup has a mass detector (Prisma QMS200, Pfeiffer) which was brought to vacuum using both a turbo molecular pump (TMH-071P, Pfeiffer, flow rate $60\ \text{L s}^{-1}$) and a rotary vane pump (Duo 2.5, Pfeiffer; flow rate $2.5\ \text{m}^3\ \text{h}^{-1}$). During measurements, the pressure inside the mass detector chamber was around 10^{-6} mbar. Volatile reaction products were collected from electrode interface by a small inlet tip positioned close ($\sim 10\ \mu\text{m}$) to electrode surface using a micrometric screw system and a camera.⁶² The inlet tip is made with a porous Teflon cylinder (Porex®) mounted in a Kel-F holder. The inlet is connected to the mass detector through a PEEK capillary. Before use, the inlet tip was cleaned during 15 min with a solution 0.2 M $\text{K}_2\text{Cr}_2\text{O}_7$ in 2 M H_2SO_4 and rinsed thoroughly with water. The electrochemical cell used for these experiments is a two compartment cell with three electrodes, using a gold bead electrode and a gold wire as working and counter electrode, respectively; the reference electrode was a RHE separated from the main cell by a Luggin capillary. Before each measurement, the working electrode was electrochemically cleaned;

the electrode was first oxidized in dilute sulfuric acid by applying 10 V for 30 s, using a graphite bar as counter electrode. Subsequently the gold oxide formed was removed by dipping the working electrode in a 6 M HCl solution for 30 s.

3.3. Results and Discussion

3.3.1. Effect of electrolyte anions

In a previous communication we reported³² the catalytic activity towards oxygen evolution for the Ir-NHC-Me₂ catalyst in aqueous solution, using cerium(IV) ammonium nitrate as chemical oxidant ($E^0_{\text{Ce(IV)/Ce(III)}} = 1.72 \text{ V vs. SHE}^{45}$) and showed that under the investigated conditions the complex exhibits a turnover frequency² of $0.34 \text{ mol O}_2 \text{ mol}_{\text{catalyst}}^{-1} \text{ s}^{-1}$, which was among the highest catalytic activities reported for an iridium based water oxidation molecular catalyst at the time. Here, we report the electrocatalytic activity of the complex immobilized on a gold surface including the effect of working conditions, such as electrolyte anions and pH.

Figure 2 shows the current-potential profiles obtained during water oxidation catalyzed by the iridium-N-dimethylimidazolin-2-ylidene on gold at pH 1 in electrolytes with different anions. The catalytic activity decreases in the order $\text{HClO}_4 > \text{H}_2\text{SO}_4 > \text{H}_3\text{PO}_4 > \text{HNO}_3$. The pH in each solution was verified with a pH meter and it was found that it was 1.0 ± 0.1 , so that we can exclude any pH effect in Figure 2.

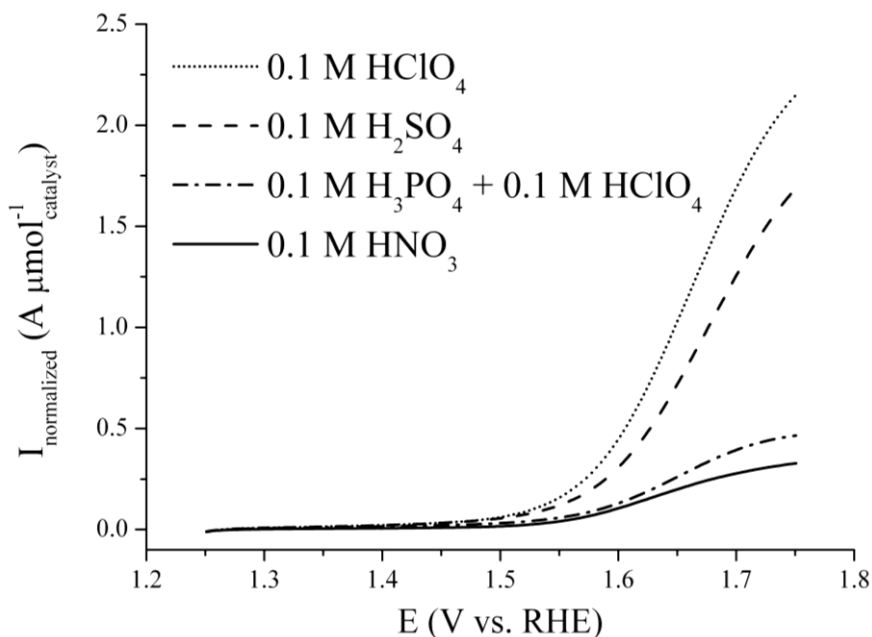


Figure 2. Current-potential profile for water oxidation catalyzed by iridium-N-dimethylimidazolin-2-ylidene immobilized on a gold rotating disk electrode, obtained under hydrodynamic conditions at pH 1 in different electrolytes. Scan rate: 0.005 V s^{-1} . Rotation rate: 1500 RPM.

The trend observed in Figure 2 shows the importance of the electrolyte anion for the water oxidation catalysis. The varying strength of the coordination of the anions to the iridium center of the molecular complex is the most likely explanation for the trend. It has been reported that metallic iridium binds NO quite strongly,⁶³ leading to poisoning of the electrode surface during nitrite reduction. Furthermore, the evidences reported by Ison *et al.*⁶⁴ show that nitrate and sulfate actually coordinate to iridium species bearing N-heterocyclic carbenes and pentamethylcyclopentadienyl ligands. Therefore, we assume that, of the anion shown in Figure 1, the nitrate anion binds to the iridium centers the strongest, so that it blocks their access for water oxidation. This was experimentally verified in aqueous solution for the iridium catalyst studied in this work with electro-spray ionization mass spectrometry (ESI-MS) in nitrate and sulfate media (see Figures B1-B2 in Appendix B). Following the same reasoning, perchlorate should coordinate the weakest, and is indeed

known to adsorb rather weakly on electrode surfaces⁶⁵⁻⁶⁸ so it is expected that catalytic activity shows its maximum in this medium. The other anions show intermediate activities which suggest that they can bind to the iridium sites but not as strong as nitrate does. It has been reported that iridium electrodes can reduce nitrate in sulfuric acid media,⁶⁹ which suggest bisulphate should adsorb less strongly than nitrate on iridium surfaces, in agreement with the higher catalytic activity for oxygen evolution in sulfuric media. Sulfate anions adsorb weaker than phosphate species;⁶⁷ therefore, it is reasonable that bisulphate (lower charge) adsorbs more weakly than dihydrogenphosphate, explaining the higher catalytic activity in sulfuric acid media compared to phosphoric acid.

The results above show that when studying the catalytic activity of iridium-based molecular catalysts using nitrate salts of cerium (IV) as chemical oxidant, one should be aware the inhibitory effect of nitrate. Kinetic parameters such as turnover frequency or turnover number for water oxidation measured in that way may therefore be lower than their optimal values.

Turnover frequencies extracted from the electrochemical experiments with the immobilized catalyst in Figure 1 are summarized in Table 1 and compared to the value reported in solution.³² The TOFs were taken at the standard equilibrium potential for the couple $\text{Ce}^{4+}/\text{Ce}^{3+}$, 1.72 V vs. SHE⁴⁵ or 1.66 V vs. RHE at pH 1, as that was the chemical oxidant used for the homogeneous experiment. We note however that the real oxidation potential in homogeneous experiments is different, due to lack of Ce^{3+} at the beginning of the experiment, as explained in the Introduction. Electrochemical currents were converted into turnover frequencies using Faraday's law, *i.e.* $\text{TOF} = I_{\text{normalized}} / 4F$, assuming 100% faradaic efficiency for the reaction (1):



Table 1. Turnover frequency for water oxidation by iridium-N-dimethylimidazolin-2-ylidene in solution and immobilized on the gold electrode surface.

Anion	Turnover frequency (mol O ₂ [mol catalyst] ⁻¹ s ⁻¹)	
	Catalyst in solution ² pH= 0.8	Immobilized catalyst pH=1, E= 1.66 V vs. RHE
Perchlorate	-----	2.9 ± 0.2
Hydrogen sulfate	-----	2.2 ± 0.2
Dihydrogen phosphate	-----	1.1 ± 0.4
Nitrate	0.34	0.8 ± 0.1

The reported turnover frequency for the molecular complex in solution² is in reasonable agreement with the value reported in this work using the immobilized catalyst, but we emphasize that a quantitative comparison is not meaningful for the reasons mentioned in the Introduction. Also, one should consider the difference in concentration of nitrate used in each case; the results in this work were obtained in 0.1 M solution of nitric acid, meaning a nominal concentration of 0.1 M in nitrate, while the kinetic data reported for the catalyst in solution² were obtained in 0.09 M of (NH₄)₂Ce(NO₃)₆. In the latter case, the nominal concentration of nitrate in solution will depend on how labile the nitrate groups in the cerium complex are. The nitrate concentration may be almost six times higher than used in this work, having a corresponding effect on the catalytic activity.

Turnover frequencies in table 1 send a clear message in terms of the conditions that should be used to study the catalytic activity for oxygen evolution of molecular catalysts in solution: in selecting the chemical oxidant to drive the reaction, one should consider the effect of the anions because they may and actually will affect the kinetic data obtained. The best option is not to use chemical oxidants at all and drive the reaction electrochemically at controlled pH, in which case the overpotential will be properly defined along the experiment.

3.3.2. Effect of the pH on the catalytic activity of the molecular complex

Figure 3 shows the current-potential profile for water oxidation in perchlorate solutions at different pH. Interestingly, there is a maximum in activity at a pH close or higher than 3, while the activity is almost negligible in alkaline pH. Figure 3 suggests the existence of a pH for which the activity reaches a maximum value between pH 3 and 11, but the intermediate pH's are not achievable in perchlorate media due to the poor buffering capacity of this electrolyte. Additional experiments were performed in phosphate buffer to study the catalytic activity at intermediate pH and results are summarized in Figure 4, showing that in phosphate media the maximum appears to be located around pH 4.

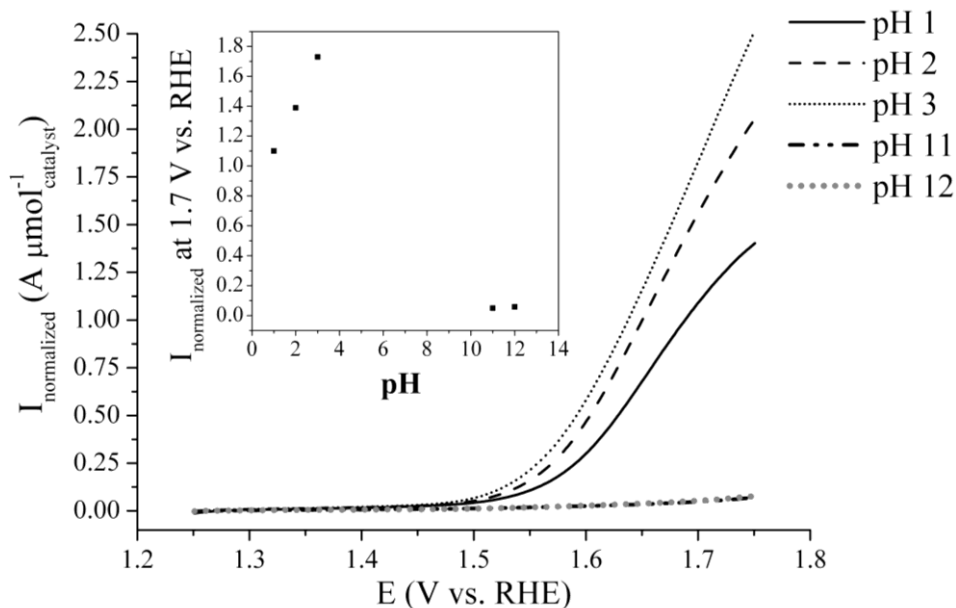


Figure 3. Current-potential profile for water oxidation catalyzed by iridium-N-dimethylimidazolin-2-ylidene immobilized on gold, obtained under hydrodynamic conditions at different pH in perchlorate media. Scan rate: 0.005 V s^{-1} . Rotation rate: 1500 RPM. Insert: Current (activity) measured at 1.7 V vs. RHE.

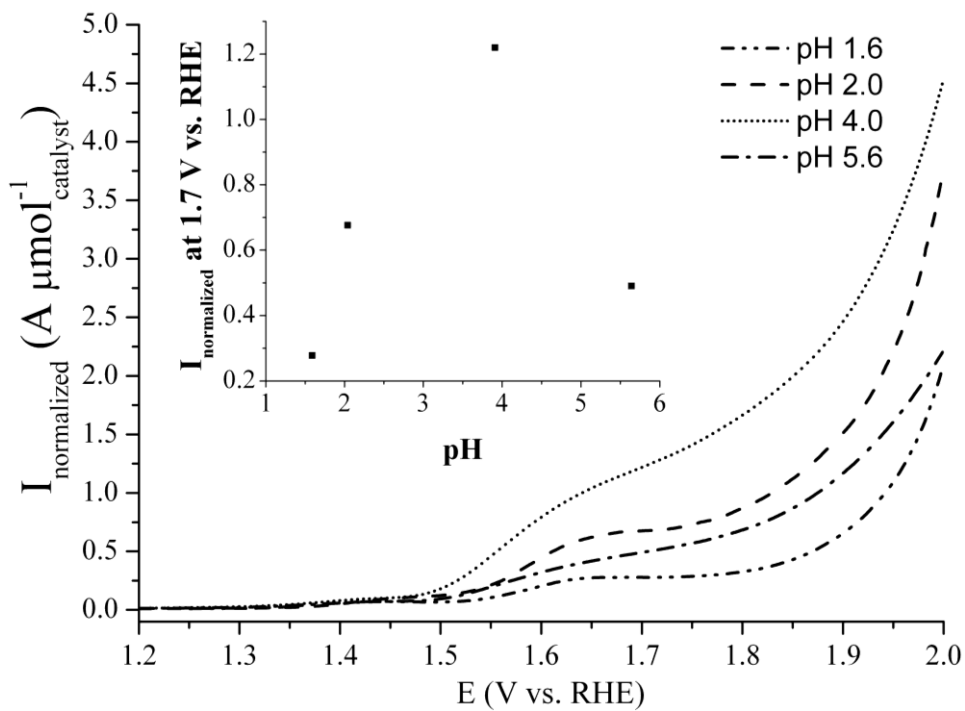


Figure 4. Current-potential profiles for water oxidation catalyzed by iridium-N-dimethylimidazolin-2-ylidene immobilized on gold, obtained with phosphate buffer at different pH. Scan rate: 0.001 V s^{-1} . Insert: Current (activity) measured at 1.7 V vs. RHE.

Nakagawa *et al.*⁷⁰ studied the catalytic activity of mesoporous iridium oxide as a function of pH, in phosphate buffer; their results showed that it does not depend on pH. Therefore, the strong pH dependence of the catalytic activity of the complex observed in Figure 3 and 4 supports the idea that the organometallic structure of the catalyst remains intact under the anodic working conditions, meaning that the active form of the catalyst is not iridium oxide as it has been reported in the literature^{56,71} for similar molecular catalysts. In addition, the pH dependence of the catalytic activity suggests the importance of decoupled proton-electron transfer steps in the overall OER mechanism.⁷²

The above results show that the catalytic activity of a given molecular compound for water oxidation can be tuned by carefully controlling the pH and anions. In the specific case studied here, the activity of iridium-N-dimethylimidazolin-2-ylidene complex for oxygen evolution, reported to be among the highest reported³², can be enhanced *ca.* 20 times by working in perchlorate media at a pH close to 3.

3.3.3. The stability of the molecular catalyst: SERS and OLEMS experiments.

In situ surface enhanced Raman spectra with the Ir-NHC-Me₂ complex immobilized on roughened gold were acquired in 0.1 M HClO₄ in a potential region prior to water oxidation as a function of the applied potential, as summarized in Figure 5.

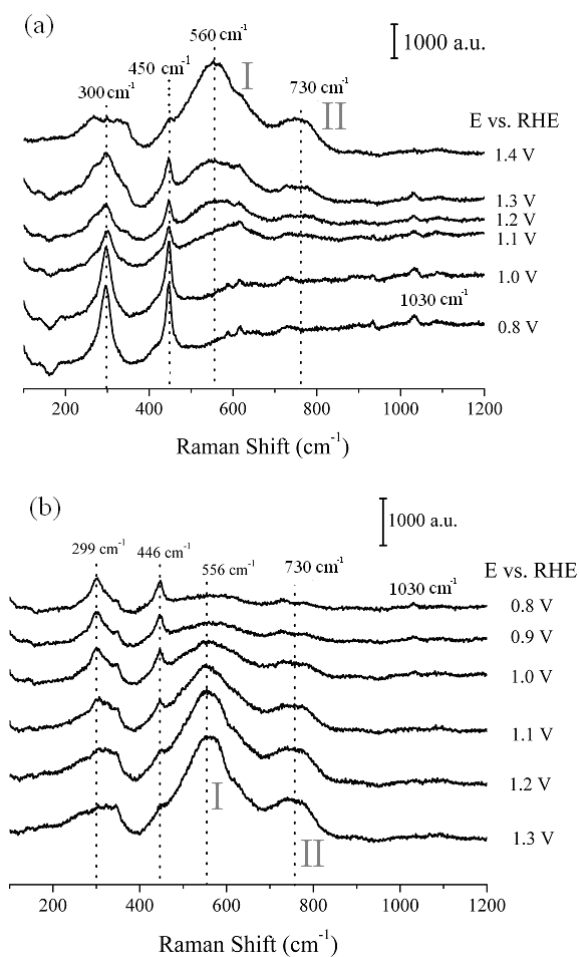


Figure 5. SERS spectra of by iridium-N-dimethylimidazolin-2-ylidene on gold, acquired under potentiostatic conditions in 0.1 M HClO₄: a) Spectra obtained by increasing the potential stepwise from 0.8 to 1.4 V vs. RHE. b) Spectra acquired after a) and by decreasing the potential stepwise back to 0.8 V vs. RHE.

The spectra in Figure 5a show two peaks located at *ca.* 300 cm^{-1} and 450 cm^{-1} at low potential which remain visible at positive potentials albeit with lower intensity. These peaks did not show isotope shifts in deuterated or ^{18}O media (see Figure B3 in Appendix B) which suggest that the vibration modes do not involve protons or oxygen atoms. Raman spectra were also obtained for the Di- μ -chloro-bis[chloro(pentamethylcyclopentadienyl)iridium(III)], and the Di-chloro-N-dimethylimidazolin-2-ylidene-(pentamethylcyclopentadienyl)iridium(III) complexes in normal Raman mode (see Figure B4 in Appendix B). The spectra of the first compound shows two peaks at *ca.* 450 cm^{-1} and 460 cm^{-1} , which merges into one at *ca.* 450 cm^{-1} for the N-dimethylimidazolin-2-ylidene compound, which has only one Cp^* ligand. Other metal-cyclopentadienyl complexes like ruthenocene and osmocene are reported⁷³ to show bending of the cyclopentadienyl ring in the region around 450 cm^{-1} . Comparison of the normal Raman spectra of Di- μ -chloro-bis[chloro(pentamethylcyclopentadienyl)iridium(III)], and Di-chloro-N-dimethylimidazolin-2-ylidene-(pentamethylcyclopentadienyl)iridium(III) with the surface enhanced Raman in Figure 5 in combination with the evidence reported for the metallocenes, let us conclude that the peak at 450 cm^{-1} corresponds to the bending vibration of the iridium- Cp^* bond. Neither the Di- μ -chloro-bis[chloro(pentamethylcyclopentadienyl)iridium(III)] compound nor the Di-chloro-N-dimethylimidazolin-2-ylidene-(pentamethylcyclopentadienyl)iridium(III) complex showed Raman peaks at 300 cm^{-1} , suggesting that the observed peak in Figure 4 does not correspond to vibrational modes of the absorbed complex, although we cannot make a proper assignment of the peak at 300 cm^{-1} based on our results.

Regarding to the Cp^* moiety, Crabtree *et al.*⁵⁶ reported that for an iridium-based molecular catalyst similar to the complex studied in this work, the Cp^* acts a sacrificial placeholder that is lost in the activation process of the catalyst. The evidence in that work shows that the activation process involves the formation of a planar bis- μ -oxo Di-iridium(IV) compound and the computational DFT calculations showed that this activated form of the catalyst has four Raman active vibrational modes in the regions 717-722 cm^{-1} and 525-532 cm^{-1} . Those modes are expected to be sensitive to oxygen isotope labeling, showing a shift between 28-41 cm^{-1} .

The peaks I and II in Figure 5a agree with the expected vibrations for the μ -oxo dimer proposed by Crabtree *et al.* and, as can be observed in Figure B3 in Appendix B, both peaks show sensitivity to oxygen labeling. The isotopic shifts in $^{18}\text{OH}_2$, $^{16}\text{OH}_2$ and D_2O are summarized in Table B1 in Appendix B. The shift observed in the ^{18}O labeled water also fits with that predicted for the μ -oxo dimer. Furthermore, the observed lack of an isotope shift in deuterated media would imply that the vibrational mode does not involve any protonated species.

Figure 5b shows that the peak corresponding to the Ir-Cp* vibration (peak at *c.a.* 450 cm^{-1}) is regenerated when the potential is set back to the original values, suggesting that the dimerization process is reversible with potential and that the Cp* is not irreversibly lost during activation process of the complex, as stated by Crabtree *et al.*

SER spectra of chemically synthesized IrO_x nanoparticles⁷⁰ drop casted on a gold electrode were also measured and are shown in Figure C5 of Appendix C, corresponding well with the spectra reported in the literature.^{74,75} These spectra are clearly different from the spectra obtained for the iridium-N-dimethylimidazolin-2-ylidene compound, suggesting that the latter is not decomposed to iridium oxide.

The stability of the molecular complex was also confirmed by OLEMS, monitoring *in situ* the production of O_2 and CO_2 during the experiment in order to check whether the organic moieties in the complex oxidize during the catalytic oxygen evolution. Figure 6 shows the current signal and the mass signals for O_2 (m/z 32) and CO_2 (m/z 44).

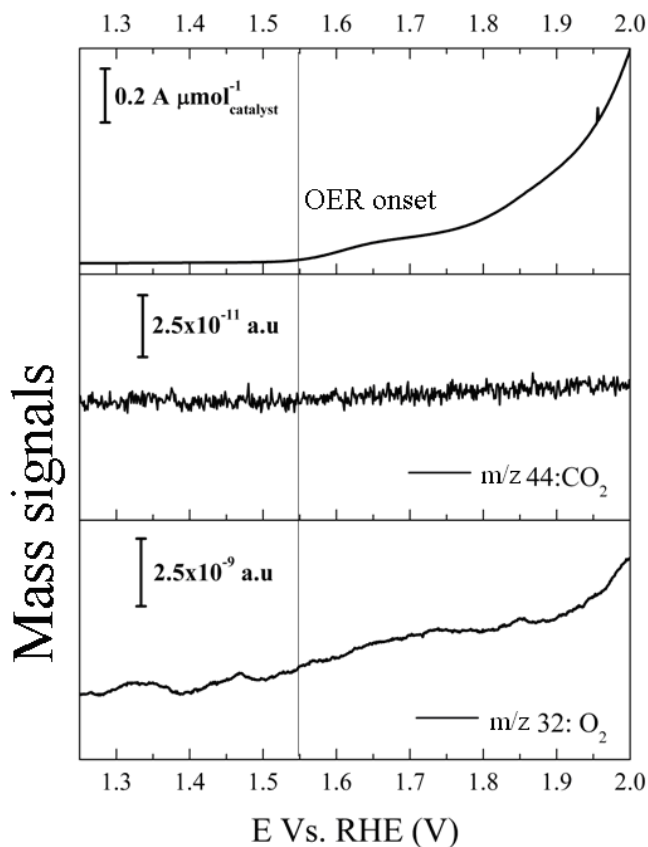


Figure 6. OLEMS signal acquired during electrochemical water oxidation in 0.1 M HClO₄ and catalyzed by iridium-N-dimethylimidazolin-2-ylidene on gold. Scan rate: 0.001 V s⁻¹

Figure 6 allows estimating the onset potential for the water oxidation on the iridium-N-dimethylimidazolin-2-ylidene complex as the potential at which the signal *m/z* 32 starts rising: *ca.* 1.55 V vs. RHE. The most important feature that can be observed in Figure 6 is the lack of a potential dependence of the mass signal of CO₂; the signal is almost flat in the potential region corresponding to water oxidation. These results show that the iridium-N-dimethylimidazolin-2-ylidene compound forms negligible amounts of carbon dioxide under oxidizing conditions, suggesting that the organic moieties are stable. Combined with the

results obtained by SERS and pH dependence, we can conclude that the molecular complex studied in this work does not form iridium oxide during the catalytic reaction.

3.4. Conclusions

We studied the effect of working conditions on the activity and stability of an iridium-N-dimethylimidazolin-2-ylidene molecular catalyst adsorbed on gold by using a variety of electrochemical and spectroelectrochemical techniques. The advantage of studying immobilized molecular catalysts lies in the better defined thermodynamic driving force through the applied electrode potential, and in the ability to use spectroelectrochemical techniques to assess catalyst stability and to obtain molecular-level insight into the reaction mechanism. The turnover rate towards water oxidation of the iridium-based organometallic compound, which we define as the reaction rate per adsorbed catalyst molecule at a pre-defined electrode potential, is strongly dependent on the nature of the electrolyte anions, which may be ascribed to a competition between the anion and water for coordination, and on the electrolyte pH, with an optimal pH close to 4 and with hardly any activity in alkaline media. By suitably tuning pH and electrolyte, the TOF for water oxidation can be enhanced by a factor of 20. *In situ* SERS experiments showed that the active state of the molecular catalyst may involve a bis- μ -oxo iridium dimer that is reversibly formed when the potential is scanned to positive values. The SERS and online electrochemical mass spectrometry experiments together with the pH dependence show that the iridium-based molecular complex does not decompose into iridium oxide during the oxygen evolution reaction. As a final more general conclusion, it is essential to clearly define electrolyte pH, electrolyte anion (or electrolyte composition in general), and thermodynamic driving force (electrode potential) in any meaningful comparison of turnover frequencies between different molecular water splitting catalysts.

3.5. Acknowledgments

This work was also supported by the Netherlands Organization for Scientific Research (NWO) and in part by the BioSolar Cells open innovation consortium, supported by the Dutch Ministry of Economic Affairs, Agriculture and Innovation. Dr. D. Hetterscheid and

Prof. Dr. J. Reek are kindly acknowledged for the synthesis of the iridium complex and its MS / NMR characterization. Special thanks to T. Hersbach for his assistance with the spectroelectrochemical experiments.

REFERENCES

- (1) Gersten, S. W.; Samuels, G. J.; Meyer, T. J. *J. Am. Chem. Soc.* **1982**, *104*, 4029.
- (2) Hettler, D. G. H.; Reek, J. N. H. *Angew. Chem. Int. Ed.* **2012**, *51*, 9740.
- (3) Wasylenko, D. J.; Palmer, R. D.; Berlinguette, C. P. *Chem. Commun.* **2013**, *49*, 218.
- (4) Sala, X.; Romero, I.; Rodriguez, M.; Escriche, L.; Llobet, A. *Angewandte Chemie-International Edition* **2009**, *48*, 2842.
- (5) Wasylenko, D. J.; Ganesamoorthy, C.; Koivisto, B. D.; Henderson, M. A.; Berlinguette, C. P. *Inorg. Chem.* **2010**, *49*, 2202.
- (6) Wasylenko, D. J.; Ganesamoorthy, C.; Henderson, M. A.; Koivisto, B. D.; Osthoff, H. D.; Berlinguette, C. P. *J. Am. Chem. Soc.* **2010**, *132*, 16094.
- (7) Concepcion, J. J.; Tsai, M. K.; Muckerman, J. T.; Meyer, T. J. *J. Am. Chem. Soc.* **2010**, *132*, 1545.
- (8) Concepcion, J. J.; Jurss, J. W.; Norris, M. R.; Chen, Z. F.; Templeton, J. L.; Meyer, T. J. *Inorg. Chem.* **2010**, *49*, 1277.
- (9) Concepcion, J. J.; Jurss, J. W.; Brennaman, M. K.; Hoertz, P. G.; Patrocino, A. O. T.; Iha, N. Y. M.; Templeton, J. L.; Meyer, T. J. *Acc. Chem. Res.* **2009**, *42*, 1954.
- (10) Duan, L. L.; Araujo, C. M.; Ahlquist, M. S. G.; Sun, L. C. *Proc. Natl. Acad. Sci. U. S. A.* **2012**, *109*, 15584.
- (11) Duan, L. L.; Bozoglian, F.; Mandal, S.; Stewart, B.; Privalov, T.; Llobet, A.; Sun, L. C. *Nat. Chem.* **2012**, *4*, 418.
- (12) Nyhlen, J.; Duan, L. L.; Akermark, B.; Sun, L. C.; Privalov, T. *Angewandte Chemie-International Edition* **2010**, *49*, 1773.
- (13) Duan, L. L.; Fischer, A.; Xu, Y. H.; Sun, L. C. *J. Am. Chem. Soc.* **2009**, *131*, 10397.

- (14) Kaveevivitchai, N.; Chitta, R.; Zong, R. F.; El Ojaimi, M.; Thummel, R. P. *J. Am. Chem. Soc.* **2012**, *134*, 10721.
- (15) Boyer, J. L.; Polyansky, D. E.; Szalda, D. J.; Zong, R. F.; Thummel, R. P.; Fujita, E. *Angewandte Chemie-International Edition* **2011**, *50*, 12600.
- (16) Yamazaki, H.; Hakamata, T.; Komi, M.; Yagi, M. *J. Am. Chem. Soc.* **2011**, *133*, 8846.
- (17) Yoshida, M.; Masaoka, S.; Abe, J.; Sakai, K. *Chemistry-an Asian Journal* **2010**, *5*, 2369.
- (18) Lopez, I.; Ertem, M. Z.; Maji, S.; Benet-Buchholz, J.; Keidel, A.; Kuhlmann, U.; Hildebrandt, P.; Cramer, C. J.; Batista, V. S.; Llobet, A. *Angewandte Chemie-International Edition* **2014**, *53*, 205.
- (19) Maji, S.; Vigara, L.; Cottone, F.; Bozoglian, F.; Benet-Buchholz, J.; Llobet, A. *Angewandte Chemie-International Edition* **2012**, *51*, 5967.
- (20) Mola, J.; Dinoi, C.; Sala, X.; Rodriguez, M.; Romero, I.; Parella, T.; Fontrodona, X.; Llobet, A. *Dalton Transactions* **2011**, *40*, 3640.
- (21) Karlsson, E. A.; Lee, B. L.; Akermark, T.; Johnston, E. V.; Karkas, M. D.; Sun, J. L.; Hansson, O.; Backvall, J. E.; Akermark, B. *Angewandte Chemie-International Edition* **2011**, *50*, 11715.
- (22) Limburg, J.; Vrettos, J. S.; Liable-Sands, L. M.; Rheingold, A. L.; Crabtree, R. H.; Brudvig, G. W. *Science* **1999**, *283*, 1524.
- (23) Limburg, J.; Vrettos, J. S.; Chen, H. Y.; de Paula, J. C.; Crabtree, R. H.; Brudvig, G. W. *J. Am. Chem. Soc.* **2001**, *123*, 423.
- (24) Fillol, J. L.; Codola, Z.; Garcia-Bosch, I.; Gomez, L.; Pla, J. J.; Costas, M. *Nat. Chem.* **2011**, *3*, 807.
- (25) Ellis, W. C.; McDaniel, N. D.; Bernhard, S.; Collins, T. J. *J. Am. Chem. Soc.* **2010**, *132*, 10990.
- (26) Wasylenko, D. J.; Ganesamoorthy, C.; Borau-Garcia, J.; Berlinguette, C. P. *Chem. Commun.* **2011**, *47*, 4249.
- (27) Yin, Q. S.; Tan, J. M.; Besson, C.; Geletii, Y. V.; Musaev, D. G.; Kuznetsov, A. E.; Luo, Z.; Hardcastle, K. I.; Hill, C. L. *Science* **2010**, *328*, 342.

- (28) Dogutan, D. K.; McGuire, R.; Nocera, D. G. *J. Am. Chem. Soc.* **2011**, *133*, 9178.
- (29) Barnett, S. M.; Goldberg, K. I.; Mayer, J. M. *Nat. Chem.* **2012**, *4*, 498.
- (30) Zhang, M. T.; Chen, Z. F.; Kang, P.; Meyer, T. J. *J. Am. Chem. Soc.* **2013**, *135*, 2048.
- (31) Chen, Z. F.; Meyer, T. J. *Angewandte Chemie-International Edition* **2013**, *52*, 700.
- (32) Hetterscheid, D. G. H.; Reek, J. N. H. *Chem. Commun.* **2011**, *47*, 2712.
- (33) Hintermair, U.; Hashmi, S. M.; Elimelech, M.; Crabtree, R. H. *J Am Chem Soc* **2012**, *134*, 9785.
- (34) Brewster, T. P.; Blakemore, J. D.; Schley, N. D.; Incarvito, C. D.; Hazari, N.; Brudvig, G. W.; Crabtree, R. H. *Organometallics* **2011**, *30*, 965.
- (35) Parent, A. R.; Blakemore, J. D.; Brudvig, G. W.; Crabtree, R. H. *Chem. Commun.* **2011**, *47*, 11745.
- (36) Blakemore, J. D.; Schley, N. D.; Balcells, D.; Hull, J. F.; Olack, G. W.; Incarvito, C. D.; Eisenstein, O.; Brudvig, G. W.; Crabtree, R. H. *J. Am. Chem. Soc.* **2010**, *132*, 16017.
- (37) Petronilho, A.; Rahman, M.; Woods, J. A.; Al-Sayyed, H.; Muller-Bunz, H.; MacElroy, J. M. D.; Bernhard, S.; Albrecht, M. *Dalton Transactions* **2012**, *41*, 13074.
- (38) Lalrempuia, R.; McDaniel, N. D.; Muller-Bunz, H.; Bernhard, S.; Albrecht, M. *Angewandte Chemie-International Edition* **2010**, *49*, 9765.
- (39) McDaniel, N. D.; Coughlin, F. J.; Tinker, L. L.; Bernhard, S. *J. Am. Chem. Soc.* **2008**, *130*, 210.
- (40) Bucci, A.; Savini, A.; Rocchigiani, L.; Zuccaccia, C.; Rizzato, S.; Albinati, A.; Llobet, A.; Macchioni, A. *Organometallics* **2012**, *31*, 8071.
- (41) Savini, A.; Bellachioma, G.; Bolano, S.; Rocchigiani, L.; Zuccaccia, C.; Zuccaccia, D.; Macchioni, A. *Chemsuschem* **2012**, *5*, 1415.
- (42) Savini, A.; Bellachioma, G.; Ciancaleoni, G.; Zuccaccia, C.; Zuccaccia, D.; Macchioni, A. *Chem. Commun.* **2010**, *46*, 9218.
- (43) Parent, A. R.; Crabtree, R. H.; Brudvig, G. W. *Chem. Soc. Rev.* **2013**, *42*, 2247.
- (44) Marcus, R. A. *Angewandte Chemie International Edition in English* **1993**, *32*, 1111.

- (45) West, R. *Handbook of Chemistry and Physics*; 53rd ed.; CRC Press Cleveland, 1972.
- (46) Wasylenko, D. J.; Ganesamoorthy, C.; Henderson, M. A.; Berlinguette, C. P. *Inorg. Chem.* **2011**, *50*, 3662.
- (47) Pecht, I.; Luz, Z. *J. Am. Chem. Soc.* **1965**, *87*, 4068.
- (48) Hettler, D. G. H.; Reek, J. N. H. *Eur. J. Inorg. Chem.* **2014**, *2014*, 742.
- (49) Joya, K. S.; Subbaiyan, N. K.; D'Souza, F.; de Groot, H. J. M. *Angewandte Chemie-International Edition* **2012**, *51*, 9601.
- (50) deKrafft, K. E.; Wang, C.; Xie, Z. G.; Su, X.; Hinds, B. J.; Lin, W. B. *Acs Applied Materials & Interfaces* **2012**, *4*, 608.
- (51) Huang, J.; Blakemore, J. D.; Fazi, D.; Kokhan, O.; Schley, N. D.; Crabtree, R. H.; Brudvig, G. W.; Tiede, D. M. *PCCP* **2014**, *16*, 1814.
- (52) Blakemore, J. D.; Mara, M. W.; Kushner-Lenhoff, M. N.; Schley, N. D.; Konezny, S. J.; Rivalta, I.; Negre, C. F. A.; Snoeberger, R. C.; Kokhan, O.; Huang, J.; Stickrath, A.; Tran, L. A.; Parr, M. L.; Chen, L. X.; Tiede, D. M.; Batista, V. S.; Crabtree, R. H.; Brudvig, G. W. *Inorg. Chem.* **2013**, *52*, 1860.
- (53) Blakemore, J. D.; Schley, N. D.; Olack, G. W.; Incarvito, C. D.; Brudvig, G. W.; Crabtree, R. H. *Chem. Sci.* **2011**, *2*, 94.
- (54) Venturini, A. B., A.; Reek, J. N. H.; Hettler, D. G. H. *Chemistry - A European Journal* **2014**, *chem.201303796*.
- (55) Zhou, M.; Balcells, D.; Parent, A. R.; Crabtree, R. H.; Eisenstein, O. *Acs Catal* **2012**, *2*, 208.
- (56) Hintermair, U.; Sheehan, S. W.; Parent, A. R.; Ess, D. H.; Richens, D. T.; Vaccaro, P. H.; Brudvig, G. W.; Crabtree, R. H. *J. Am. Chem. Soc.* **2013**, *135*, 10837.
- (57) Hong, D. C.; Murakami, M.; Yamada, Y.; Fukuzumi, S. *Energ Environ Sci* **2012**, *5*, 5708.
- (58) Grotjahn, D. B.; Brown, D. B.; Martin, J. K.; Marelius, D. C.; Abadjian, M. C.; Tran, H. N.; Kalyuzhny, G.; Vecchio, K. S.; Specht, Z. G.; Cortes-Llamas, S. A.; Miranda-Soto, V.; van Niekerk, C.; Moore, C. E.; Rheingold, A. L. *J. Am. Chem. Soc.* **2011**, *133*, 19024.

- (59) Diaz-Morales, O.; Calle-Vallejo, F.; de Munck, C.; Koper, M. T. M. *Chemical Science* **2013**, *4*, 2334.
- (60) Lai, S. C. S.; Kleyn, S. E. F.; Rosca, V.; Koper, M. T. M. *The Journal of Physical Chemistry C* **2008**, *112*, 19080.
- (61) Gao, P.; Gosztola, D.; Leung, L. W. H.; Weaver, M. J. *J. Electroanal. Chem.* **1987**, *233*, 211.
- (62) Wonders, A. H.; Housmans, T. H. M.; Rosca, V.; Koper, M. T. M. *J Appl Electrochem* **2006**, *36*, 1215.
- (63) Duca, M.; van der Klugt, B.; Koper, M. T. M. *Electrochim. Acta* **2012**, *68*, 32.
- (64) Feng, Y.; Jiang, B.; Boyle, P. A.; Ison, E. A. *Organometallics* **2010**, *29*, 2857.
- (65) Borkowska, Z.; Slimming, U. *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry* **1991**, *312*, 237.
- (66) Clavilier, J.; Van Huong, C. N. *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry* **1977**, *80*, 101.
- (67) Silva, F.; Martins, A. *J. Electroanal. Chem.* **1999**, *467*, 335.
- (68) Angerstein-Kozłowska, H.; Conway, B. E.; Hamelin, A.; Stoicoviciu, L. *Electrochim. Acta* **1986**, *31*, 1051.
- (69) Dima, G. E.; de Voors, A. C. A.; Koper, M. T. M. *J. Electroanal. Chem.* **2003**, *554–555*, 15.
- (70) Nakagawa, T.; Beasley, C. A.; Murray, R. W. *J. Phys. Chem. C* **2009**, *113*, 12958.
- (71) Limburg, B.; Bouwman, E.; Bonnet, S. *Coord. Chem. Rev.* **2012**, *256*, 1451.
- (72) Koper, M. T. M. *Chemical Science* **2013**, *4*, 2710.
- (73) Lokshin, B. V.; Aleksanian, V. T.; Rusach, E. B. *J. Organomet. Chem.* **1975**, *86*, 253.
- (74) Musić, S.; Popović, S.; Maljković, M.; Skoko, Z.; Furić, K.; Gajović, A. *Mater. Lett.* **2003**, *57*, 4509.
- (75) Thanawala, S.; Georgiev, D. G.; Baird, R. J.; Auner, G. *Thin Solid Films* **2007**, *515*, 7059.