



Universiteit  
Leiden  
The Netherlands

## Probing quantum materials with novel scanning tunneling microscopy techniques

Bastiaans, K.M.

### Citation

Bastiaans, K. M. (2019, December 10). *Probing quantum materials with novel scanning tunneling microscopy techniques*. *Casimir PhD Series*. Retrieved from <https://hdl.handle.net/1887/81815>

Version: Publisher's Version

License: [Licence agreement concerning inclusion of doctoral thesis in the Institutional Repository of the University of Leiden](#)

Downloaded from: <https://hdl.handle.net/1887/81815>

**Note:** To cite this publication please use the final published version (if applicable).

Cover Page



Universiteit Leiden



The handle <http://hdl.handle.net/1887/81815> holds various files of this Leiden University dissertation.

**Author:** Bastiaans, K.M.

**Title:** Probing quantum materials with novel scanning tunneling microscopy techniques

**Issue Date:** 2019-12-10

# 4

## Imaging doubled shot noise in a Josephson Scanning Tunneling Microscope

This chapter has been published as *Physical Review B* **100**, 104506 (2019)

We have imaged the current noise with atomic resolution in a Josephson scanning tunneling microscope with a Pb-Pb junction. By measuring the current noise as a function of applied bias, we reveal the change from single electron tunneling above the superconducting gap energy to double electron charge transfer below the gap energy when Andreev processes become dominant. Our spatially resolved noise maps show that this doubling occurs homogeneously on the surface, and also on impurity locations, demonstrating that indeed the charge pairing is not influenced by disruptions in the superconductor smaller than the superconducting coherence length.



## 4.1. INTRODUCTION

The coupling between two macroscopic superconducting electrodes through an insulating layer can lead to a dissipationless current called the Josephson supercurrent. The critical current  $I_C$  is the maximal supercurrent that the junction can sustain; it is related to the individual superconducting order parameters in both electrodes, as well as their coupling [1]. In the zero-voltage limit, this supercurrent is carried by paired electrons (Cooper pairs), carrying twice the electron charge  $e$ . Applying a bias voltage  $V_B$  larger than twice the pair-breaking gap energy  $\Delta$ ,  $eV_B > 2\Delta$ , over the junction results in a normal current carried predominantly by quasiparticles with a single-electron charge (Fig. 4.1.b). In the energy range below the gap edge, only the so-called Andreev reflection processes can transport the quasiparticles across the junction by reflecting particles carrying the opposite charge. These processes lead to the effective charge transfer of multiple electron charges [2–4]. In the energy range  $\Delta < eV_B < 2\Delta$ , the dominant process is a single Andreev reflection leading to the transfer of effectively double the electron charge, as illustrated in Fig. 4.1.c.

One cannot tell from the time-averaged value of the current whether it is carried by multiple integers of charge, but this becomes apparent when measuring the fluctuations of the current, or in other words, the current noise [5–10]. In general, the noise originating from the flow of uncorrelated particles in a tunneling junction (shot noise) is a purely Poissonian process. The current noise power  $S_I$  is then proportional to the charge  $q$  and the current  $I$  of the carriers,  $S = 2q|I|$  [5]. At lower bias voltages, when Andreev processes become relevant, the transferred charge in a Josephson junction can effectively double and therefore the noise is also expected to be two times the Poissonian value [11, 12]. Spectroscopic noise measurements in mesoscopic systems have revealed such noise signatures of multiple electron charge transport in superconducting junctions associated with Andreev processes [6–10], as well as fractional charges in quantum hall systems [13, 14] and the vanishing of shot noise at atomic-scale point contacts [15–17].

In this chapter we perform such noise spectroscopy measurements spatially resolved with atomic resolution in a Josephson scanning tunneling microscope. We use our recently developed scanning tunneling noise microscopy (STNM) technique to spatially resolve the current and its time-resolved fluctuations simultaneously with atomic resolution, as discussed in chapters 2 and 3 [18]. We first demonstrate the current noise doubling from single to double charge transfer below the gap edge in a junction between a superconducting Pb tip and a Pb(111) sample. We then visualize this noise enhancement by spatially mapping the effective charge transfer over the sample surface. We show that it is homogeneous over the sample surface, also including impurity locations, demonstrating that the charge pairing is not influenced by disruptions smaller than the coherence length ( $\xi \sim 80$  nm in Pb).

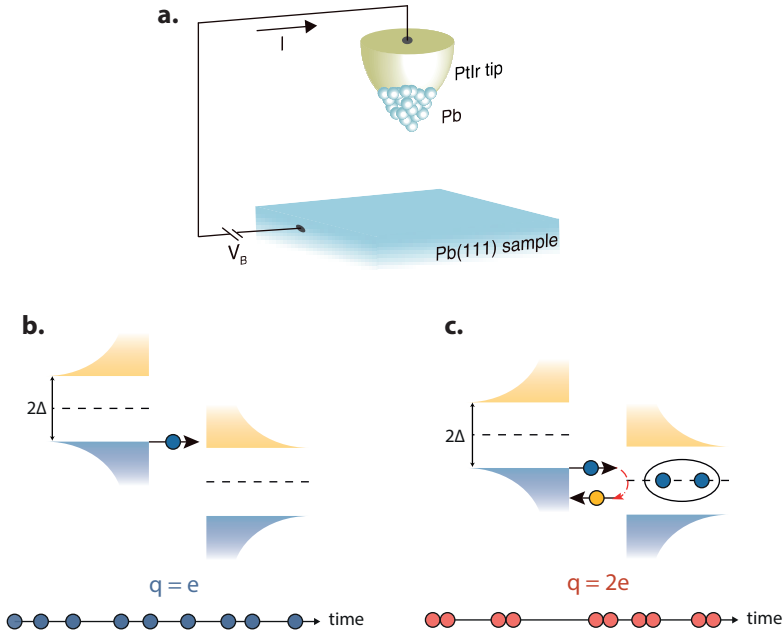


Figure 4.1: **a.** Schematics of a Josephson scanning tunneling microscope. The SIS junction consists of a Pb-coated tip ( $\Delta_{\text{tip}} = 1.31$  meV) and an atomically flat Pb(111) surface ( $\Delta_{\text{sample}} = 1.35$  meV) separated by a thin vacuum barrier. **b.** Normal current carried by quasiparticles transferring single electron charge. The characteristic density of states of both superconducting electrodes are shown, with filled and empty states denoted by blue and yellow separated by the pair-breaking gap  $2\Delta_{\text{tip/sample}}$ . **c.** Andreev reflection process. An electron transfers a Cooper-pair into the superconducting condensate by reflecting a hole in the opposite direction, effectively transferring  $2e$  charge.

## 4.2. EXPERIMENTAL SETUP

A schematic of our setup is shown in Fig. 4.1, where a superconducting STM tip is brought in tunneling contact with a superconducting sample to form a superconductor-insulator-superconductor (SIS) junction. We create this junction in our modified low-temperature (2.2 K) Unisoku USM-1500 STM setup. First, the Pb(111) single crystal surface is cleaned by repetitive cycles of  $\text{Ar}^+$  sputtering at 1 kV with an Ar pressure of  $5.0 \times 10^{-5}$  mbar (background pressure  $< 1.0 \times 10^{-10}$  mbar) and annealing. We then push the mechanically grinded PtIr tip into the surface to decorate it with a superconducting cluster of Pb atoms until we obtain a SIS junction [19–21].

### 4.3. JOSEPHSON TUNNELING SPECTROSCOPY

To demonstrate the high quality of the SIS junction in our setup, we display its distinct spectroscopic signatures for varying normal state resistance  $R_N$  (by adjusting the bias and current setpoint) in Fig. 4.2. The first signature is visible in the single particle channel, where quasiparticles with energies larger than the pair-breaking gap transfer the charge. The tunneling spectra in Fig. 4.2.a show sharp coherence peaks, which are located at energies equal to the sum of both superconducting gaps of the tip and the sample  $2\Delta = \Delta_{\text{tip}} + \Delta_{\text{sample}} = 2.66$  meV. The clear U-shaped gap at  $13.6$  M $\Omega$  can be used as a benchmark for bulk-like superconducting properties of the tip and, also considering the low conductance, indicates that only a single transmission channel is present [22]. Due to the sharp density of states of the superconducting tip, the spectroscopic features are much sharper than one would expect from conventional thermal broadening [19]. We can fit these spectra with a modified phenomenological gap equation [23] to extract an effective electron temperature of  $2.2$  K, which is similar to the measured phonon temperature, as electron-phonon coupling is still rather efficient at these temperatures.

The next signature stems from Andreev processes that are visible at lower junction resistances. These lead to a sub-gap structure with humps in the differential conductance. Specifically, at energies below  $2\Delta/n$ , Andreev processes of order  $n$  become possible with the relative probability  $\tau^{n+1}$ , where  $\tau$  is the transparency of the junction. A small hump, indicated by the black arrows in Fig. 4.2.a-b, is visible in the differential conductance when the order of the lowest-allowed Andreev reflection process changes [2, 3].

The spectroscopic signatures related to the Josephson supercurrent in the junction are observed in the differential conductance at energies close to the Fermi level  $E_F$ : a peak that is enhanced with decreasing  $R_N$ , and small oscillations around the central peak (Fig. 4.2.b). To understand these, we first survey the energy scales in our setup. The capacitive energy  $E_C$  and the thermal energy are larger than the Josephson energy  $E_J$ . Therefore, the environmental impedance becomes a relevant quantity, and thermal phase fluctuations across the junction govern the Josephson current, shifting the maximum current to a non-zero bias [24]. Close to the Fermi energy  $E_F$  we access the Cooper-pair channel associated with the coupling between the two superconducting condensates. The prominent peak at  $E_F$  in Fig. 4.2.b, corresponding to the local maximum in the current in Fig. 4.2.c, originates from the phase fluctuating Josephson current [21, 24]. Both the maximum Josephson current and the differential conductance at zero bias are proportional to the square of the intrinsic critical current of the Josephson junction. The critical currents we obtain for these spectra show a linear relation with  $R_N$  and are consistent with the Ambegaokar-Baratoff formula (Fig. 4.2.d) [25]. We also note the small oscillating features in both the con-

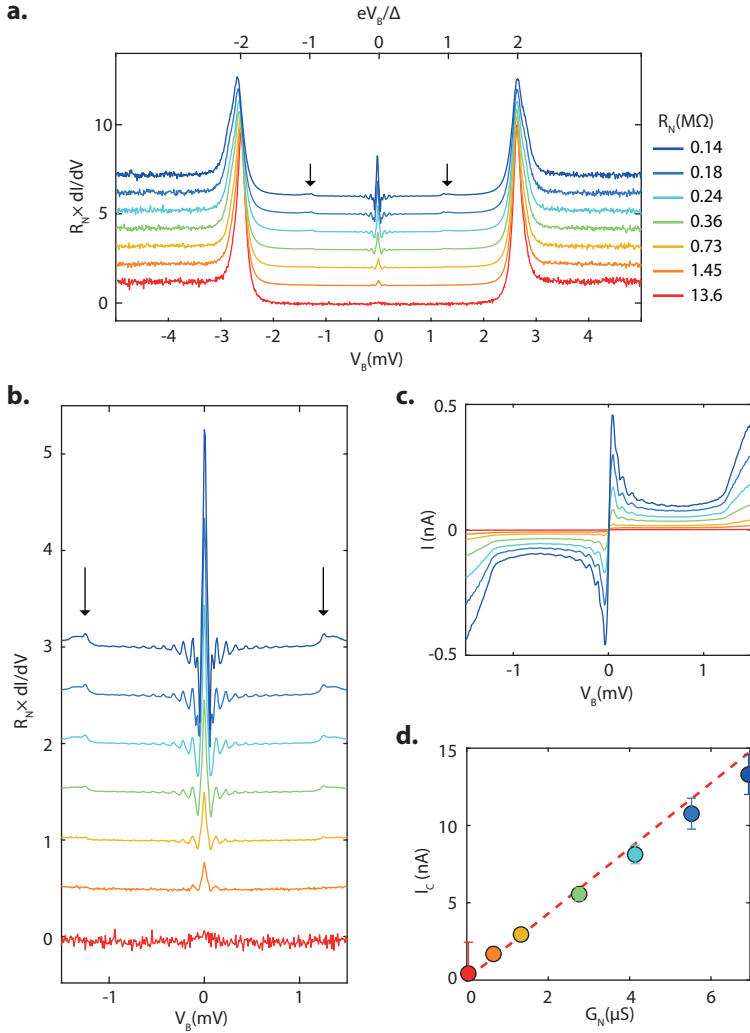


Figure 4.2: **a.** Differential conductance spectra multiplied by the normal state resistance acquired for various setup conditions. Sharp coherence peaks can be seen at  $eV_B/\Delta = \pm 2$ . The increasing conductance around  $eV_B/\Delta = \pm 1$  (arrows) with various normal state resistance indicates the presence of Andreev processes. Curves are offset for clarity. **b.** Zoom in at the low energy features in the differential conductance spectra. The prominent peak at the Fermi energy that rises with decreasing  $R_N$  is a signature of the Josephson supercurrent. Curves are offset for clarity. **c.** Current-voltage characteristics acquired simultaneously with the spectra shown in panel (b). **d.** Critical supercurrent of the junction (points) and its quantitative agreement with the Ambegaokar-Baratoff formula (red dashed line).



ductance and the current spectra stretching far out to  $\sim 1$  meV, originating from coupling of the junction with its dissipative electromagnetic environment, previously explained by a tip-induced antenna mode [21, 26].

## 4.4. NOISE SPECTROSCOPY

We now come to the central part of this chapter, where we visualize the doubling of the current noise in this scanning Josephson junction using STNM. The central challenge for measuring current noise in a conventional scanning tunneling microscope (STM) is that the temporal resolution is generally limited to only a few kHz, because the combination of the high impedance ( $\sim G\Omega$ ) tunnel junction and capacitance of the interfacing cables ( $\sim 100$  pF) form an inherent low-pass filter. As a consequence, STM usually provides a static, time-averaged picture, lacking information about possible dynamical phenomena in the junction [27], especially when requiring atomic-resolution scanning.

Our noise measurement apparatus, described in detail in chapter 2 [18], builds upon earlier high-frequency STMs [28–30] but is based on a superconducting LC resonating circuit that is connected to the Josephson junction, as illustrated in Fig. 4.3.a. Current fluctuations in the junction are converted into voltage fluctuations at resonance of the LC circuit, which are then amplified by the custom-built cryogenic amplifier [31] into a  $50 \Omega$  line. To illustrate how we extract the magnitude of the current noise in the junction, we plot several curves of the measured power spectral density in Fig. 4.3.b for various bias voltages. To mitigate the effect of a non-linear differential conductance on the effective resonator impedance, one needs to separate the measured signal into the noise components [18, 32]. The total measured voltage noise is

$$S_V^{\text{meas}}(\omega, V) = G^2 |Z_{\text{res}}|^2 S_I, \quad (4.1)$$

where  $G$  is the total gain of the amplification chain,  $Z_{\text{res}}$  the impedance of the resonating circuit and  $S_I$  the total current noise in the circuit. The strong influence of the highly non-linear differential conductance on the total impedance of the resonator is also illustrated in Fig. 4.3.b, where the clear change of the measured power spectral density for varying bias voltage is due to the simultaneously changing impedance of the resonator and the amplitude of the noise as a function of bias.

After correcting for the non-linear differential conductance, the total current noise equals

$$S_I(I) = 2q|I| \coth \frac{qV}{2k_B T} + \frac{4k_B T}{|Z_{\text{res}}|} + S_{\text{amp}}, \quad (4.2)$$

where  $q$  is the effective charge,  $T$  is the effective temperature and  $S_{\text{amp}}$  is the input noise of the amplifier. The first term represents the shot noise in the junction and the

second term represents the thermal noise. The black curves in Fig. 4.3.b represent fitting of  $S_V^{\text{meas}}(\omega, V)$  to the measured noise spectra, which we then use to obtain a value for the effective charge  $q$  transferred across the junction.

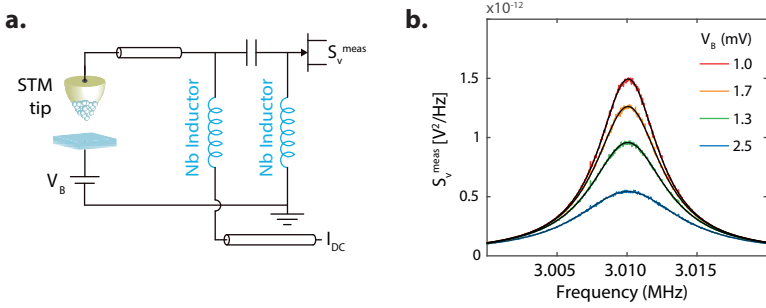


Figure 4.3: **a.** Measurement circuit of STNM, which allows for spatial mapping of the current fluctuations with atomic resolution. Superconducting niobium ( $T_C = 9.2$  K, indicated in blue) inductors are used for the resonating circuit. **b.** Power spectral density of the resonator circuit, in a small bandwidth around the resonance frequency. The different spectra represent various values of the applied bias to the Josephson junction. Measured data are plotted by the colored lines, the black curves correspond to a circuit diagram fit via Eq. 4.1.

## 4.5. DOUBLED NOISE DUE TO ANDREEV REFLECTIONS

We first measure the current noise as a function of energy at a single location. Figure 4.4.a shows the measured current noise power as a function of bias, with the zero-current noise subtracted to remove the thermal noise component and input noise of the amplifier:  $S_I(I) - S_I(0)$ . The dashed lines indicate the theoretically calculated shot-noise curves as described above, for effective charge  $e$  (blue) and  $2e$  (red). At large bias voltage the experimental data follows the noise for single-electron tunneling. However, the current noise clearly doubles from  $e$  to  $2e$  at the coherence peak energy  $eV_B/\Delta = \pm 2$ . We obtain the effective charge transferred by dividing the measured noise power by the full Poissonian noise  $S = 2e|I| \coth \frac{eV}{2k_B T}$  (Fig. 4.4.b). Note that, since we keep the junction resistance  $R_J$  constant, the transmission of the junction is changing when the bias voltage is reduced, leading to a correction of the effective  $q$  by  $(1 - \tau_n)$  with  $\tau_n \sim (G_0 R_J)^{-1/n}$  for small transparencies. The correction, applied to the data points in Fig. 4.4.b is smaller than the scatter of our data points, due to the low transparency of our junction. The clear step in effective charge as a function of applied bias at the gap energy demonstrates that the tunneling current is now effectively carried by double charge quanta due to Andreev reflection processes. This is well consistent with theoretical descriptions [2–4, 11, 12] and experimental observations in mesoscopic devices, where Andreev reflections lead to enhanced noise in nanofabricated SIS junctions [9, 10] and short diffusive normal metal – supercon-

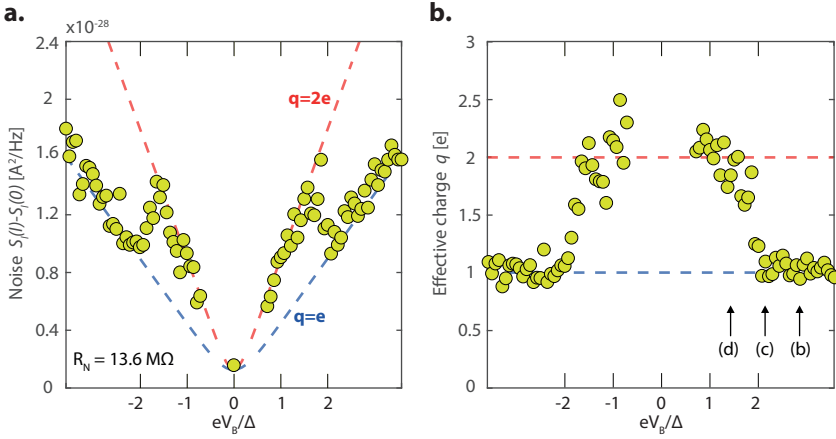


Figure 4.4: **a.** Measured current noise for varying bias voltage acquired at a random location in Fig. 4.5.a, maintaining a constant junction resistance  $R_J = 13.6 \text{ M}\Omega$ . The dashed lines represent the calculated values for an effective charge equals  $e$  (blue) and  $2e$  (red). **b.** Effective charge transferred through the Josephson junction for varying bias. The data points represent  $q = (S(I) - S(0))/2e|I|$ , similar to the Fano factor. Dashed lines indicate  $q = e$  and  $q = 2e$  lines. The black arrows indicate the bias voltage of the spatially resolved noise maps of Fig. 4.5.

ductor contacts [6, 8], but have never been seen in a STM setup or at such low transparencies. In the present project, we use transparencies of  $\tau \sim 10^{-3} - 10^{-4}$  leading to a single channel of transmission, whereas in mesoscopic devices usually multiple channels of  $\tau \sim 10^{-1}$  are involved.

## 4.6. SPATIALLY RESOLVED NOISE DOUBLING

Finally, we apply the spatial mapping capabilities of our STNM setup to resolve this doubling of the noise over the sample surface with atomic-scale resolution. Figure 4.5.a shows a topographic image of the Pb(111) surface in a 12,5 nm field of view, including a hexagonal shaped impurity previously identified as a sub-surface Ar nanocavity [33]. Next to locally reducing the scattering length, this nanocavity located beneath the surface also vertically and laterally confines charge carriers on a few nanometer length scale. We performed the noise-spectroscopy measurement in the same field of view by scanning the tip over the surface while simultaneously measuring the current noise. The spatially resolved noise maps at various bias voltages shown in Fig. 4.5.b-d, exhibit a homogeneous contrast at energies above the pair-breaking gap energy, as is expected for transfer of uncorrelated particles. Below the superconducting gap energy we again observe homogeneous contrast, but now at an elevated value of the noise power around an effective charge equal to  $2e$ . While we observe a strong contrast in the topography, these spatially resolved noise maps

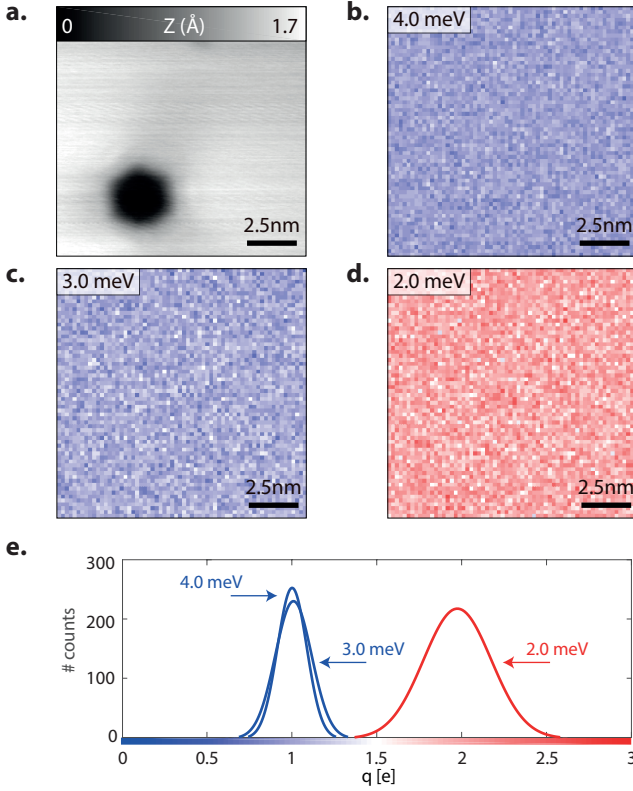


Figure 4.5: **a.** Topograph of 12,5 nm field of view on the Pb(111) surface, including a hexagonal shaped Ar nanocavity. **b-d.** Spatial imaging of the effective charge for various bias voltages measured in feedback with a normal state resistance  $R_N = 13.6 \text{ M}\Omega$ . The spatially resolved noise maps show homogeneous  $q = e$  noise for  $eV_B > 2\Delta$  (4.0 (b) and 3.0 (c) meV) and  $q = 2e$  noise for  $eV_B < 2\Delta$  (2.0 meV (d)). **e.** Distribution of the effective charge for each spatial noise map, obtained by fitting a normal distribution to the histogram of each panel.

show that the doubling occurs homogeneously over the surface, also on the location of the nanocavity. This demonstrates that disruptions in the superfluid, due to local confinement of the charge carriers or scattering on the nanocavity [33], on length scales smaller than the superconducting coherence length ( $\xi \sim 80 \text{ nm}$  in Pb), do not influence the charge pairing, since the spatially resolved current noise is unaffected. This finding is in line with STM experiments showing that Andreev reflections are virtually unaffected by small diameter molecules [34].

## 4.7. CONCLUSIONS AND OUTLOOK

In this chapter we measured doubled shot noise caused by Andreev reflections in a Josephson scanning tunneling microscope using noise spectroscopy measurements. We spatially resolved this doubling with atomic-scale resolution on the surface of the conventional superconductor Pb(111). The ability to spatially resolve the charge dynamics with such precision opens new paths for investigating many-body correlation effects in quantum materials.

As we have seen in chapter 3, scanning noise spectroscopy led to a novel understanding of cuprate high-temperature superconductors, where the discovery of charge trapping dynamics suggests a picture of copper-oxide planes separated by thin insulating layers within the three-dimensional superconducting state [35, 36]. But the list of potential for STNM is a continuously growing one; we believe that atomically resolved noise measurements will also reveal new insight in fluctuating stripe order [37] and pre-formed pairing in the pseudogap regime [38, 39]. One could imagine a similar experiment like the one presented in this chapter being performed on a cuprate high-temperature superconductor. If the sample would be in the superconducting phase one would expect to measure similar noise doubling as for the Pb-Pb junction in this chapter, but then with one of the gaps  $\Delta_{\text{sample}}$  shifted to the relative value of the cuprate superconductor. The real interesting question would be what will happen if one would then tune the cuprate sample into the pseudogap regime. This phase is sometimes considered to be a precursor phase of superconductivity, hosting pre-formed pairs [39, 40]. A direct measurement of the effective charge of the carries would help to resolve the real nature of this phase.

Further examples of potential experiments where our scanning noise technique could lead to new insights include Kondo effects in heavy fermion systems, where the shot noise exhibits a characteristic bias dependence arising from Kondo screening, depending on the ratio of the different tunneling amplitudes [41, 42]. Finally, similar noise investigations as presented in this chapter could also reveal signatures of Majorana zero-modes in one-dimensional chains of atoms on a superconducting surface [43, 44].

## BIBLIOGRAPHY

- [1] B. D. Josephson, *Possible new effects in superconductive tunnelling*, Phys. Lett. **1**, 251 (1963).
- [2] G. E. Blonder, M. Tinkham, and T. M. Klapwijk, *Transition from metallic to tunneling regimes in superconducting microconstrictions: Excess current, charge imbalance, and supercurrent conversion*, Phys. Rev. B **25**, 4515 (1982).
- [3] M. Octavio, M. Tinkham, G. E. Blonder, and T. M. Klapwijk, *Subharmonic energy-gap structure in superconducting constrictions*, Phys. Rev. B **27**, 6739 (1983).
- [4] C. W. J. Beenakker, *Random-matrix theory of quantum transport*, Rev. Mod. Phys. **69**, 731 (1997).
- [5] Y. M. Blanter and M. Büttiker, *Shot noise in mesoscopic conductors*, Physics Reports **336**, 1 (2000).
- [6] X. Jehl, M. Sanquer, R. Calemczuk, and D. Mailly, *Detection of doubled shot noise in short normal-metal/superconductor junctions*, Nature **405**, 50 (2000).
- [7] T. Hoss, C. Strunk, T. Nussbaumer, R. Huber, U. Staufer, and C. Schönenberger, *Multiple andreev reflection and giant excess noise in diffusive superconductor/normal-metal/superconductor junctions*, Phys. Rev. B **62**, 4079 (2000).
- [8] F. Lefloch, C. Hoffmann, M. Sanquer, and D. Quirion, *Doubled Full Shot Noise in Quantum Coherent Superconductor-Semiconductor Junctions*, Phys. Rev. Lett. **90**, 067002 (2003).
- [9] Y. Ronen, Y. Cohen, J.-H. Kang, A. Haim, M.-T. Rieder, M. Heiblum, D. Mahalu, and H. Shtrikman, *Charge of a quasiparticle in a superconductor*, PNAS **113**, 1743 (2016).
- [10] P. Dieleman, H. Bukkems, T. Klapwijk, M. Schicke, and K. Gundlach, *Observation of Andreev Reflection Enhanced Shot Noise*, Phys. Rev. Lett. **79**, 3486 (1997).
- [11] M. J. M. de Jong and C. W. J. Beenakker, *Doubled shot noise in disordered normal-metal-superconductor junctions*, Phys. Rev. B **49**, 16070 (1994).
- [12] J. C. Cuevas, A. Martín-Rodero, and A. L. Yeyati, *Shot noise and coherent multiple charge transfer in superconducting quantum point contacts*, Phys. Rev. Lett. **82**, 4086 (1999).
- [13] R. De-Picciotto, M. Reznikov, M. Heiblum, V. Umansky, G. Bunin, and D. Mahalu, *Direct observation of a fractional charge*, Nature **389**, 162 (1997).

- [14] L. Saminadayar, D. C. Glatzli, Y. Jin, and B. Etienne, *Observation of the  $e/3$  fractionally charged Laughlin quasiparticle*, Phys. Rev. Lett. **79**, 2526 (1997).
- [15] H. E. van den Brom and J. M. van Ruitenbeek, *Quantum suppression of shot noise in atom-size metallic contacts*, Phys. Rev. Lett. **82**, 1526 (1999).
- [16] N. Agrait, A. L. Yeyati, and J. M. Van Ruitenbeek, *Quantum properties of atomic-sized conductors*, Physics Reports **377**, 81 (2003).
- [17] A. Burtzloff, A. Weismann, M. Brandbyge, and R. Berndt, *Shot noise as a probe of spin-polarized transport through single atoms*, Phys. Rev. Lett. **114**, 016602 (2015).
- [18] K. M. Bastiaans, T. Benschop, D. Chatzopoulos, D. Cho, Q. Dong, Y. Jin, and M. P. Allan, *Amplifier for scanning tunneling microscopy at MHz frequencies*, Rev. Sci. Instrum. **89**, 093709 (2018).
- [19] M. Ruby, B. W. Heinrich, J. I. Pascual, and K. J. Franke, *Experimental demonstration of a two-band superconducting state for lead using scanning tunneling spectroscopy*, Phys. Rev. Lett. **114**, 157001 (2015).
- [20] K. J. Franke, G. Schulze, and J. I. Pascual, *Competition of Superconducting Phenomena and Kondo Screening at the Nanoscale*, Science **332**, 940 (2011).
- [21] M. T. Randeria, B. E. Feldman, I. K. Drozdov, and A. Yazdani, *Scanning Josephson spectroscopy on the atomic scale*, Phys. Rev. B **93**, 161115(R) (2016).
- [22] E. Scheer, N. Agrait, J. C. Cuevas, A. L. Yeyati, B. Ludoph, A. Martín-Rodero, G. R. Bollinger, J. M. van Ruitenbeek, and C. Urbina, *The signature of chemical valence in the electrical conduction through a single-atom contact*, Nature **394**, 154 (1998).
- [23] R. C. Dynes, V. Narayanamurti, and J. P. Garno, *Direct Measurement of Quasiparticle-Lifetime Broadening in a Strong-Coupled Superconductor*, Phys. Rev. Lett. **41**, 1509 (1978).
- [24] G.-I. Ingold, H. Grabert, and U. Eberhardt, *Cooper-pair current through ultra-small Josephson junctions*, Phys. Rev. B **50**, 395 (1994).
- [25] V. Ambegaokar and A. Baratoff, *Tunneling between Superconductors*, Phys. Rev. Lett. **10**, 486 (1963).
- [26] B. Jäck, M. Eltschka, M. Assig, A. Hardock, M. Etzkorn, and C. R. Ast, *A nanoscale gigahertz source realized with Josephson scanning tunneling microscopy*, Appl. Phys. Lett. **106**, 013109 (2015).
- [27] C. J. Chen, *Introduction to Scanning Tunneling Microscopy Second Edition* (Oxford University Press, 2008).

- [28] H. Birk, M. J. M. de Jong, and C. Schönenberger, *Shot-noise suppression in the single-electron tunneling regime*, Phys. Rev. Lett. **75**, 1610 (1995).
- [29] H. Birk, K. Oostveen, and C. Schönenberger, *Preamplifier for electric-current noise measurements at low temperatures*, Rev. Sci. Instrum. **67**, 2977 (1996).
- [30] U. Kemiktarak, T. Ndukum, K. C. Schwab, and K. L. Ekinici, *Radio-frequency scanning tunnelling microscopy*. Nature **450**, 85 (2007).
- [31] Q. Dong, Y. X. Liang, D. Ferry, A. Cavanna, U. Gennser, L. Couraud, and Y. Jin, *Ultra-low noise high electron mobility transistors for high-impedance and low-frequency deep cryogenic readout electronics*, Appl. Phys. Lett. **105**, 6 (2014).
- [32] R. N. Jabdaraghi, D. S. Golubev, J. P. Pekola, and J. T. Peltonen, *Noise of a superconducting magnetic flux sensor based on a proximity Josephson junction*, Scientific Reports **7**, 8011 (2017).
- [33] M. Müller, N. Neel, S. Crampin, and J. Kröger, *Lateral Electron Confinement with Open Boundaries : Quantum Well States above Nanocavities at Pb ( 111 )*, Phys. Rev. Lett. **117**, 136803 (2016).
- [34] J. Brand, P. Ribeiro, N. Néel, S. Kirchner, and J. Kröger, *Impact of atomic-scale contact geometry on andreev reflection*, Phys. Rev. Lett. **118**, 107001 (2017).
- [35] K. M. Bastiaans, D. Cho, T. Benschop, I. Battisti, Y. Huang, M. S. Golden, Q. Dong, Y. Jin, and M. P. Allan, *Charge trapping and super-Poissonian noise centres in a cuprate superconductor*, Nature Physics **14**, 1183 (2018).
- [36] F. Massei, Y. K. Huang, M. S. Golden, and M. Aprili, *Noisy defects in the high-  $T_c$  superconductor  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$* , Nature Comm. **10**, 544 (2019).
- [37] E. W. Carlson, K. A. Dahmen, E. Fradkin, and S. A. Kivelson, *Hysteresis and noise from electronic nematicity in high-temperature superconductors*, Phys. Rev. Lett. **96**, 097003 (2006).
- [38] P. A. Lee, *Amperean Pairing and the Pseudogap Phase of Cuprate Superconductors*, Phys. Rev. X **4**, 031017 (2014).
- [39] B. Keimer, S. A. Kivelson, M. R. Norman, S. Uchida, and J. Zaanen, *From quantum matter to high-temperature superconductivity in copper oxides*. Nature **518**, 179 (2015).
- [40] P. A. Lee, N. Nagaosa, and X.-G. Wen, *Doping a mott insulator: Physics of high-temperature superconductivity*, Rev. Mod. Phys. **78**, 17 (2006).
- [41] J. Figgins and D. K. Morr, *Differential conductance and quantum interference in kondo systems*, Phys. Rev. Lett. **104**, 187202 (2010).



- [42] S. Cocklin and D. K. Morr, *Scanning tunneling shot noise spectroscopy in kondo systems*, arXiv:1906.02553 (2019).
- [43] S. Nadj-Perge, I. K. Drozdov, J. Li, H. Chen, S. Jeon, J. Seo, A. H. MacDonald, B. A. Bernevig, and A. Yazdani, *Topological matter. Observation of Majorana fermions in ferromagnetic atomic chains on a superconductor*. *Science* **346**, 602 (2014).
- [44] T. Jonckheere, J. Rech, A. Zazunov, R. Egger, A. L. Yeyati, and T. Martin, *Giant shot noise from majorana zero modes in topological trijunctions*, *Phys. Rev. Lett.* **122**, 097003 (2019).