



Universiteit
Leiden
The Netherlands

Reprint of "Electrocatalytic CO₂ reduction to C₂+ products on Cu and Cu_xZn_y electrodes: effects of chemical composition and surface morphology"

Marques da Silva, A.H.; Raaijman, S.J.; Santana, C.S.; Assaf, J.M.; Gomes, J.F.; Koper, M.T.M.

Citation

Marques da Silva, A. H., Raaijman, S. J., Santana, C. S., Assaf, J. M., Gomes, J. F., & Koper, M. T. M. (2021). Reprint of "Electrocatalytic CO₂ reduction to C₂+ products on Cu and Cu_xZn_y electrodes: effects of chemical composition and surface morphology". *Journal Of Electroanalytical Chemistry*, 896. doi:10.1016/j.jelechem.2021.115609

Version: Publisher's Version

License: [Creative Commons CC BY 4.0 license](#)

Downloaded from: <https://hdl.handle.net/1887/3275600>

Note: To cite this publication please use the final published version (if applicable).



Reprint of “Electrocatalytic CO₂ reduction to C₂+ products on Cu and Cu_xZn_y electrodes: Effects of chemical composition and surface morphology”[☆]



Alisson H.M. da Silva^{a,b}, Stefan J. Raaijman^a, Cássia S. Santana^{a,b}, José M. Assaf^b, Janaina F. Gomes^b, Marc T.M. Koper^{a,*}

^a Leiden Institute of Chemistry, Leiden University, Leiden, Netherlands

^b Chemical Engineering Department, São Carlos Federal University, São Carlos, São Paulo, Brazil

ARTICLE INFO

Keywords:

CO₂ electroreduction
Cu
CuZn
Shape
Roughness factor

ABSTRACT

The electrocatalytic CO₂ reduction reaction (CO₂RR) is a promising strategy for producing multi carbon compounds using only CO₂ and H₂O at room temperature. Significant advances have already been achieved in understanding how some characteristics of copper electrodes, the current state-of-the-art catalyst for multi carbon formation via CO₂RR, affect the product spectrum. Advances and insights have been reported for, among others, the effect of crystallographic orientation, active surface area, and composition of M copper (M = Au, Ag, Zn, etc.) materials, and how these alter the distribution of CO₂RR products. However, a systematic study evaluating the significance of these variables in the CO₂RR to C₂+ products is still lacking in the literature and represents an important step in the development of new materials with optimized properties that can be more selective to C₂+ compounds. In this paper, we have systematically investigated the effect of the roughness factor, chemical composition, and surface morphology of Cu_xZn_y electrocatalysts on the product distribution during CO₂RR. Firstly, Cu, Cu₉₀Zn₁₀, and Cu₇₅Zn₂₅ electrodes were exposed to oxidation-reduction cycles to produce Cu and Cu_xZn_y electrodes with different morphologies, roughness factors, and chemical composition. Our results show that an increase in the roughness factor and Zn content lead to higher faradaic efficiency (FE) to C₂+ products. Furthermore, the influence of the nanoscale morphology is imperative for the production of C₂+ compounds. Specifically, nanocubes of Cu and Cu_xZn_y presented the highest FE to C₂+ products among the different surface morphologies studied in this work (polished flat surface, nanoshers, nanocubes, nanodendrites, and nanocauliflowers), showing that C–C coupling during CO₂RR is mainly shape dependent.

1. Introduction

The conversion of CO₂ to molecules with high energy density via the electroreduction of CO₂ represents a promising strategy for storing renewable energy and electricity, and generating important fuels and chemicals such as hydrocarbons and alcohols from CO₂ and H₂O at ambient conditions. Many products can be obtained from the CO₂RR, such as carbon monoxide, methane, formic acid, as well as multi carbon (C₂+) compounds, such as ethylene, ethanol, and propanol, which exhibit higher energy densities and higher economic value than C₁ products. Among the investigated electrodes applied to CO₂RR, copper (Cu) has been reported to be the only catalyst that has shown a significant propensity for C–C coupling, leading to appreciable amounts of C₂+ products [1].

As such, the copper-catalyzed CO₂ reduction has received much scientific interest and many advances have been made in understanding how certain characteristics of copper electrodes alter the distribution of products obtained from CO₂RR [1,2]. For example, it is known that the surface faceting affects the products distribution of the CO₂RR. Specifically, among the three low-index Cu single crystals, the Cu (100) surface favors the formation of C₂+ compounds over C₁, whereas the opposite is observed on Cu(110) and Cu(111) surfaces [3–5]. This knowledge has been applied in practice via the development of catalysts with controlled shapes, exposing predominantly a specific type of facet. In this direction, Wang et al. [6], for example, showed that {100}-rich Cu nanocubes yield 50% FE to C₂H₄ at –0.8 V vs. reversible hydrogen electrode (RHE), in 10 M KOH electrolyte during CO₂RR, in contrast with polycrystalline Cu nanospheres, which produce ethy-

DOI of original article: <https://doi.org/10.1016/j.jelechem.2020.114750>

[☆] A publisher's error resulted in this article appearing in the wrong issue. The article is reprinted here for the reader's convenience and for the continuity of the special issue. For citation purposes, please use the original publication details; Volume 880, 1 January 2021, 114750, DOI of original item: 10.1016/j.jelechem.2020.114750.

^{*} Corresponding author.

E-mail address: m.koper@lic.leidenuniv.nl (M.T.M. Koper).

<https://doi.org/10.1016/j.jelechem.2021.115609>

Received 20 August 2020; Received in revised form 7 October 2020; Accepted 7 October 2020

Available online 20 August 2021

1572-6657/© 2020 The Author(s). Published by Elsevier B.V.

This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

lene with only ~20% of FE under the same reaction conditions. Loui-dice et al. [7] showed that in addition to the geometrical effects (cubes vs. spheres), the size of the Cu cubes also has an important effect on the selectivity of C_{2+} products. They showed that cubes with 44 nm of edges results in higher FE for ethylene than cubes with 24 and 63 nm of edges. The authors suggest that the unique reactivity of the 44 nm cubes derives from an optimal balance between plane and edge sites.

Another criterion for selectivity towards C_{2+} compounds is the electrode surface area, and the associated roughness, defects, electrode potential, and current density. By increasing the amount of catalytically active sites per geometric unit of area, i.e. the roughness factor (RF), the catalytic conversion to C_{2+} products from CO_2 RR can be enhanced compared to that less roughened electrodes [8–11]. Higher roughness creates more undercoordinated sites on the electrode surface and these defects have a higher binding energy for CO_2 and/or precursor to C_{2+} compounds [11–14]. Jiang et al. [11], showed that roughened surfaces contain square sites similar to those on a Cu (100) surface but with neighboring step sites, which exhibit a favorable values of binding energy of $OC - COH$, a key precursor to C_{2+} products. Finally, rough electrodes enhance the current density which affect the selectivity of CO_2 RR by changes in the local pH and/or the CO_2 mass transport. The increase in the local pH has been shown to suppress the hydrogen evolution reaction (HER) by shifting the equilibrium potential to more negative values on an SHE scale and favors C–C bond formation, resulting in enhanced selectivity towards CO_2 RR in general, with more multi carbon products at lower overpotentials [2,9,15]. However, it has been shown that high current densities ($> 20 \text{ mA}\cdot\text{cm}^{-2}$) limits the mass transport of CO_2 to the electrode due its poor solubility in aqueous electrolytes (~34 mM at 25 °C) and hence reducing the selectivity to CO_2 RR products [16]. For example, Raciti et al. [9] showed that, at -0.8 V vs. RHE in 0.1 M $KHCO_3$, an increase in the Cu surface roughness augmented the local pH from 9.0 to 11.0 when the RF was increased from 23 to 365. The latter, rougher, catalyst exhibited higher CO_2 conversion rates and higher FEs for C_2 compounds at low overpotentials ($> -0.8 \text{ V}$) as compared to the catalyst with lower RF. At higher overpotentials ($E \leq -0.8 \text{ V}$), the local pH for the electrode with RF = 365 was even higher (reaching around 12.5 at -1.0 V), but the FE for the formation of C_{2+} compounds decreased due to the mass transport limitation of CO_2 [9].

In addition to the surface crystallographic orientation and roughness, the exact surface chemical composition of copper-based electrodes also influences the selectivity during the CO_2 RR. Bimetallic copper electrodes (copper with e.g., Au, Ag or Zn) are known to promote the formation of C_{2+} compounds [8,17–19] due to a synergetic effect between the two metals. Specifically, it has been hypothesized that the dimerization of $*CO$ (yielding $*OCCO$) [20–22] is enhanced on bimetallic Cu surfaces, due to an increase in θ_{CO} , because of the enhanced reduction of CO_2 to CO by Au, Ag, or Zn sites [8,17,18]. For example, Morales-Guio et al. [8] showed that, at -0.7 V vs. RHE, using 0.1 M $KHCO_3$ as electrolyte, a Au–Cu bimetallic catalyst can be two orders of magnitude more selective for C–C coupled products than pristine Cu. In another study, Huang et al. [18] investigated Ag–Cu bimetallic materials and observed that, at -1.1 V vs. RHE, using 0.1 M $KHCO_3$ as electrolyte, the FE to C_2H_4 increased from 13% to 37% when comparing a pure Cu catalyst with a $Ag_{1.1}Cu_{1.1}$ bimetallic catalyst (atomic composition). In a similar study, Feng et al. [17] reported that the FE to C_2H_4 increased from 15% to 33% for a Cu and a Cu_4Zn_1 alloy (atomic composition) catalyst, respectively. In these three works, it was shown that gold, silver, or zinc generate an increased CO concentration near the surface, where copper sites then reduce it further to C_{2+} compounds. The interatomic distance is also reported to influence the selectivity during the CO_2 RR. Recently, Timoshenko et al. [23] showed by in situ EXAFS that the product distribution from CO_2 RR is composition- and structure-dependent: Cu–Zn nanoparticles with shorter interatomic distance favor

the production of CH_4 , while nanoparticles with longer Cu–Zn distances favor the production of CO, which is then reduced further to C_{2+} .

Although it is already known that the surface crystal orientation, roughness, and chemical composition independently can alter product distribution, a systematic study evaluating the significance of each one of these variables in conjunction to the catalytic performance of Cu-based materials in the CO_2 RR to C_{2+} products is still lacking in the literature and would represent an important step in the development of new materials optimized for activity and selectivity to C_{2+} compounds. Here we explore the faradaic efficiency of the CO_2 RR to C_{2+} products, investigating the concerted effects of surface roughness and nanoscale morphology on monometallic Cu and bimetallic Cu_xZn_y electrodes. The measurements provide us with insights as to which is most important characteristic for the synthesis of C_{2+} compounds: nanoparticle shape/surface morphology, chemical composition, or surface roughness.

2. Experimental section

2.1. Chemicals

$KHCO_3$ (99.95%, Aldrich), KCl ($>99\%$, Aldrich), $HClO_4$ (60%, Aldrich), and ultrapure water (Milli-Q gradient, $\geq 18.2 \text{ M}\Omega\text{cm}$, TOC $< 5 \text{ ppb}$) were used as received to prepare the electrolytic solutions. CO_2 (4.5 purity, Linde) and Ar (6.0 purity, Linde) were used to saturate and purge the electrolyte.

2.2. Electrochemistry

Electrochemical cells used during experiments (standard two compartment glass cells and a custom H-cell made from PEEK) were initially cleaned by storing in acidic (0.5 M H_2SO_4 , 95–98%, Sigma Aldrich) permanganate (1 g L^{-1} , $>99\%$, Sigma Aldrich) solution overnight. Then, traces of $KMnO_4$ and manganese oxide were removed from the glassware and H-Cell by initial rinsing with Milli-Q water and subsequently submerging them in a solution of 10 mL L^{-1} of H_2O_2 (30% (w/w), Aldrich) and 2 mL L^{-1} of concentrated H_2SO_4 (95–98%, Aldrich) followed by boiling four times in ultrapure water (Milli-Q, $\geq 18 \text{ M}\Omega$).

The polycrystalline Cu disk working electrode (WE) (99.99%, trace metals basis, Mateck), with a diameter of 1 cm was polished with two different alumina suspension ($5 \mu\text{m}$ and $1 \mu\text{m}$, Buehler), rinsed with ultrapure water in-between, and electropolished in a solution of 66% of H_3PO_4 by applying $+3 \text{ V}$ vs. a Cu counter electrode (CE) for 10 s and subsequently rinsed with ultrapure water, prior to each experiment. The $Cu_{90}Zn_{10}$ and $Cu_{75}Zn_{25}$ (99.99%, trace metals basis, Good-fellow) alloy disk electrodes (subscripts represent the atomic composition), with a diameter of 0.5 cm were similarly polished with two different alumina suspension ($5 \mu\text{m}$ and $1 \mu\text{m}$) followed by rinsing with ultrapure water, prior to each experiment.

2.3. Preparation of electrodes with different shapes

The preparation of surfaces with controlled morphology was performed according to the procedure described by Roberts, Kuhl and Nilsson [24] with some modifications. Briefly, in a 3-electrode cell with Pt wire as counter electrode and a $Ag/AgCl/KCl_{sat}$ reference electrode, the working-electrode (Cu, $Cu_{90}Zn_{10}$, or $Cu_{75}Zn_{25}$) was subjected to 4 potential oxidation-reduction cycles in 0.1 M $KHCO_3$ solution containing 4 mM KCl saturated with CO_2 at a scan rate of 5 mV s^{-1} in the potential range $0.0 \text{ V} \rightarrow E_{upper} \rightarrow -1.2 \text{ V}$ vs. RHE (with $E_{upper} = 0.7, 0.9$ or 1.1 V vs. RHE) to synthesize surfaces with controlled morphology, specifically: irregularly shaped rounded particles (for Cu and Cu_xZn_y), called here nanospheres, nanocubes (for Cu and

Cu_xZn_y), nanodendrites (for Cu) or nanocauliflowers (for Cu_xZn_y), respectively. During all electrochemical measurements, a CO₂ flow was maintained over the electrolyte to avoid ambient oxygen. The pH of the bulk CO₂-saturated electrolyte was 6.8, as measured with a pH meter. Through the oxidative treatment described above, a set of nine electrodes was obtained, denoted herein as: Cu_(spheres), Cu_(cubes), Cu_(dendrites), Cu₉₀Zn₁₀(spheres), Cu₉₀Zn₁₀(cubes), Cu₉₀Zn₁₀(cauliflowers), Cu₇₅Zn₂₅(spheres), Cu₇₅Zn₂₅(cubes), and Cu₇₅Zn₂₅(cauliflowers).

2.4. Characterization of morphology and chemical composition

Micrographs of Cu and Cu_xZn_y electrodes (before and after oxidation-reduction cycles) were obtained by scanning electron microscopy (SEM) in an Apreo SEM (ThermoFisher Scientific) with an acceleration voltage of 15 kV and an electron beam current of 0.4 nA. Electrode chemical composition was investigated by energy dispersive X-Ray spectrometry (EDX) using an Oxford Instruments X-MaxN 150 Silicon Drift detector coupled to the Apreo SEM. EDX data processing was carried out with the Pathfinder™ X-ray Microanalysis software v1.3. The quantification of chemical elements was performed in automatic mode and the resulting electrodes chemical composition was determined by averaging the chemical compositions of at least 10 different regions of the electrode surface.

2.5. Roughness factor (RF) measurement

Electrochemically active surface area (ECSA) of the different electrodes were measured via a procedure described by Kanan and co-workers [25–27]. The experiments were carried out in a 3-electrode cell containing 0.1 M HClO₄. Argon was bubbled into the electrolyte for at least 15 min to remove oxygen from the solution, and a flow of argon was maintained over the solution during the electrochemical measurements. Typically, cyclic voltammetry was performed in a potential range from –0.05 V to –0.35 V vs. RHE (DL region), applying 6 different scan rates (100, 80, 60, 40, 20, and 10 mV s^{–1}). Then, the double layer capacitance was determined by plotting the DL current (in terms of geometric area) as a function of scan rate and calculating the slope of the resulting line. Assuming that the double layer capacitance value in the double layer region is proportional to the number of electrochemically active sites, it is possible to estimate the roughness factors (RF) of the electrodes by normalizing the measured capacitances with respect to that of the flat polycrystalline Cu electrode, which is conventionally taken as a reference with RF = 1.

2.6. Electrolysis experiments

CO₂ electroreduction was performed using a homemade H-cell in PEEK containing 10 mL of 0.1 M KHCO₃ of electrolyte per compartment. CO₂ was continuously fed at a flow rate of 10 mL min^{–1} during electrolysis. An anionic exchange membrane (AHO, AGC Inc.) was used to separate the working-electrode compartment from that of the counter-electrode. A dimensionally stable anode (DSA, Magneto) and Ag/AgCl/KCl_{sat.} were used as a counter-electrode and reference electrode, respectively. All potentials measured against the Ag/AgCl/KCl_{sat.} electrode were converted to RHE values according to the equation:

$$E_{\text{RHE}} = E_{\text{Ag/AgCl(KCl}_{\text{sat.}})} + E^{\circ}_{\text{Ag/AgCl(KCl}_{\text{sat.}})} + 0.059 \times \text{pH}$$

where E_{RHE} is the converted potential vs. RHE, E_{Ag/AgCl(KCl_{sat.})} is the experimentally measured potential against the Ag/AgCl/KCl_{sat.} reference electrode, and E[°]_{Ag/AgCl(KCl_{sat.})} is the standard potential of Ag/AgCl at 25 °C (0.197 V vs. NHE). Unless otherwise specified, all reported potentials herein are vs. RHE.

The potential of the working-electrode was controlled by a Biologic SP-300 potentiostat. Gaseous products were analyzed online using a


Shimadzu 2014 gas chromatograph with two detectors (one TCD and one FID). Liquid products were measured by high performance liquid chromatography (HPLC) and by hydrogen nuclear magnetic resonance spectroscopy (H¹-NMR), as described elsewhere [28,29].

3. Results and discussion

The electro oxidation-reduction treatment of the Cu, Cu₉₀Zn₁₀ and Cu₇₅Zn₂₅ electrodes surfaces in presence of Cl[–] to produce different surfaces exposes intricate nanostructures with controlled shapes, as depicted in Scheme 1. Fig. S1 shows the cyclic voltammograms recorded for the nine electrodes after the electro oxidation-reduction treatment. These materials are generally referred to as oxide-derived electrodes (OD-electrodes), as they are metallic electrodes resulting from the reduction of an oxide [30]. Our results show that by sweeping the potential from 0.0 V to 0.7 V vs. RHE and sweeping back from 0.7 V to –1.2 V vs. RHE (for four times), nanoparticles with irregular spherical shapes were formed on the Cu, Cu₉₀Zn₁₀ and Cu₇₅Zn₂₅ electrodes (Fig. 1a, d, and g, respectively). When the same procedure was used with an increased upper potential of 0.9 V vs. RHE, nanocubes with 54 ± 5 nm of edge size were formed for Cu and both Cu_xZn_y electrodes (Fig. 1b, e, and h, respectively). In agreement with previous work, we consider these images as evidence for (100) facets [24,31–33]. It is known that copper nanocubes can be synthesized via this procedure [24,31–33], but we report here the applicability of this method for synthesizing Cu_xZn_y nanocubes. Lastly, when the oxidation potential was increased to 1.1 V, Cu nanodendrites (Fig. 1c), looking like double compound leaves, or Cu_xZn_y “nanocauliflowers” (Fig. 1f and i) were formed instead. SEM images of the Cu, Cu₉₀Zn₁₀, and Cu₇₅Zn₂₅ electrodes before the oxidation-reduction treatment are shown in Fig. S2.

These materials were also characterized by cyclic voltammetry in 0.1 M NaOH solution between –0.25 V to 0.45 V vs RHE [34], and the results are shown in Fig. 2. For Cu electrodes before the electro oxidation-reduction treatment (Fig. 2a), symmetrical oxidation and reduction peaks were observed at –0.15 V, 0.05 V, 0.35 V and 0.43 V vs RHE. The peaks of low intensity at –0.15 V and –0.05 V correspond to the adsorption and desorption of OH[–] on Cu (100) terraces and Cu (111) terraces, respectively, and the pronounced peaks at 0.35 V and 0.43 V are both related to the oxidation and reduction of Cu to Cu₂O on different domains of the polycrystalline electrode. For the OD-Cu electrodes (Fig. 2b), the same profile was observed, but with peaks of significantly higher intensity. This increase in the current is due to an increase in surface roughness as consequence of the oxidation-reduction treatment. The corresponding electrode surface area will be discussed in more detail when we present the results concerning the roughness factor. For CuZn electrodes before the oxidation-reduction treatment (Fig. 2c and e), significant differences between the voltammetric profiles were found, although the same procedure was used. A broad peak between –0.2 V and –0.05 V was observed for the Cu₉₀Zn₁₀ electrode (Fig. 2c) and it became more pronounced for samples with increased zinc content, e.g., Cu₇₅Zn₂₅ (Fig. 2e), suggesting that these voltammetric features are related to Zn. For OD-CuZn electrodes (Fig. 2d and f) an increase in the current was also observed, as observed for OD-Cu, with intense voltammetric features between –0.3 V ≤ E ≤ 0.45 V, indicative of increased surface area after the oxidation-reduction treatment. The appearance of the oxidation-reduction peaks between 0.0 and 0.1 V suggests that cycling the CuZn electrodes exposes more Cu to the surface. The electrochemical characterization was mainly used here as a reference: Cu, OD-Cu, CuZn, and OD-CuZn were systematically prepared and characterized in NaOH prior to being subjected to the CO₂RR conditions, ensuring reproducible surface conditions at the beginning of each measurement.

The atomic composition of the electrodes at the surface before and after the oxidation-reduction treatment was investigated by SEM-EDX

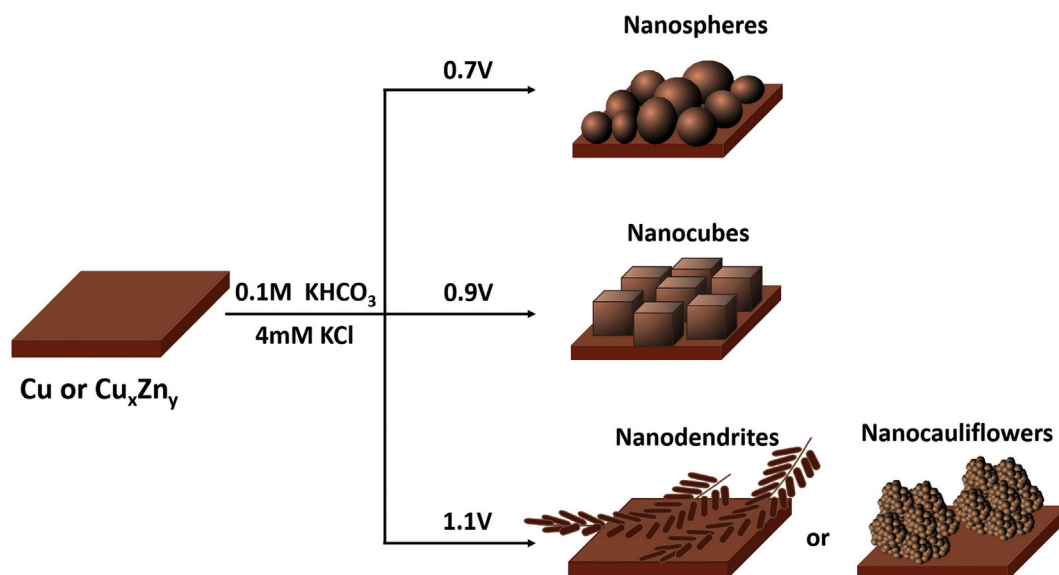

Scheme 1. Preparation of Cu, Cu₉₀Zn₁₀, and Cu₇₅Zn₂₅ electrodes which expose nanospheres, nanocubes, or nanodendrites/nanocauliflowers by cycling from -1.2 V vs RHE to 0.7 V, 0.9 V, or 1.1 V vs. RHE, respectively. Electrolyte: 0.1 M KHCO₃ + 4 mM KCl.

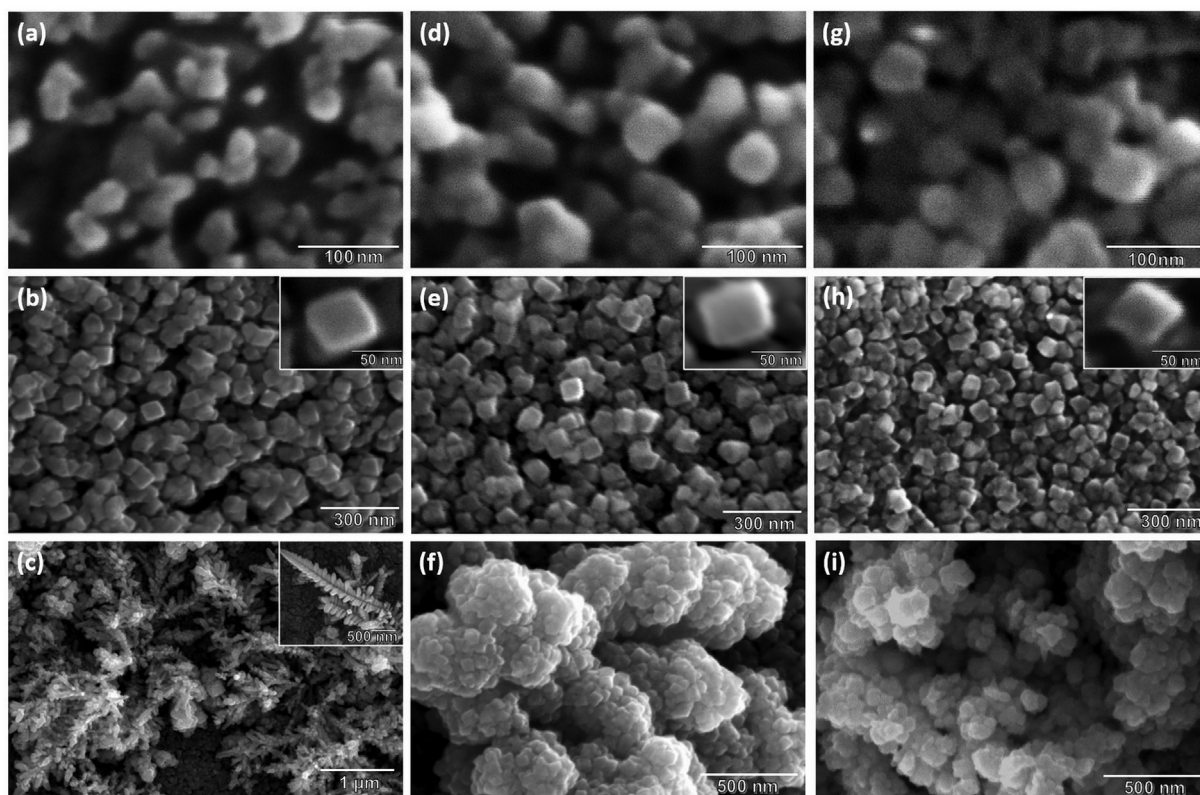


Fig. 1. SEM images of (a) OD-Cu_(spheres), (b) OD-Cu_(cubes), (c) OD-Cu_(dendrites), (d) OD-Cu₉₀Zn_{10(spheres)}, (e) OD-Cu₉₀Zn_{10(cubes)}, (f) OD-Cu₉₀Zn_{10(cauliflowers)}, (g) OD-Cu₇₅Zn_{25(spheres)}, (h) OD-Cu₇₅Zn_{25(cubes)}, (i) OD-Cu₇₅Zn_{25(cauliflowers)}.

and the results are shown in Table 1. For the Cu electrodes, only copper was identified on the surface, as expected. For the Cu₉₀Zn₁₀ and Cu₇₅Zn₂₅ alloys, before the oxidation-reduction treatment, the contents of Cu and Zn on the surfaces were close to those reported by the supplier. Specifically, a composition of $88.2 \pm 5.2\%$ of Cu and $11.1 \pm 2.4\%$ of Zn was found for Cu₉₀Zn₁₀ and $73.2 \pm 4.8\%$ of Cu and $24.6 \pm 2.1\%$ of Zn for Cu₇₅Zn₂₅. However, after the oxidation-reduction, the atomic composition of the surface for zinc-containing

bimetallic catalysts changed in comparison to their composition before the treatment. Particularly, the relative content of zinc at the surface gradually decreased as the oxidation potential in the oxidation-reduction procedure was increased. For example, for the Cu₇₅Zn_{25(spheres)} electrode, which was subjected to a maximum of 0.7 V, the surface atomic composition was found to be $79.1 \pm 5.1\%$ of Cu and $21.7 \pm 2.9\%$ of Zn, as compared to the original value of $73.2 \pm 4.8\%$ of Cu and $24.6 \pm 2.1\%$ of Zn. For the Cu₇₅Zn_{25(cubes)}

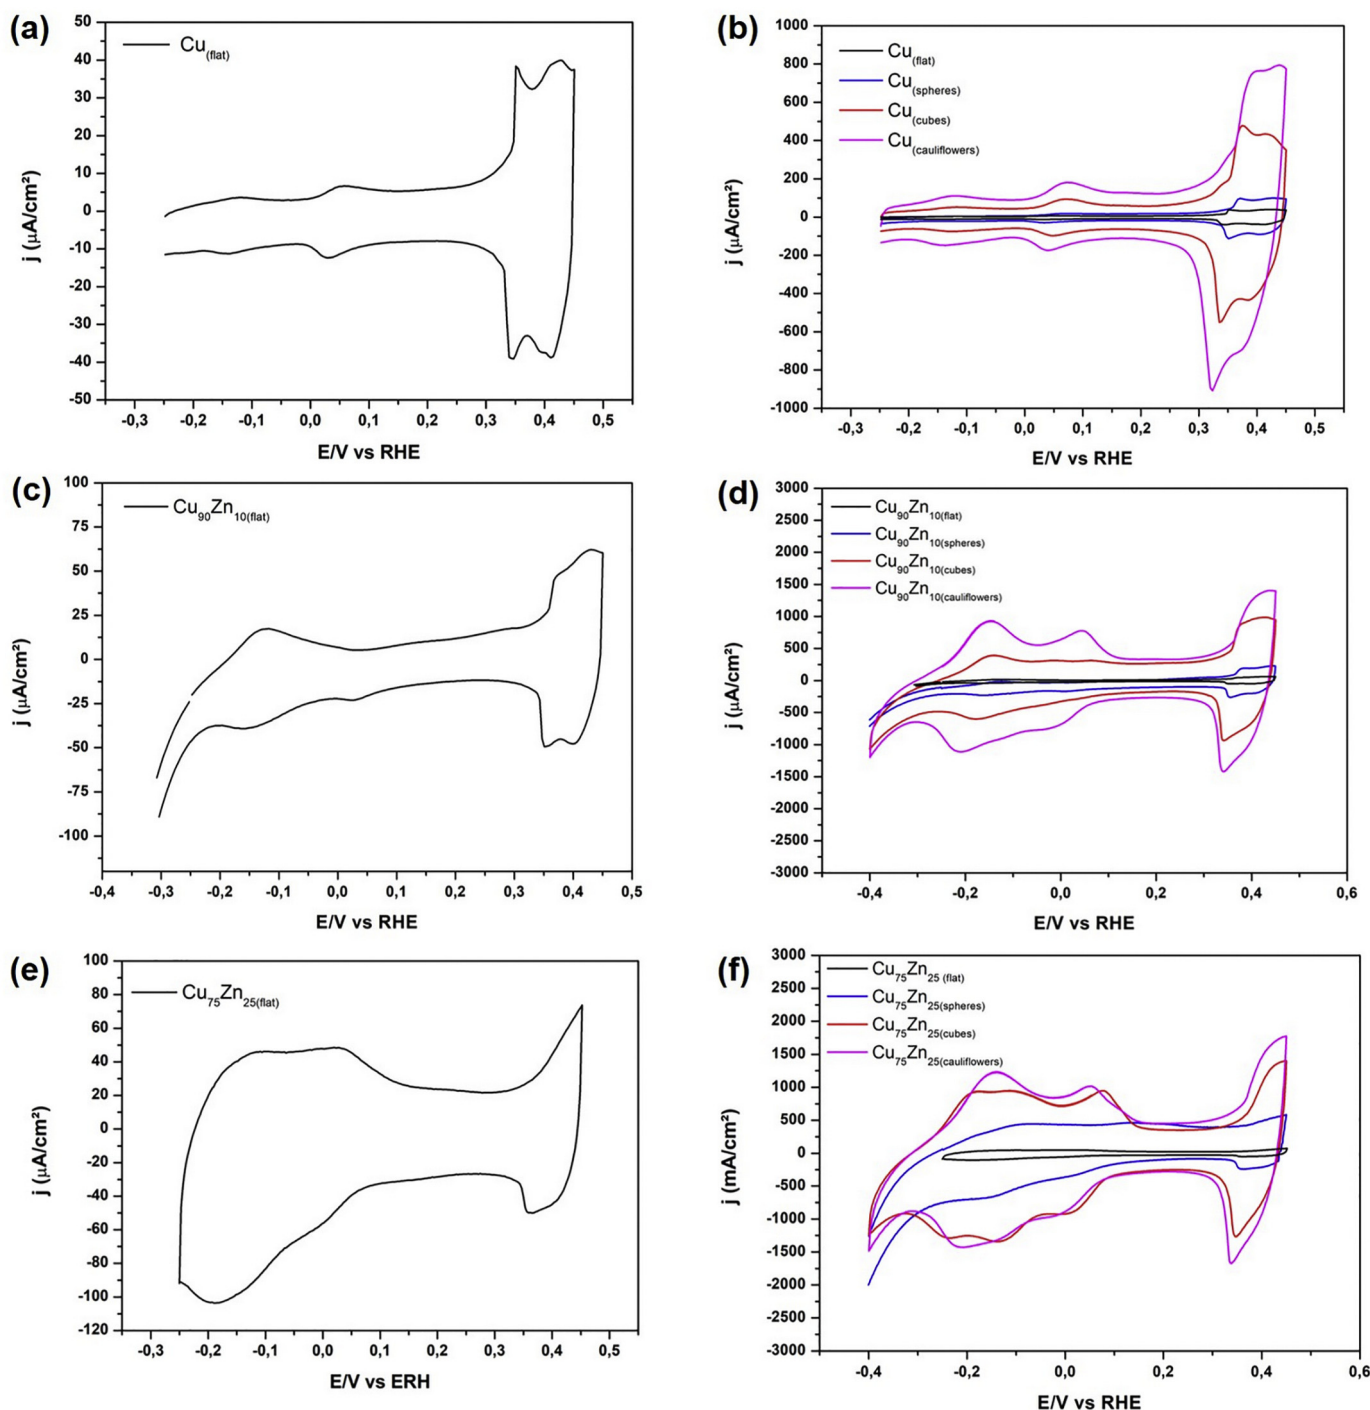


Fig. 2. Cyclic voltammograms of (a) Cu_{flat} ; (b) OD-Cu; (c) $\text{Cu}_{90}\text{Zn}_{10}\text{flat}$; (d) OD- $\text{Cu}_{90}\text{Zn}_{10}$; (e) $\text{Cu}_{75}\text{Zn}_{25}\text{flat}$; and (f) OD- $\text{Cu}_{75}\text{Zn}_{25}$ electrodes in 0.1 M NaOH at a scan rate of 50 mV s^{-1} .

electrode, oxidized up to 0.9 V, only $13.6 \pm 2.7\%$ of Zn was found and for the $\text{Cu}_{75}\text{Zn}_{25}\text{(cauliflowers)}$, oxidized up to 1.1 V, the Zn content was again lower, measuring only $6.1 \pm 1.6\%$ at the surface. The same trend was observed for the $\text{Cu}_{90}\text{Zn}_{10}$ electrodes. The decrease of Zn content at the surface can be explained by the electrodisolution of zinc into the electrolyte, as Zn can easily be oxidized to Zn^{2+} at potentials positive of the equilibrium potential ($\text{Zn} \leftrightarrow \text{Zn}^{2+} + 2\text{e}^-$, $E^\circ(\text{V}) = -0.3606 \text{ V vs. RHE}$ at $\text{pH} = 6.8$). As the equilibrium potential for zinc lies well below that of copper, this can reasonably explain the relative enrichment of the surface in copper as the driving force for the

leaching of zinc is relatively greater, with increased upper oxidation limits enhancing this effect. Our results therefore show that, by applying the oxidation-reduction procedure, not only the surface morphology is modified, but also the chemical composition at the interface.

Surface roughness factors (RF) of the Cu and Cu_xZn_y electrodes were determined through measurement of the double layer (DL) capacitance by recording cyclic voltammograms in the double layer window, and the results are shown in Table 1 (RFs) and Fig. S3 (DL current measurements and analysis). For the OD-Cu and OD- Cu_xZn_y electrodes, higher capacitance and hence higher roughness factor val-

Table 1

Atomic composition, as studied by SEM-EDS, and roughness factor of the Cu, OD-Cu, Cu₉₀Zn₁₀, OD-Cu₉₀Zn₁₀, Cu₇₅Zn₂₅ and OD-Cu₇₅Zn₂₅ electrodes.

Sample	Atomic composition (by EDS)		Roughness factor (compared to Cu _(flat))
	Cu (%)	Zn (%)	
Cu _(flat)	100	0	1.0
OD-Cu _(spheres)	100	0	1.8
OD-Cu _(cubes)	100	0	2.9
OD-Cu _(dendrites)	100	0	5.5
Cu ₉₀ Zn ₁₀ (flat)	88.2 ± 5.2	11.1 ± 2.4	2.7
OD-Cu ₉₀ Zn ₁₀ (spheres)	91.4 ± 4.9	8.6 ± 2.0	5.1
OD-Cu ₉₀ Zn ₁₀ (cubes)	93.1 ± 4.3	6.8 ± 2.0	12.9
OD-Cu ₉₀ Zn ₁₀ (cauliflowers)	97.4 ± 4.7	2.8 ± 1.5	18.8
Cu ₇₅ Zn ₂₅ (flat)	73.2 ± 4.8	24.6 ± 2.1	7.1
OD-Cu ₇₅ Zn ₂₅ (spheres)	79.1 ± 5.1	21.7 ± 2.9	7.4
OD-Cu ₇₅ Zn ₂₅ (cubes)	86.4 ± 5.5	13.6 ± 2.7	15.0
OD-Cu ₇₅ Zn ₂₅ (cauliflowers)	95.9 ± 4.7	6.1 ± 1.6	18.2

ues were obtained when the final oxidation potential was increased in the oxidation-reduction treatment. For example, Cu_(dendrites), which were cycled up to 1.1 V vs. RHE, presented a higher roughness factor (RF = 5.5) than Cu_(cubes) (RF = 2.9), which formed upon cycling to 0.9 V vs. RHE, which was still higher than the roughness of an uncycled polished copper surface (RF = 1). This increase in the roughness factor by applying increasingly positive oxidation potentials during electrochemical cycling can be explained by higher surface disorder upon reduction of the increasingly thicker copper oxide layer. Specifically, when Cu electrodes are used, Cl[−] reacts with Cu to form CuCl. At oxidative potentials at neutral or basic pH, CuCl is converted to Cu₂O through two reactions in series (CuCl + OH[−] ↔ CuOH + Cl[−] and 2CuOH ↔ Cu₂O + H₂O) [24,35,36]. By cycling to increasingly positive potentials, thicker oxide layers are generated which result in more disordered surfaces upon reduction and hence in progressively higher surface roughness values as one cycles to more oxidative potentials.

CO₂ electroreduction in CO₂-saturated 0.1 M KHCO₃ (pH = 6.8) was performed at four different potentials (−0.8, −0.9, −1.0, and −1.1 V vs RHE) on Cu and Cu_xZn_y electrodes. It is important to point out that in the oxidation-reduction treatment over the electrodes, the sweeping of the potential ends at −1.2 V vs. RHE and thus it is considered that the Zn and Cu are both in metallic form. In addition, we note that Chen et al. [33] showed by HR-TEM that the morphology of the nanoparticles remained as cubes even after 70 min of CO₂ electroreduction in CO₂-saturated 0.1 M KHCO₃, pH = 6.8 (same reaction conditions as applied in our experiments). Furthermore, they also showed the presence of (100) facets in their HR-TEM images reinforcing the stability of the particles under the applied reaction conditions. The corresponding faradaic efficiencies to H₂, CO, CH₄, HCOOH, C₂H₄, EtOH, and PrOH (main products identified herein) are shown in Table S1. The sum of FE varied from 85%, for the lowest potentials, to 105%, for the highest potentials. As small amounts of aldehydes, ketones, and other liquid products have not been quantified and they are preferably formed at lower potentials, the total FE at −0.8 and −0.9 V vs RHE is below 90%. For the higher potentials, only gaseous products and higher alcohols are preferably formed and thus it is reasonable to achieve total FE close to 100% since they were all quantified. Values found around 105% are due to cumulative experimental errors since different quantification techniques were used (GC, HPLC and H¹-NMR). As a general trend, with some exceptions, the faradaic efficiency (FE) of the H₂ and CO production decreased when a higher reduction potential was applied. For example, for the Cu_(cubes) electrode the FE of the H₂ synthesis diminished from 49.3% at −0.8 V to 22.3% at −1.1 V. The same behavior was also observed for CO, for which FE decreased from 13.6% at −0.8 V to 2.6% at −1.1 V. On the other hand, for C₂⁺ products (C₂H₄, EtOH and PrOH),

higher FEs were observed for the Cu and Cu_xZn_y electrodes at more reductive potentials. The opposite trends observed for CO formation and that of C₂⁺ compounds is consistent with the fact that adsorbed CO is the key species of the CO dimerization considered to be involved in the C₂⁺ synthesis [1,2,37]. At these more negative potentials, the higher current leads to more hydroxide formation and thus to an increase in local pH near the electrode. In turn, this inhibits the hydrogen evolution reaction [9,38,39] and hence favors to the formation of carbon products. In the present work, we are interested in evaluating how the catalytic performance towards the production of C₂⁺ compounds is affected by the surface morphology (nanoparticle shapes), the roughness factor and the composition of the interface. As the best potential for C₂⁺ product formation on the investigated electrodes was −1.1 V vs RHE, the following discussion will be focused on the C₂⁺ production at this potential.

Fig. 3 shows the FEs to C₂H₄, EtOH, and PrOH (C₂⁺ products identified here) for the Cu (Fig. 3a), Cu₉₀Zn₁₀ (Fig. 3b), and Cu₇₅Zn₂₅ (Fig. 3c) electrodes at −1.1 V, before and after the oxidation-reduction treatment. The values of the RF were added below the name of each electrode to make the discussion easier, since the increase in the RF is considered to be one of the important factors for improving the catalytic performance of the CO₂ reduction [2,9,15,16]. For the electrodes without the oxidation-reduction treatment (polished flat electrodes), the faradaic efficiency to C₂⁺ compounds were around 15% for Cu and Cu₉₀Zn₁₀ and decreased to about 7.5% for the Cu₇₅Zn₂₅ electrode. This result shows that the mere addition of Zn to the Cu structure does not enhance the C₂⁺ production. By contrast, C₂⁺ production decreases when the atomic percentage of Zn in the electrode increases from ca. 10% to approximately 25%, even though the roughness factor increased from 1.0 for Cu to 7.1 for the Cu₇₅Zn₂₅ alloy. Instead of C₂⁺ production, CH₄ and H₂ are enhanced by Cu₉₀Zn₁₀ and Cu₇₅Zn₂₅, respectively (Table S1). This behavior agrees with the results of Timoshenko et al. [23], who showed that CH₄, H₂, and CO production were dependent of the composition and structure of Cu–Zn and specifically that a low content of Zn leads to higher CH₄ formation and high content of Zn leads to higher H₂ formation as observed here for Cu₉₀Zn₁₀ and Cu₇₅Zn₂₅. On the other hand, our results differs from results reported by Feng et al. [17] who showed that CuZn alloy can enhance the C₂⁺ production in comparison to the pure Cu. However, in that work the authors synthesized spherical nanoparticles of CuZnO alloys with 7 to 15 nm in diameter by pulsed laser ablation of a CuZn alloy target and, before the CO₂RR tests, CuZnO alloys were deposited on glassy carbon and reduced at −1.6 V vs RHE, producing OD-electrodes. Therefore, in the studies reported by Feng et al. [17] not only the composition effect (Cu_xZn_y vs Cu) was considered, but also the influence of the nanoparticle size, dispersion, subsurface oxygen, etc. Here, by investigating non-oxidized Cu, Cu₉₀Zn₁₀, and Cu₇₅Zn₂₅ polished disc electrodes with low surface roughness, morphological and/or particle size effects and surface roughness effects between the different electrodes were minimized leading to more accurate relationships between the Zn content in the CuZn alloy and the catalytic performance of the electrodes towards the formation of C₂⁺ compounds.

For the electrodes obtained after oxidation-reduction treatment (OD-electrodes), catalytic performances were significantly improved in comparison to the flat Cu and Cu_xZn_y electrodes. The catalytic behavior is similar for the OD-Cu, OD-Cu₉₀Zn₁₀, and OD-Cu₇₅Zn₂₅ electrodes. Specifically, the faradaic efficiency towards C₂⁺ products increases going from a polished flat surface to a nanosphere-covered electrode, reaching the highest performance for surfaces comprised of nanocubes, and decreasing in the case of nanodendrite (for Cu) or nanocauliflower (for Cu_xZn_y) morphologies. In general, the catalytic performance seems to be impacted by the surface roughness factor, chemical composition, and nanostructure shape.

To obtain a better understanding of the influence of the roughness factor, Fig. 3d shows the FE to C₂⁺ compounds for the oxide derived

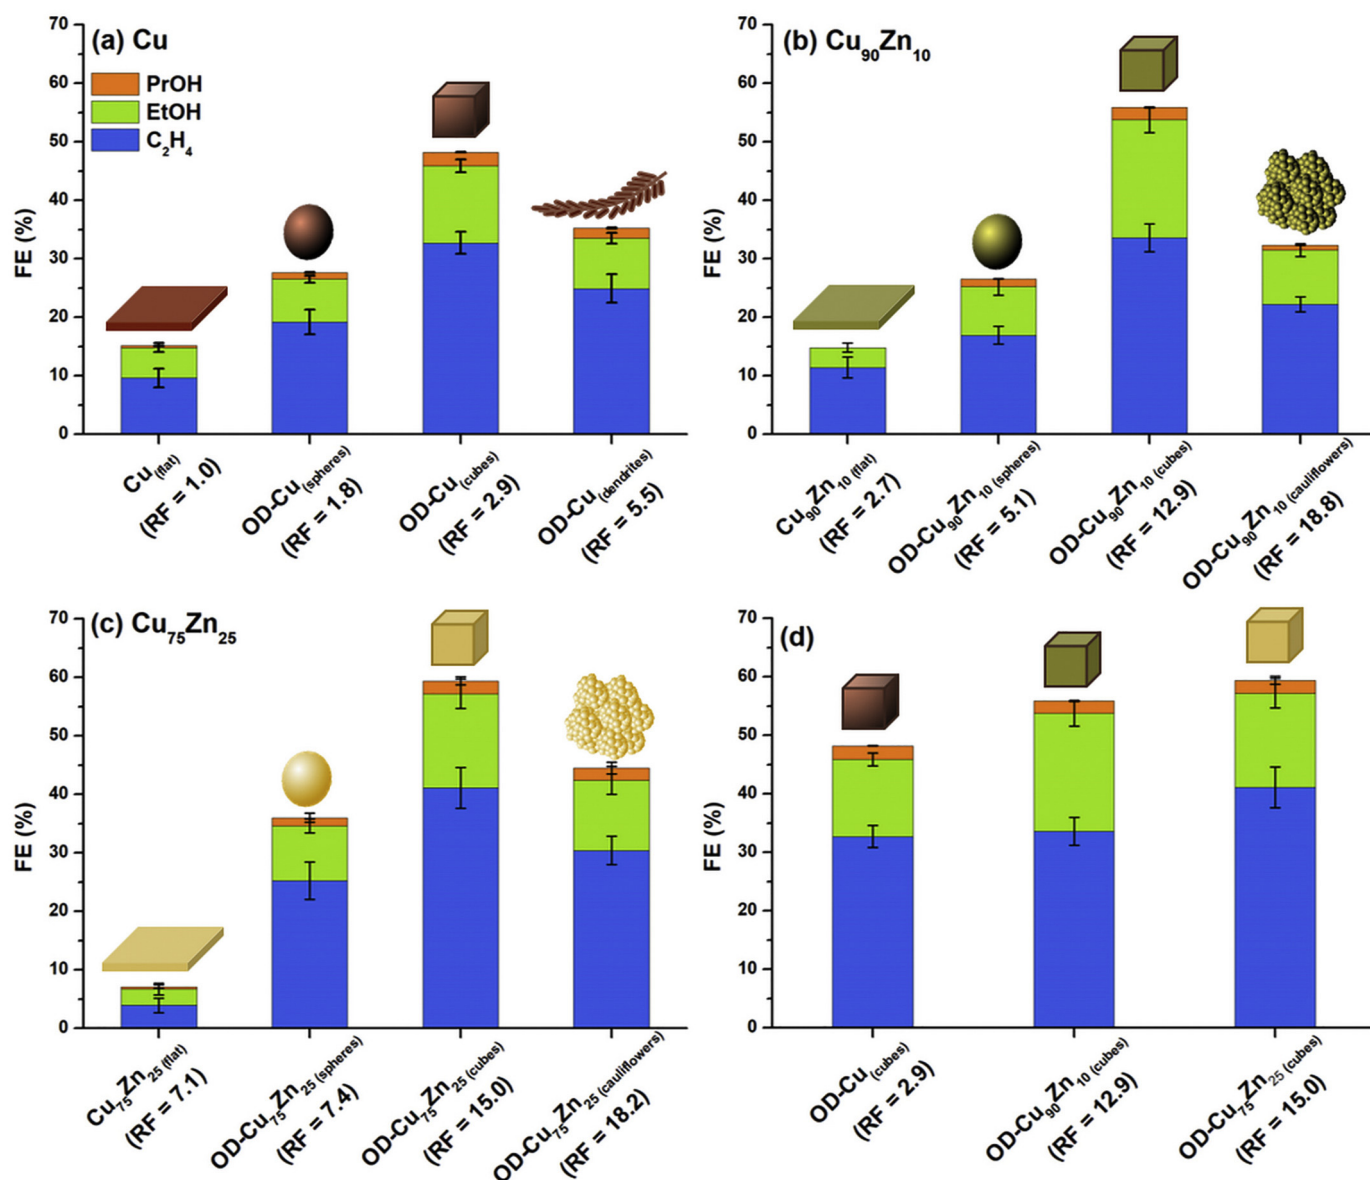


Fig. 3. Faradaic efficiency (FE) of the C_2H_4 (blue), EtOH (green), and PrOH (orange) production on (a) Cu_(flat), OD-Cu_(spheres), OD-Cu_(cubes), and OD-Cu_(dendrites), (b) Cu₉₀Zn₁₀(flat), OD-Cu₉₀Zn₁₀(spheres), OD-Cu₉₀Zn₁₀(cubes), and OD-Cu₉₀Zn₁₀(cauliflowers), (c) Cu₇₅Zn₂₅(flat), OD-Cu₇₅Zn₂₅(spheres), OD-Cu₇₅Zn₂₅(cubes), and OD-Cu₇₅Zn₂₅(cauliflowers), and (d) OD-Cu_(cubes), OD-Cu₉₀Zn₁₀(cubes), and OD-Cu₇₅Zn₂₅(cubes) at -1.1 V vs RHE. Roughness factor (RF) values were added below the name of each electrode to facilitate the discussion. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

Cu, Cu₉₀Zn₁₀, and Cu₇₅Zn₂₅ electrodes containing nanobubular features. The effect of the nanoparticle shape is minimized here since the electrodes contain cubic nanostructures of similar sizes, although the chemical composition is not identical between different electrodes. It is evident that the production of C_2+ compounds is enhanced with increasing surface roughness factor, for the same type of surface morphology. The same trend was also observed for the nanosphere electrodes. Cu₇₅Zn₂₅(spheres) has a higher RF and higher FE to C_2+ than Cu₉₀Zn₁₀(spheres) and Cu_(spheres). However, besides the surface roughness factor, the Zn content was also higher for the Cu₇₅Zn₂₅ nanocubes and Cu₇₅Zn₂₅ nanospheres electrodes in comparison with the Cu₉₀Zn₁₀ and pure Cu materials. Although for the polished flat electrodes, the presence of Zn in Cu is not beneficial to the C_2+ production (Fig. 3), by subjecting the Cu and Cu_xZn_y electrodes to electrochemical cycling, surface morphologies containing nanostructures with different size and shapes are formed and hence the physical and electronic properties of the OD-electrodes are likely different from those of the non-oxi-

dized, mechanically polished surfaces. Therefore, in contrast to the polished flat electrodes, we cannot discard the existence of synergistic effects between Zn and Cu in the OD-electrodes and this can also contribute to improve the production of C_2+ compounds, as previously reported by other authors [17,19,40–42]. In comparison to the materials investigated by Feng et al. [17], our OD-electrodes are in better agreement regarding their electrocatalytic behavior than polished flat electrodes: we also see a higher production of C_2+ compounds on Cu_xZn_y alloys compared to pure Cu. Further evidence that the zinc content has a positive impact on the catalytic performance of OD-Cu_xZn_y electrodes towards the production of C_2+ compounds is provided by the nanocauliflower materials. For Cu₇₅Zn₂₅(cauliflower) (%Zn = 6.1 ± 1.6) the RF is slightly lower than that of Cu₉₀Zn₁₀(cauliflower) (%Zn = 2.8 ± 1.5), but Cu₇₅Zn₂₅(cauliflower) presents a higher FE for C_2+ compounds (~44% for Cu₇₅Zn₂₅(cauliflower) versus ~33% for Cu₉₀Zn₁₀(cauliflower)). Therefore, it seems that for the OD-Cu_xZn_y electrodes, a higher zinc content leads to improved C_2+ production.

Even though, in general, RF and Zn content can both improve the selectivity towards higher FE to C_{2+} products, when comparing different nanoparticle geometries, it is clear the shape is dominant factor for the synthesis of C_{2+} compounds. When we move from nanocubes to nanodendrites or nanocauliflowers, even though the roughness factor increases, the FE to C_{2+} products decrease. From nanocubes to nanospheres, an increase in the Zn content is observed but also a decrease in FE to C_{2+} products. In other words, whenever the structure is diverted from the nanocubes, even if the RF or Zn content are increased, the production of C_{2+} compounds is reduced. Nanocubes are well-known to expose preferentially {100} facets [6,24,43] and, according to previous studies with copper single crystals [1–5], C_{2+} products are favorably synthesized on Cu(100), while C_1 compounds are mainly formed on Cu(110) and Cu(111). Therefore, the best performance of nanocubes exposed-OD-electrodes for the synthesis of C_{2+} products can be associated with the preferential exposition of {100} facets. To date, relevant advances have been reported with respect to the impacts of roughness [8–11], crystalline structure [3–5], composition of Cu–Zn electrodes [17,23,40,41], interatomic distance between Cu and Zn [23], etc., on the CO_2 RR. However, here we show that among all these important characteristics, the particle geometry is a dominant factor in the synthesis of C_{2+} compounds.

4. Conclusions

Cu and Cu_xZn_y electrodes with different zinc contents, roughness factors, and surface morphologies were successfully prepared by electrocycling polished Cu, $Cu_{90}Zn_{10}$, and $Cu_{75}Zn_{25}$ electrodes between -1.2 V and 0.7 V, 0.9 V, or 1.1 V vs. RHE in 0.1 M $KHCO_3$ containing 4 mM KCl. From SEM images, it was observed that nanospheres (for Cu and Cu_xZn_y), nanocubes (for Cu and Cu_xZn_y) and nanodendrites (for Cu) or nanocauliflowers (for Cu_xZn_y) were formed when the oxidation potential was changed from 0.7 V to 0.9 V, and 1.1 V, respectively. Surface roughness was increased when higher oxidation potential limits were applied to the electrodes during the oxidation-reduction treatment (nanocauliflowers $\sim$ nanodendrites $>$ nanocubes $>$ nanospheres). The production of C_{2+} compounds was showed to be influenced by the roughness factor, zinc content, and nanostructure shape. For a given shape, increasing the surface roughness factor led to higher FEs to C_{2+} compounds. The increase of zinc content in the polished flat electrodes showed to decrease the amount C_{2+} compounds produced. On the other hand, for OD-electrodes of a given shape, zinc content leads to a higher total FE for C_{2+} . Although both roughness factor and catalyst alloy composition can impact the catalytic performance towards the production of C_{2+} compounds, the electrode nanostructure shape showed to be the biggest factor in enhancing C_{2+} formation. Specifically, nanocube (which preferentially expose {100} facets) covered surfaces of Cu and Cu_xZn_y electrocatalysts, were found to lead to higher FE to C_{2+} compounds among the different shapes evaluated in this work (nanospheres, nanocubes, nanodendrites and nanocauliflowers). We believe these results provide important guidelines for the rational design of optimized electrodes to be applied in the conversion of CO_2 to C_{2+} compounds.

Declaration of Competing Interest

In this paper, we have systematically investigated the effect of the roughness factor, chemical composition, and surface morphology of Cu_xZn_y electrocatalysts on the product distribution during CO_2 reduction reaction. Our results show that an increase in the roughness factor and Zn content lead to higher faradaic efficiency (FE) to C_{2+} products. Furthermore, the influence of the nanoscale morphology is imperative for the production of C_{2+} compounds. Specifically, nanocubes of Cu and Cu_xZn_y presented the highest FE to C_{2+} products among the different surface morphologies studied in this work (polished flat surface,

nanospheres, nanocubes, nanodendrites, and nanocauliflowers), showing that C–C coupling during CO_2 RR is mainly shape dependent.

Acknowledgements

This work was supported by PDSE/CAPES (grant number 88881.189108/2018-01), CNPq (grant number 141482/2016-8) and FAPESP (grant numbers: 2017/08420-0, 2015/06246-7, 2018/23601-3, 2017/05241-7, and 2018/24339-0). The Leiden work was financed by the Solar-to-Products program of the Netherlands Organization for Scientific Research (NWO).

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.jelechem.2020.114750>.

References

- [1] S. Nitopi, E. Bertheussen, S.B. Scott, X. Liu, A.K. Engstfeld, S. Horch, B. Seger, I.E.L. Stephens, K. Chan, C. Hahn, J.K. Nørskov, T.F. Jaramillo, I. Chorkendorff, Progress and perspectives of electrochemical CO_2 reduction on copper in aqueous electrolyte, *Chem. Rev.* 119 (2019) 7610–7672, <https://doi.org/10.1021/acs.chemrev.8b00705>.
- [2] Y.Y. Birdja, E. Pérez-Gallent, M.C. Figueiredo, A.J. Göttele, F. Calle-Vallejo, M.T.M. Koper, Advances and challenges in understanding the electrocatalytic conversion of carbon dioxide to fuels, *Nat. Energy* 4 (2019) 732–745, <https://doi.org/10.1038/s41560-019-0450-y>.
- [3] K.W. Frese, Electrochemical reduction of CO_2 at solid electrodes, in: B.P. Sullivan (Ed.), *Electrochem. Electrocatal. React. Carbon Dioxide*, Elsevier, 1993, pp. 145–213.
- [4] Y. Hori, H. Wakebe, T. Tsukamoto, O. Koga, Adsorption of CO accompanied with simultaneous charge transfer on copper single crystal electrodes related with electrochemical reduction of CO_2 to hydrocarbons, *Surf. Sci.* 335 (1995) 258–263, [https://doi.org/10.1016/0039-6028\(95\)00441-6](https://doi.org/10.1016/0039-6028(95)00441-6).
- [5] Y. Huang, A.D. Handoko, P. Hirunsit, B.S. Yeo, Electrochemical reduction of CO_2 using copper single-crystal surfaces: effects of CO^* coverage on the selective formation of ethylene, *ACS Catal.* 7 (2017) 1749–1756, <https://doi.org/10.1021/acscatal.6b03147>.
- [6] Y. Wang, H. Shen, K.J.T. Livi, D. Raciti, H. Zong, J. Gregg, M. Onadeko, Y. Wan, A. Watson, C. Wang, Copper nanocubes for CO_2 reduction in gas diffusion electrodes, *Nano Lett.* 19 (2019) 8461–8468, <https://doi.org/10.1021/acs.nanolett.9b02748>.
- [7] A. Loiudice, P. Lobaccaro, E.A. Kamali, T. Thao, B.H. Huang, J.W. Ager, R. Buonsanti, Tailoring copper nanocrystals towards C_2 products in electrochemical CO_2 reduction, *Angew. Chem. Int. Ed.* 55 (2016) 5789–5792, <https://doi.org/10.1002/anie.201601582>.
- [8] C.G. Morales-Guio, S.A. Nitopi, J.T. Feaster, L. Wang, K.P. Kuhl, A. Jackson, N.C. Johnson, D.N. Abram, T. Hatsukade, C. Hahn, T.F. Jaramillo, Improved CO_2 reduction activity towards C_{2+} alcohols on a tandem gold on copper electrocatalyst, *Nat. Catal.* 1 (2018) 764–771, <https://doi.org/10.1038/s41929-018-0139-9>.
- [9] D. Raciti, M. Mao, J.H. Park, C. Wang, Local pH effect in the CO_2 reduction reaction on high-surface-area copper electrocatalysts, *J. Electrochem. Soc.* 165 (2018) F799–F804, <https://doi.org/10.1149/2.0521810jes>.
- [10] B. Qin, H. Wang, F. Peng, H. Yu, Y. Cao, Effect of the surface roughness of copper substrate on three-dimensional tin electrode for electrochemical reduction of CO_2 into $HCOOH$, *J. CO_2 Util.* 21 (2017) 219–223, <https://doi.org/10.1016/j.jcou.2017.07.012>.
- [11] K. Jiang, Y. Huang, G. Zeng, F.M. Toma, W.A. Goddard, A.T. Bell, Effects of surface roughness on the electrochemical reduction of CO_2 over Cu, *ACS Energy Lett.* 5 (2020) 1206–1214, <https://doi.org/10.1021/acsenergylett.0c00482>.
- [12] Y. Wang, P. Han, X. Lv, L. Zhang, G. Zheng, Defect and interface engineering for aqueous electrocatalytic CO_2 reduction, *Joule*. 2 (2018) 2551–2582, <https://doi.org/10.1016/j.joule.2018.09.021>.
- [13] Y. Lum, B. Yue, P. Lobaccaro, A.T. Bell, J.W. Ager, Optimizing C–C coupling on oxide-derived copper catalysts for electrochemical CO_2 reduction, *J. Phys. Chem. C* 121 (2017) 14191–14203, <https://doi.org/10.1021/acs.jpcc.7b03673>.
- [14] T.-T. Zhuang, Z.-Q. Liang, A. Seifitokaldani, Y. Li, P. De Luna, T. Burdyny, F. Che, F. Meng, Y. Min, R. Quintero-Bermudez, C.T. Dinh, Y. Pang, M. Zhong, B. Zhang, J. Li, P.-N. Chen, X.-L. Zheng, H. Liang, W.-N. Ge, B.-J. Ye, D. Sinton, S.-H. Yu, E.H. Sargent, Steering post-C–C coupling selectivity enables high efficiency electroreduction of carbon dioxide to multi-carbon alcohols, *Nat. Catal.* 1 (2018) 421–428, <https://doi.org/10.1038/s41929-018-0084-7>.
- [15] W. Tang, A.A. Peterson, A.S. Varela, Z.P. Jovanov, L. Bech, W.J. Durand, S. Dahl, J. K. Nørskov, I. Chorkendorff, The importance of surface morphology in controlling the selectivity of polycrystalline copper for CO_2 electroreduction, *Phys. Chem. Chem. Phys.* 14 (2012) 76–81, <https://doi.org/10.1039/C1CP22700A>.
- [16] D. Ren, J. Fong, B.S. Yeo, The effects of currents and potentials on the selectivities of copper toward carbon dioxide electroreduction, *Nat. Commun.* 9 (2018) 925, <https://doi.org/10.1038/s41467-018-03286-w>.

- [17] Y. Feng, Z. Li, H. Liu, C. Dong, J. Wang, S.A. Kulich, X. Du, Laser-prepared CuZn alloy catalyst for selective electrochemical reduction of CO₂ to ethylene, *Langmuir*. 34 (2018) 13544–13549, <https://doi.org/10.1021/acs.langmuir.8b02837>.
- [18] J. Huang, M. Mensi, E. Oveisi, V. Mantella, R. Buonsanti, Structural sensitivities in bimetallic catalysts for electrochemical CO₂ reduction revealed by Ag–Cu nanodimers, *J. Am. Chem. Soc.* 141 (2019) 2490–2499, <https://doi.org/10.1021/jacs.8b12381>.
- [19] T. Zhang, Z. Li, J. Zhang, J. Wu, Enhance CO₂-to-C₂+ products yield through spatial management of CO transport in Cu/ZnO tandem electrodes, *J. Catal.* 387 (2020) 163–169, <https://doi.org/10.1016/j.jcat.2020.05.002>.
- [20] R. Kortlever, J. Shen, K.J.P. Schouten, F. Calle-Vallejo, M.T.M. Koper, Catalysts and reaction pathways for the electrochemical reduction of carbon dioxide, *J. Phys. Chem. Lett.* 6 (2015) 4073–4082, <https://doi.org/10.1021/acs.jpcclett.5b01559>.
- [21] F. Calle-Vallejo, M.T.M. Koper, Theoretical considerations on the Electroreduction of CO to C₂ species on Cu(100) electrodes, *Angew. Chem. Int. Ed.* 52 (2013) 7282–7285, <https://doi.org/10.1002/anie.201301470>.
- [22] E. Pérez-Gallent, M.C. Figueiredo, F. Calle-Vallejo, M.T.M. Koper, Spectroscopic observation of a hydrogenated CO dimer intermediate during CO reduction on Cu (100) electrodes, *Angew. Chem. Int. Ed.* 56 (2017) 3621–3624, <https://doi.org/10.1002/anie.201700580>.
- [23] J. Timoshenko, H.S. Jeon, I. Sinev, F.T. Haase, A. Herzog, B. Roldan Cuenya, Linking the evolution of catalytic properties and structural changes in copper–zinc nanocatalysts using operando EXAFS and neural-networks, *Chem. Sci.* 11 (2020) 3727–3736, <https://doi.org/10.1039/D0SC00382D>.
- [24] F.S. Roberts, K.P. Kuhl, A. Nilsson, High selectivity for ethylene from carbon dioxide reduction over copper nanocube electrocatalysts, *Angew. Chem.* 127 (2015) 5268–5271, <https://doi.org/10.1002/ange.201412214>.
- [25] A. Verdager-Casadevall, C.W. Li, T.P. Johansson, S.B. Scott, J.T. McKeown, M. Kumar, I.E.L. Stephens, M.W. Kanan, I. Chorkendorff, Probing the active surface sites for CO reduction on oxide-derived copper electrocatalysts, *J. Am. Chem. Soc.* 137 (2015) 9808–9811, <https://doi.org/10.1021/jacs.5b06227>.
- [26] C.W. Li, J. Ciston, M.W. Kanan, Electroreduction of carbon monoxide to liquid fuel on oxide-derived nanocrystalline copper, *Nature*. 508 (2014) 504–507, <https://doi.org/10.1038/nature13249>.
- [27] C.W. Li, M.W. Kanan, CO₂ reduction at low overpotential on Cu electrodes resulting from the reduction of thick Cu₂O films, *J. Am. Chem. Soc.* 134 (2012) 7231–7234, <https://doi.org/10.1021/ja3010978>.
- [28] K.P. Kuhl, E.R. Cave, D.N. Abram, T.F. Jaramillo, New insights into the electrochemical reduction of carbon dioxide on metallic copper surfaces, *Energy Environ. Sci.* 5 (2012) 7050, <https://doi.org/10.1039/c2ee21234j>.
- [29] E. Pérez-Gallent, G. Marcandalli, M.C. Figueiredo, F. Calle-Vallejo, M.T.M. Koper, Structure- and potential-dependent cation effects on CO reduction at copper single-crystal electrodes, *J. Am. Chem. Soc.* 139 (2017) 16412–16419, <https://doi.org/10.1021/jacs.7b10142>.
- [30] J.E. Pander, D. Ren, Y. Huang, N.W.X. Loo, S.H.L. Hong, B.S. Yeo, Understanding the heterogeneous electrocatalytic reduction of carbon dioxide on oxide-derived catalysts, *ChemElectroChem.* 5 (2018) 219–237, <https://doi.org/10.1002/celec.201701100>.
- [31] F.S. Roberts, K.P. Kuhl, A. Nilsson, Electroreduction of carbon monoxide over a copper nanocube catalyst: surface structure and pH dependence on selectivity, *ChemCatChem.* 8 (2016) 1119–1124, <https://doi.org/10.1002/cctc.201501189>.
- [32] Y. Kwon, Y. Lum, E.L. Clark, J.W. Ager, A.T. Bell, CO₂ electroreduction with enhanced ethylene and ethanol selectivity by nanostructuring polycrystalline copper, *ChemElectroChem.* 3 (2016) 1012–1019, <https://doi.org/10.1002/celec.201600068>.
- [33] C.S. Chen, A.D. Handoko, J.H. Wan, L. Ma, D. Ren, B.S. Yeo, Stable and selective electrochemical reduction of carbon dioxide to ethylene on copper mesocrystals, *Catal. Sci. Technol.* 5 (2015) 161–168, <https://doi.org/10.1039/C4CY00906A>.
- [34] K.J.P. Schouten, E.P. Gallent, M.T.M. Koper, The electrochemical characterization of copper single-crystal electrodes in alkaline media, *J. Electroanal. Chem.* 699 (2013) 6–9, <https://doi.org/10.1016/j.jelechem.2013.03.018>.
- [35] G. Bianchi, P. Longhi, Copper in sea-water, potential-pH diagrams, *Corros. Sci.* 13 (1973) 853–864, [https://doi.org/10.1016/S0010-938X\(73\)80067-8](https://doi.org/10.1016/S0010-938X(73)80067-8).
- [36] H. Liu, Y. Zhou, S.A. Kulich, J.-J. Li, L.-L. Han, S.-Z. Qiao, X.-W. Du, Scalable synthesis of hollow Cu₂O nanocubes with unique optical properties via a simple hydrolysis-based approach, *J. Mater. Chem. A* 1 (2013) 302–307, <https://doi.org/10.1039/C2TA00138A>.
- [37] Y. Hori, O. Koga, H. Yamazaki, T. Matsuo, Infrared spectroscopy of adsorbed CO and intermediate species in electrochemical reduction of CO₂ to hydrocarbons on a Cu electrode, *Electrochim. Acta* 40 (1995) 2617–2622, [https://doi.org/10.1016/0013-4686\(95\)00239-B](https://doi.org/10.1016/0013-4686(95)00239-B).
- [38] A.S. Varela, M. Kroschel, T. Reier, P. Strasser, Controlling the selectivity of CO₂ electroreduction on copper: the effect of the electrolyte concentration and the importance of the local pH, *Catal. Today* 260 (2016) 8–13, <https://doi.org/10.1016/j.cattod.2015.06.009>.
- [39] D. Raciti, M. Mao, C. Wang, Mass transport modelling for the electroreduction of CO₂ on Cu nanowires, *Nanotechnology.* 29 (2018), <https://doi.org/10.1088/1361-6528/aa9bd7> 044001.
- [40] H.S. Jeon, J. Timoshenko, F. Scholten, I. Sinev, A. Herzog, F.T. Haase, B. Roldan Cuenya, Operando insight into the correlation between the structure and composition of CuZn nanoparticles and their selectivity for the electrochemical CO₂ reduction, *J. Am. Chem. Soc.* 141 (2019) 19879–19887, <https://doi.org/10.1021/jacs.9b10709>.
- [41] D. Ren, B.S.-H. Ang, B.S. Yeo, Tuning the selectivity of carbon dioxide electroreduction toward ethanol on oxide-derived Cu x Zn catalysts, *ACS Catal.* 6 (2016) 8239–8247, <https://doi.org/10.1021/acscatal.6b02162>.
- [42] S. Ikeda, S. Shiozaki, J. Susuki, K. Ito, H. Noda, Electroreduction of CO₂ using Cu/Zn Oxides Loaded Gas Diffusion Electrodes, 1998, pp. 225–230, [https://doi.org/10.1016/S0167-2991\(98\)80748-9](https://doi.org/10.1016/S0167-2991(98)80748-9).
- [43] H.-J. Yang, S.-Y. He, H.-L. Chen, H.-Y. Tuan, Monodisperse copper nanocubes: synthesis, self-assembly, and large-area dense-packed films, *Chem. Mater.* 26 (2014) 1785–1793, <https://doi.org/10.1021/cm403098d>.