



Universiteit
Leiden
The Netherlands

Dioxygen reduction in acetonitrile with copper pyridylalkylamine complexes: the influence of acid strength on the catalytic performance

Langerman, M.; Dorth, M. van; Hetterscheid, D.G.H.

Citation

Langerman, M., Dorth, M. van, & Hetterscheid, D. G. H. (2023). Dioxygen reduction in acetonitrile with copper pyridylalkylamine complexes: the influence of acid strength on the catalytic performance. *European Journal Of Inorganic Chemistry*, 26(24).
doi:10.1002/ejic.202300218

Version: Publisher's Version

License: [Creative Commons CC BY 4.0 license](https://creativecommons.org/licenses/by/4.0/)

Downloaded from: <https://hdl.handle.net/1887/3728487>

Note: To cite this publication please use the final published version (if applicable).

Dioxygen Reduction in Acetonitrile with Copper Pyridylalkylamine Complexes: The Influence of Acid Strength on the Catalytic Performance

Michiel Langerman,^[a] Micha van Dorth,^[a] and Dennis G. H. Hetterscheid^{*[a]}

The pyridylalkylamine copper complex $[\text{Cu}(\text{tmpa})(\text{L})]^{2+}$ has previously been proposed to reduce dioxygen via a dinuclear resting state, based on experiments in organic aprotic solvents using chemical reductants. Conversely, a mononuclear reaction mechanism was observed under electrochemical conditions in a neutral aqueous solution. We have investigated the electrochemical oxygen and hydrogen peroxide reduction reaction catalyzed by $[\text{Cu}(\text{tmpa})(\text{L})]^{2+}$ in acetonitrile, using several different acids over a range of pK_a . We demonstrate that strong acids lead to the loss of redox reversibility and to the destabilization

of the copper complex under non-catalytic conditions. Under milder conditions, the electrochemical oxygen reduction reaction (ORR) was shown to proceed via a mononuclear catalytic intermediate, similar to what we have previously observed in water. However, in acetonitrile the catalytic rate constants of the ORR are dramatically lower by a factor 10^5 , which is caused by the unfavorable equilibrium of formation of $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^{+}$ in acetonitrile. This results in higher catalytic rates for the reduction of hydrogen peroxide than for the ORR.

Introduction

A thorough fundamental understanding of the oxygen reduction reaction (ORR) is indispensable in light of the electrification of our infrastructure and the application of fuel cell chemistry.^[1] Also nature is very capable of activation dioxygen, and here in particular, Cu sites play a significant role. This holds both for oxygenase chemistry,^[2] and oxidase chemistry.^[3] Many dioxygen adducts of copper have been spectroscopically detected, identified and isolated, and many reaction paths involving these species have been unraveled, leading to a great understanding of this chemistry.^[4] This wealth of available knowledge concerning the nature of reaction intermediates and their reaction kinetics may help shed light on the catalytic pathway of the ORR by homogeneous electrocatalysts. Indeed, it has been established that the ORR can indeed be catalyzed by Cu-complexes.^[4–5] Several examples of mixtures of complex with carbon black have been reported to give excellent catalytic results,^[6] but in quite some cases one may wonder to which extend the catalytic reaction still occurs at well-defined homogeneous sites.^[7] It was also shown that in particular Cu-tmpa is an excellent ORR catalyst (Cu-tmpa = tris(2-pyridylmeth-

yl)amine).^[5d,h,6c,8] The chemistry of Cu-tmpa with O_2 has been studied in detail by Karlin and others in organic solvent.^[4e,8a,9] We showed that the ORR in aqueous solution occurs with record breaking turnover frequencies of $1.8 \times 10^6 \text{ s}^{-1}$, and proceeds via a stepwise mechanism wherein hydrogen peroxide is formed as an obligatory intermediate.^[5d] H_2O_2 itself is reduced in a slower electrochemical reaction, which most likely occurs via a Fenton like mechanism.^[10] Yet, the very high catalytic rates observed for these reactions and the abundance of protons in the aqueous environment preclude clear identification of reaction intermediates.


Earlier studies with Cu-tmpa and O_2 in organic solvent with stoichiometric amounts of sacrificial reductant paints a different story. It was shown that O_2 reduction in acetone mediated by ferrocene (Fc) as a sacrificial reducing agent,^[5b,h,11] that the dinuclear peroxido complex $[(\text{Cu}^{\text{II}}(\text{tmpa}))(\mu\text{-O}_2)]^{2+}$ is formed as a resting state upon the addition of O_2 to the Cu-tmpa compound. From this resting state dioxygen reduction can take place after addition of a proton source. Whether this dinuclear peroxido complex is responsible for the catalysis is unclear. For a similar complex with a pivalamido functional group attached to one of the pyridine arms, $[\text{Cu}(\text{PV-tmpa})(\text{L})]^{2+}$, it was shown that a mononuclear Cu-OOH species is formed upon addition of acid to a solution containing the dinuclear species, from which the catalytic cycle proceeds.^[5b] Thus, this shows that O_2 bridging between two Cu centres is perhaps not essential for the breaking of the O–O bond. Similarly, the related complex $[\text{Cu}(\text{tepa})]^{2+}$ (tepa = tris[2-(2-pyridyl)ethyl]-amine) does not form a dinuclear species at all in the presence of O_2 and ferrocene in acetone, but is able to perform the 2-electron reduction of O_2 to H_2O_2 upon addition of HClO_4 .^[11c] The proposed catalytic mechanisms for the electrochemical ORR in water and the ORR in acetone using sacrificial reductants are shown in Scheme 1.

[a] Dr. M. Langerman, M. van Dorth, Dr. D. G. H. Hetterscheid
Leiden University
Faculty of Science
Leiden Institute of Chemistry, Leiden, Netherlands
E-mail: d.g.h.hetterscheid@chem.leidenuniv.nl
<https://hetterscheidgroup.com/>

Supporting information for this article is available on the WWW under <https://doi.org/10.1002/ejic.202300218>

Part of the Special Collection on "Inorganic Reaction Mechanisms".

© 2023 The Authors. European Journal of Inorganic Chemistry published by Wiley-VCH GmbH. This is an open access article under the terms of the Creative Commons Attribution License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited.

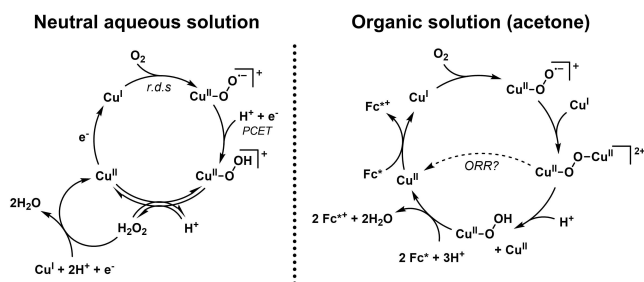

Scheme 1. Different catalytic mechanisms have been proposed for the reduction of O_2 by Cu-tmpa in neutral aqueous solution (electrochemistry driven),^[5d] and in acetone (ferrocene-mediated).^[5b,h,9c] The tmpa ligand is excluded from the scheme for clarity.

We have shown in our previous work that mechanistic details are not necessarily transferable from one system to the other, either due to differences between chemical and electrochemical reduction, such as much faster electrochemical electron transfer, the nature of the solvent, or the acidity and mobility of the protons involved in the catalytic mechanism. Therefore, an important next step would be to study the electrocatalytic ORR by Cu-tmpa in non-aqueous solutions, where the precise specification of all catalytic species under resting conditions is known. This would help to bridge the gap in knowledge between the very efficient oxygen reduction chemistry in aqueous conditions and the stoichiometric studies by Karlin *et al.* in organic solvents. Here, we report the electrochemical behavior of Cu-tmpa in acetonitrile (MeCN), using several acids with a range of different pKa values as proton donors. Additionally, the electrocatalytic performance of Cu-tmpa for the ORR and the hydrogen peroxide reduction reaction (HPRR) will be discussed, including the overpotential observed in a buffered electrolyte solution.

Results and Discussion

Behavior of Cu-tmpa in an MeCN electrolyte solution in the absence of acid

The redox behavior of Cu-tmpa in an acetonitrile solution containing the supporting electrolyte NBu_4PF_6 (100 mM) was investigated in the absence of acids. Cyclic voltammograms (CVs) of Cu-tmpa in this solution were recorded using a Glassy Carbon (GC) working electrode ($A = 0.0707 \text{ cm}^2$). When the solution is saturated with argon, a well-defined reversible $\text{Cu}^{\text{II/I}}$ redox couple is observed at $E_{1/2} = -0.41 \text{ mV vs. Fc}^+/\text{Fc}$ with a peak-to-peak separation (ΔE_p) of 59 mV, shown in Figure 1a. This corresponds well to the previously reported half-wave potential for this complex in acetonitrile.^[12] Upon saturation of the solution with 1 atm O_2 , the initial reduction of Cu^{II} to Cu^{I} is still observed (Figure 1b). However, an additional reduction takes place when the applied potential is lower than -0.80 V . At the same time, the oxidative current associated with the oxidation of Cu^{I} to Cu^{II} is significantly lower than the same oxidative peak measured in the presence of 1 atm argon.

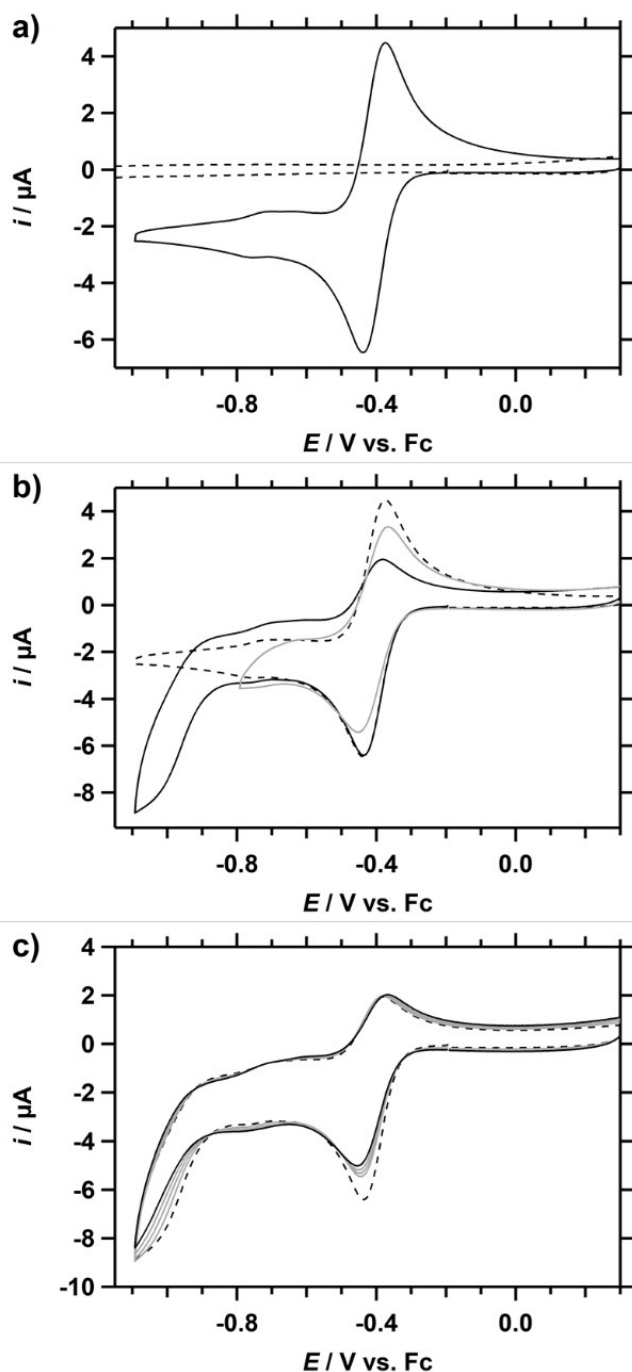


Figure 1. a) Cyclic voltammogram of Cu-tmpa (0.3 mM) in the absence of acid, including GC blank measurement (dashed), under 1 atm Ar. b) CVs of Cu-tmpa in the presence of 1 atm O_2 with varying potential windows. The redox couple in the presence of Ar is shown for comparison (dashed). c) CVs showing the redox behavior in the presence of oxygen over 5 cycles; first scan (dashed trace) and last scan (solid trace). Conditions: NBu_4PF_6 (100 mM) in MeCN, 100 mV s^{-1} , 293 K.

Subsequent CV cycles in the same potential window (up to -1.1 V) also show a decrease of the $\text{Cu}^{\text{II/I}}$ reduction peak and an increase in of the ΔE_p from 56 mV in the first scan to 88 mV (Figure 1c). The oxidation at -0.35 V reappears when this measurement is repeated while limiting the lower limit of the

potential window to -0.75 V (Figure 1b, grey trace). However, the ΔE_p remains at 88 mV and is stable over several scans.

Selection of acids and homoconjugation of acids and conjugate bases

Much research has been performed on electrocatalytic reactions for small molecule conversion catalyzed by transition metal complexes in non-aqueous electrolyte solutions, particularly MeCN and DMF, often for solubility reasons.^[13] However, comparing the catalytic performance of different molecular electrocatalysts in different non-aqueous media using a range of different proton sources may pose a significant challenge. Thermodynamics of the catalytic reactions of interest vary wildly with differing conditions and are more challenging to probe than in aqueous solutions, where reactions can easily be referenced to the H_2/H^+ couple, regardless of different acids, bases, or supporting electrolytes being used. To be able to determine the overpotential of the ORR in organic media, the equilibrium potential of the reaction has to be known for the given conditions. Recent work by Roberts and Bullock,^[14] and Pegis, Appel and Mayer^[15] has been key in providing a reliable method for determination of the equilibrium potential of the hydrogen evolution reaction (HER) and in determining the standard potential of O_2/H_2O in MeCN and DMF, thus enabling more reliable and meaningful comparisons of the performance of catalysts towards the ORR.

However, the standard potentials for the catalytic reactions only apply when both the acid (HA or HB^+) and its base (A^- or B) are present in the solution in equal amounts, as different ratios can cause significant shifts in the equilibrium potential of the studied reactions. This is especially relevant as there will be a significant decrease in $[HA]$ and concurrent increase in $[A^-]$ during the catalytic reaction, resulting in shift of the equilibrium potential as the catalytic reaction progresses. This requires the use of a buffered electrolyte for the determination of the overpotential, with equal concentrations of HA and A^- .

One complicating factor connected to the use of such a buffered electrolyte solution is the occurrence of homoconjugation. Homoconjugation occurs when the base A^- (or B) reacts with the acid HA (or HB^+), resulting in the formation of the conjugate species HA_2^- (or HB_2^+). Thus, upon homoconjugation of the acid and the conjugate base, the acidity of the solution and the effective concentration of available protons is reduced. However, it does not affect the equilibrium potential, as the ratio of available $[HA]$ to $[A^-]$ is not changed. The extent of this effect is dependent on the homoconjugation constant (K_f), which varies with different acids. The K_f values of the acids relevant to this work are shown in Table 1. It has been reported that triethylamine does not undergo homoconjugation.^[16]

Table 1. Acid strength (pK_a) and homoconjugation formation constants (K_f) in MeCN of the acids used in this work.

Acid	pK_a	$\log(K_f)$
HOAc	23.5 ^[17]	3.9 ^[17b]
$HNEt_3^+$	18.8 ^[14]	n/a
TFA	12.7 ^[17]	3.9 ^[17b]
$HDMF^+$	6.1 ^[17b]	1.6 ^[13a]

Stability and electrochemical behavior of Cu-tmpa in the presence of different organic acids

To study the electrochemical activity of Cu-tmpa in acetonitrile, several different organic acids were used, namely triethylammonium ($HNEt_3^+$), acetic acid (HOAc), trifluoroacetic acid (HTFA), and dimethylformamidium ($HDMF^+$). These acids find common use in homogeneous electrocatalysis as proton sources for HER and ORR and were chosen for their range of pK_a values in MeCN, as shown in Table 1. As the strength of the aforementioned acids span a wide range of pK_a , from very strong acid ($HDMF$)OTf to the very weakly acidic $HNEt_3PF_6$, the stability of Cu-tmpa in the presence of the selected acids was studied using both cyclic voltammetry and UV-vis absorption measurements (see SI section S9). Unless otherwise stated, all electrochemical measurements were performed in MeCN containing NBu_4PF_6 (0.1 M) as supporting electrolyte and the potential is reported versus the Fc^+/Fc redox couple.

The CV of Cu-tmpa in 50 mM $HNEt_3PF_6$ saturated with 1 atm argon showed a reversible redox couple at -0.61 V (Figure 2). In an electrolyte solution containing HOAc (20 mM) a reversible redox couple is observed at -0.40 V, which is very close to the $E_{1/2}$ of the complex in the absence of acid. In the presence of either of these acids, the CV was shown to be very stable over multiple cycles. However, electrochemical stability was not observed in solutions containing HTFA or $HDMF^+$. In the presence of HTFA, only the reduction of Cu^{II} to Cu^I is observed at -0.30 V, but the associated oxidation peak is absent. When scanning below -0.9 V a small reduction event is visible, and a sharp oxidative stripping peak appears on the forward scan of the CV. With ($HDMF$)OTf the voltammogram is even less-defined, showing a broad first reduction starting below 0 V, followed by second broad reduction event below -0.5 V. Below $E = -0.9$ V a sharp reduction is observed, which is indicative of proton reduction.

Although the voltammograms of the full potential window are shown in Figure 2, limiting the potential windows of the measurements to -0.5 V did not lead to the re-appearance of the $Cu^{II/I}$ oxidation peak, whether in a solution containing HTFA or ($HDMF$)OTf. Considering this lack of reversible redox couple, or as is the case with ($HDMF$)OTf, the lack of clearly defined reduction and oxidation events that could be assigned to Cu-tmpa even under non-catalytic conditions. Therefore these acids were no longer considered. In water, it was found that below pH 4 the stability of Cu-tmpa decreased, thought to be due to demetallation of a Cu^{II} -tmpa or Cu^I -tmpa complex, while the complex is stable under strongly alkaline conditions.^[8c] Protonation of the pyridine moieties at low pH is a likely cause for

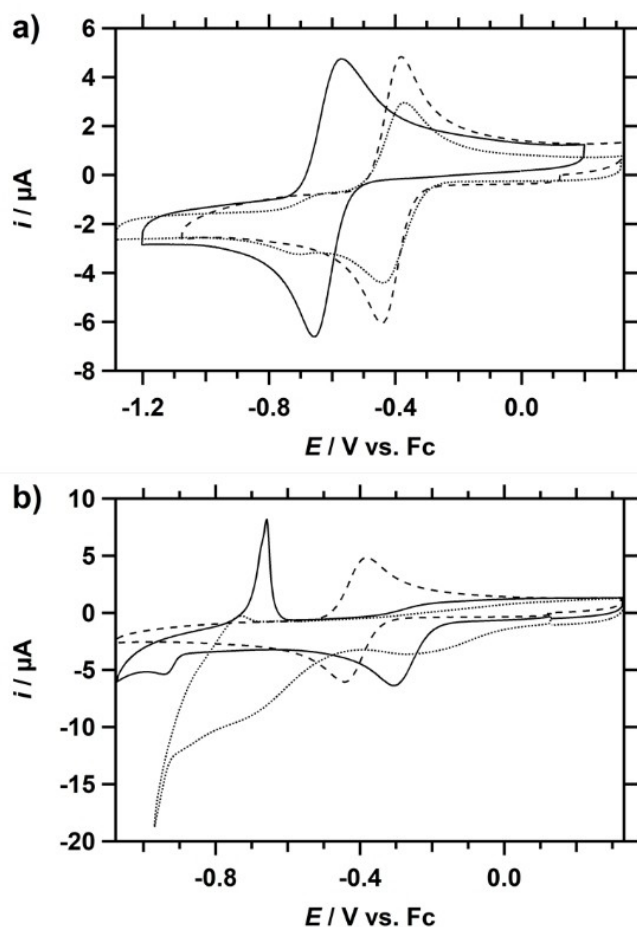


Figure 2. CVs of Cu-tmpa (0.3 mM) in a solution with (a) 50 mM HNEt₃PF₆ (solid) and 20 mM HOAc (dotted), and (b) 20 mM (HDMF)OTf (solid) and 20 mM TFA (dotted), under 1 atm Ar. For reference, a CV of the complex in absence of acid (dashed trace) is shown in both. Conditions: NBu₄PF₆ (100 mM) in MeCN, 100 mVs⁻¹, 293 K.

the observed instability of Cu-tmpa, both in water and organic solvents.

Comparison of catalytic activity between unbuffered and buffered acid conditions

Acetic acid

The redox and catalytic behavior of Cu-tmpa was investigated by performing cyclic voltammetry measurements in a NBu₄PF₆ electrolyte solution containing HOAc or a buffered HOAc/Oac⁻ acid-conjugate base mixture, using a glassy carbon electrode. The resulting CVs are shown in Figure 3a. The Cu^{II/I} redox couple with $E_{1/2} = -0.40$ V has a ΔE_p of 66 mV in the electrolyte solution containing 20 mM HOAc saturated with 1 atm argon. Additionally, a small redox event is visible at -0.68 V. In the solution containing the acid-conjugate base pair HOAc/Oac⁻ (each 20 mM), the redox couple is shifted to a more negative potential, with $E_{1/2} = -0.73$ V and a larger ΔE_p of 78 mV.

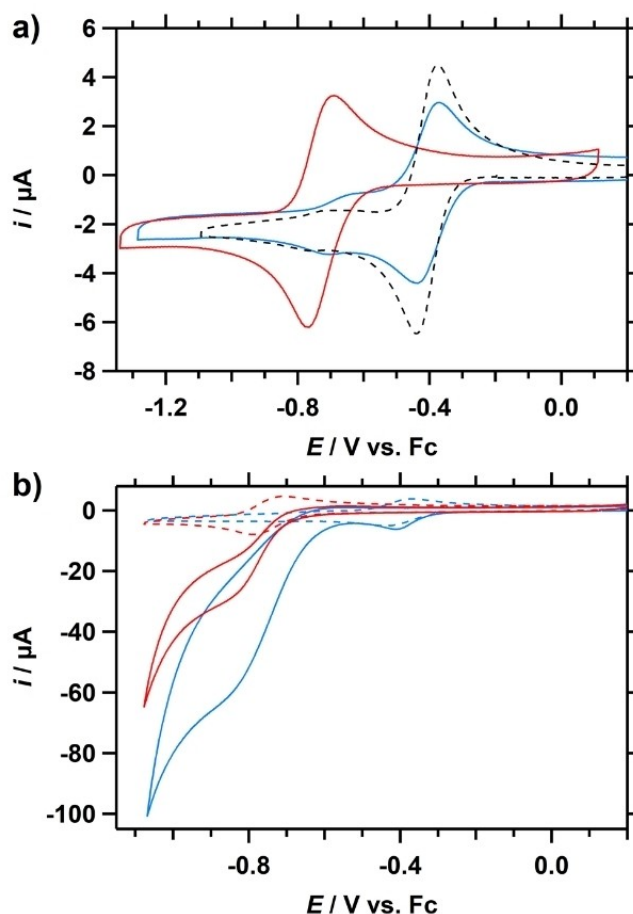


Figure 3. CV of Cu-tmpa (0.3 mM) under 1 atm Ar (a) and under 1 atm O₂ (b), in the presence of 20 mM HOAc (blue) or 20 mM HOAc/OAc⁻ (red). For reference, a CV of the complex in absence of acid under 1 atm Ar (dashed trace) is shown on the left. Conditions: NBu₄PF₆ (100 mM) in MeCN, 100 mVs⁻¹, 293 K.

However, only a single redox couple is observed under these conditions as opposed to the two distinct redox couples observed in HOAc.

When the solutions are saturated with O₂ a catalytic wave is observed in both cases (Figure 3b), however a lower catalytic current is observed for the buffered system. This is unsurprising, as homoconjugation lowers the availability of the protons compared to the situation where no conjugated base is present. Interestingly, Cu-tmpa shows very different catalytic characteristics under both conditions. With HOAc, the reduction from Cu^{II} to Cu^I is still distinctly visible, and the onset potential of the catalytic reaction is 220 mV below the peak reduction potential (E_{pc}) of -0.44 V in the absence of oxygen. Here, the catalytic onset potential is defined as the potential where the current is 1 μA higher than the current in the absence of the substrate. In the solution containing the acid-conjugate base pair, the reduction of Cu^{II} and the onset of catalysis overlap, and the catalytic half-wave potential ($E_{cat/2}$) of -0.77 V coincides closely with E_{pc} (-0.77 V). This is more easily visualized after performing a background correction. The resulting linear sweep voltammograms (LSVs) are shown in Figure S4 (Section S3). The back-

ground corrected LSVs show a peak catalytic current (i_{cat}) of 56 μA in the solution containing HOAc, while the i_{cat} in the buffered solution is almost halved to 29 μA .

To get more insight into the catalytic pathway and the product that is formed, the reduction of H_2O_2 by Cu-tmpa was investigated. One key difference between the conditions in which the ORR and HPRR were performed is the presence of 30 mM of H_2O during the HPRR, as H_2O_2 was added in the form of a 30% solution in water. CVs of the complex in both unbuffered and buffered electrolyte solution are shown in Figure 4. As was the case for the ORR, the onset of H_2O_2 reduction in the presence of HOAc only starts after the complex has been reduced to Cu^{I} . However, the onset potential of the HPRR is shifted by -100 mV versus the onset of the ORR. For the solution containing HOAc a single catalytic wave is observed, while for the buffered system a double S-shaped catalytic curve is visible with a much lower current, which again can be explained by a lowered availability of acidic protons compared to the electrolyte solution containing only HOAc, due to homoconjugation. Additionally, acetate coordination to Cu-tmpa may play a role in the buffered solution.

HNET_3PF_6

Similarly, the use of protonated triethylamine as the proton donor for the ORR was investigated. Cyclic voltammograms were recorded in a NBu_4PF_6 electrolyte solution containing HNET_3^+ (in the form of HNET_3PF_6) or a buffered $\text{HNET}_3^+/\text{NET}_3$ acid-conjugate base mixture and are shown in Figure 5. In the presence of argon, the $E_{1/2}$ of the Cu-tmpa redox couple in the solution containing HNET_3^+ is -0.61 V. Seemingly, Cu-tmpa has a well-defined single redox couple, although the somewhat large ΔE_p of 88 mV indicates a degree of irreversibility. On the other hand, in the solution containing the $\text{HNET}_3^+/\text{NET}_3$ acid-conjugate base pair, two distinct reductions are observed, one

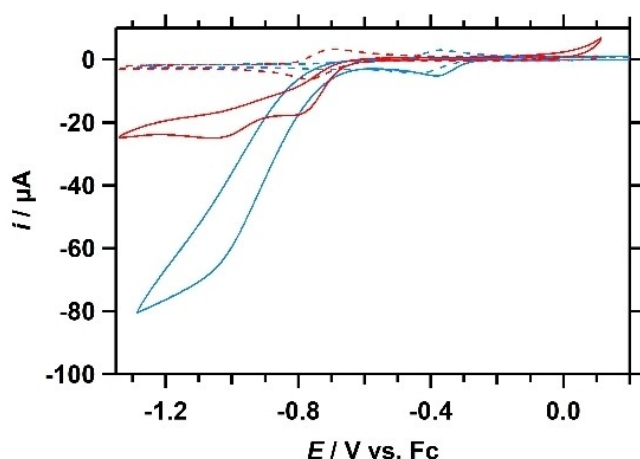


Figure 4. CV of Cu-tmpa (0.3 mM) under 1 atm Ar (dotted lines) and with 8.1 mM H_2O_2 under 1 atm Ar (solid lines), in the presence of 20 mM HOAc (blue) or HOAc/OAc^- (each 20 mM; red). Conditions: NBu_4PF_6 (100 mM) in MeCN, $[\text{H}_2\text{O}] = 30$ mM, 100 mV s^{-1} , 293 K.

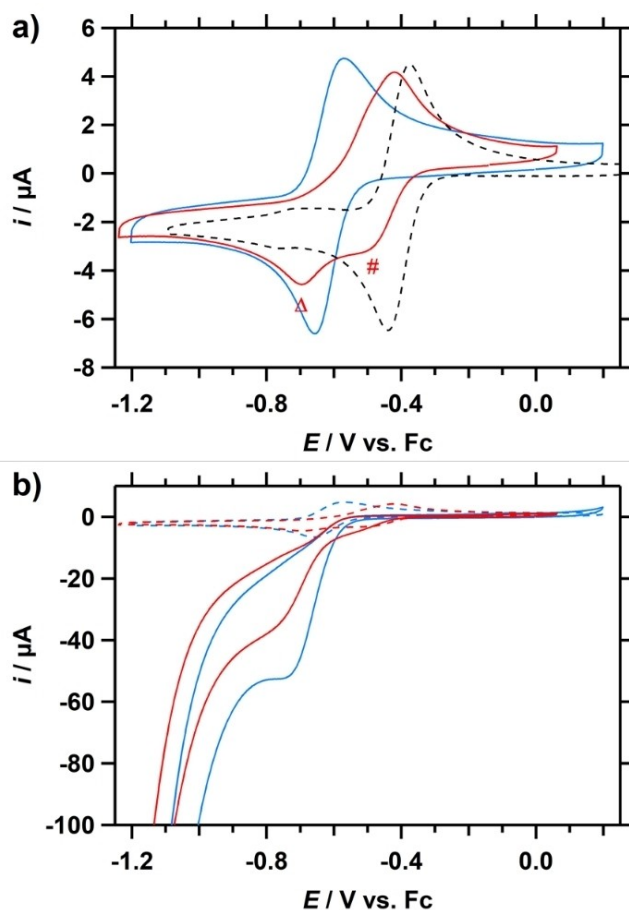


Figure 5. CVs of Cu-tmpa (0.3 mM) under 1 atm Ar (a) and under 1 atm O_2 (b), in the presence of 50 mM HNET_3PF_6 (blue) or $\text{HNET}_3\text{PF}_6/\text{NET}_3$ (each 50 mM; red). For reference, a CV of the complex in absence of acid under 1 atm Ar (dashed trace) is shown in (a). Conditions: NBu_4PF_6 (100 mM) in MeCN, 100 mV s^{-1} , 293 K.

with a cathodic peak potential (E_{pc}) centered at -0.50 V (marked by #) and the second at -0.70 V (marked by Δ). These are paired with a broadened oxidation wave, which is caused by two overlapping redox couples. This is more evident when looking at a differential-pulse voltammogram (DPV) measured in the same solution (Figure S3, SI section S2). In the DPV, a smaller oxidative peak is visible at a more negative potential, shifted by -0.20 V from the main oxidative peak. This is the same difference in potential as observed for the E_{pc} of the two reductive peaks. The $E_{1/2}$ of the main redox event is -0.462 V and has a ΔE_p of 81 mV. The behavior of Cu-tmpa under these conditions is opposite to what was observed in presence of HOAc and HOAc/OAc^- , where the redox couple was shifted to more negative potentials in the buffered electrolyte solution, while no shift was observed in the solution with only HOAc.

In the presence of 1 atm O_2 , a catalytic response is observed in CV for both buffered and unbuffered electrolyte solutions containing 0.3 mM Cu-tmpa (Figure 5b). The catalytic onset in the unbuffered solution (-0.56 V) coincides with the redox potential of Cu-tmpa under argon. In the buffered solution the catalytic onset coincides with the previously discussed second

redox event at -0.70 V (Figure 5a; Δ) that is observed in the same buffered solution under argon. As was observed with HOAc, Cu-tmpa shows a higher maximum current and a somewhat earlier onset in the unbuffered electrolyte solution, compared to that observed in the buffered electrolyte solution. The background corrected LSVs show an i_{cat} of $53 \mu\text{A}$ in the solution containing HNEt_3^+ (Figure S4a), while the i_{cat} in the buffered $\text{HNEt}_3^+/\text{NEt}_3$ electrolyte solution is about a third lower at $35 \mu\text{A}$ (Figure S4b).

The CVs of the catalytic response upon the addition of H_2O_2 to the electrolyte solutions containing 0.3 mM Cu-tmpa are shown in Figure 6. While similar peak catalytic currents are reached for both buffered and unbuffered solutions, some differences can be observed. In both cases, the catalytic wave seems to consist of two different waves (I and II), but in the buffered solution the initial "peak" current (I) is reached at a higher potential and lower current, while for the unbuffered system a higher current is reached and more overlap between the first (I) and second (II) wave is observed, which precludes the formation of a current plateau for the first wave.

For clarity, the electrochemical properties of Cu-tmpa in the presence of argon, O_2 , and H_2O_2 for the different acid and acid-

conjugate base systems, with equal concentrations of HA (or HB^+) and A^- (or B), have been summarized in Table 2 and Table 3.

OCP values for the determination of H_2/H^+ and the overpotential for the ORR in non-aqueous solutions

The open circuit potential (OCP) can be used as a direct measure of the equilibrium potential of the H^+/H_2 couple in organic solvent, which is especially useful in solvents where no robust pK_a scale is available and the standard potential of the H^+/H_2 redox couple is not known.^[14] In combination with the catalytic half-wave potential, the OCP can be used to determine overpotential and compare these with results obtained in different media.

The OCPs were measured using a platinum wire and averaged over a 60 second window in a 100 mM NBu_4PF_6 electrolyte solution saturated with H_2 , containing the desired acid or acid-conjugate base mixture, and referenced versus Fc^+/Fc . The resulting OCP values are summarized in Table 4. Buffering of the HNEt_3^+ solution resulted in the largest OCP shift of -297 mV , while buffering of the HOAc containing solution resulted in a positive shift of 162 mV . To determine the effect of water in the acetonitrile solutions on the OCP, the OCP values were also determined for the same solutions containing 0.10 M H_2O . Adding water to acetonitrile solutions containing either only the acid or a 1:1 acid-conjugate base mixture does not have a large effect on the OCP, at most only shifting the

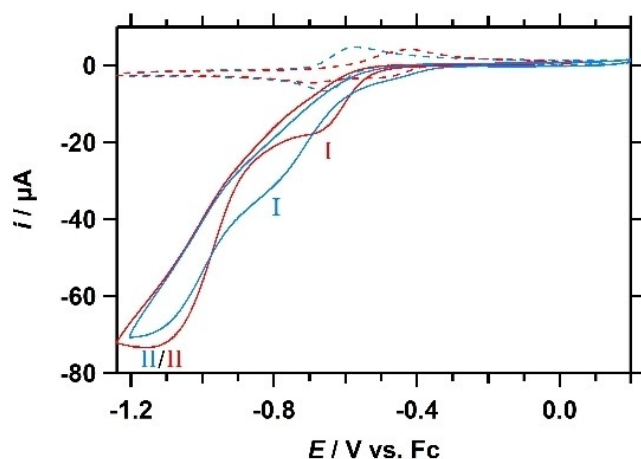


Figure 6. CVs of Cu-tmpa under 1 atm Ar (dashed lines) and with 8.1 mM H_2O_2 under 1 atm Ar (solid lines), in the presence of 50 mM HNEt_3PF_6 (blue) or $\text{HNEt}_3\text{PF}_6/\text{NEt}_3$ (each 50 mM ; red). Conditions: NBu_4PF_6 (100 mM) in MeCN, $[\text{H}_2\text{O}] = 30 \text{ mM}$, 100 mV s^{-1} , 293 K .

Table 2. Overview of the electrochemical properties of Cu-tmpa and its catalytic activity toward the ORR under different conditions.

	E_{pc} (V)	$E_{1/2}$ (V)	ΔE_{p} (mV)	$E_{\text{onset, ORR}}$	$E_{\text{cat}/2}$	i_{cat} (μA)
No acid	-0.44	-0.41	59	–	–	–
HNEt_3PF_6	-0.66	-0.61	88	-0.56	-0.65	53
$\text{HNEt}_3\text{PF}_6/\text{NEt}_3$	$-0.50^{[a]}$	-0.46	81	-0.52	-0.68	35
	$-0.70^{[b]}$					
HOAc	-0.44	-0.40	66	-0.56	-0.73	56
HOAc/ NBu_4OAc	-0.77	-0.73	78	-0.70	-0.77	29

[a] E_{pc} of the first reduction. [b] E_{pc} of the second reduction. E_{onset} is defined as the potential where the catalytic current i_{cat} is $1 \mu\text{A}$ higher than i_{p} under argon. Potential V vs. Fc^+/Fc .

Table 3. Overview of the electrochemical properties of Cu-tmpa related to the catalytic reduction of H_2O_2 under different conditions.

	$E_{\text{onset, HPFR}}$	$E_{\text{cat}/2}$	i_{cat} (μA)
HNEt_3PF_6	-0.35	-0.59	$40^{[a]}$ 71
$\text{HNEt}_3\text{PF}_6/\text{NEt}_3$	-0.56	-0.60	$19^{[b]}$ 72
HOAc	-0.66	-0.88	77
HOAc/ OAcNBu_4	-0.68	-0.72	$18^{[a]}$ 25

[a] catalytic current measured at -0.80 V . [b] Catalytic current measured at -0.75 V . E_{onset} is defined as the potential where current i_{cat} is $1 \mu\text{A}$ higher than i_{p} under argon.

Table 4. Overview of the open-circuit potentials obtained in solutions containing HNEt_3^+ , HOAc, or their respective acid-conjugate base 1:1 mixture.

Conditions		E_{OCP} (V vs. Fc^+/Fc)	η_{OCP} (V)	η_{Nernst} (V)
HNEt_3PF_6 (50 mM)	No added water	-0.851		
	$[\text{H}_2\text{O}] = 0.10 \text{ M}$	-0.825		
1:1 $\text{HNEt}_3\text{PF}_6/\text{NEt}_3$ (both 50 mM)	No added water	-1.148	0.77	0.78
	$[\text{H}_2\text{O}] = 0.10 \text{ M}$	-1.132		
HOAc (20 mM)	No added water	-1.011		
	$[\text{H}_2\text{O}] = 0.10 \text{ M}$	-1.017		
1:1 HOAc/ NBu_4OAc (both 20 mM)	No added water	-1.207	0.80	0.59
	$[\text{H}_2\text{O}] = 0.10 \text{ M}$	-1.178		

potential by +29 mV in the case of the 1:1 HOAc/OAc[−] mixture. This also indicates that the in-situ generation of conjugate base during the electrocatalytic reaction will have a larger effect on local potential and pH than the generation of water during the same reaction.

To validate the experimental setup and the method that was used to determine the OCP, the values for the buffered HNEt₃⁺/NEt₃ system were compared to the OCP values of HNEt₃⁺ (used as a BF₄[−] salt) in MeCN as reported in the literature,^[14] which showed good agreement with the OCP value reported in Table 4. For HOAc/OAc⁺, a standard reduction potential of H⁺ (E_H⁰) of 0.159 V vs. Fc⁺/Fc was obtained, by applying the Nernst equation on the measured OCP potential (Eq. 1). This is almost 200 mV higher than the previously determined E_H⁰ in MeCN (0.028 V vs. Fc⁺/Fc).^[14]

$$E_{H^+}^0 = E_{OCP} + \frac{RT}{F} \ln(K_a)$$

Thus, two different methods were applied to determine the overpotential (η) of the ORR in the buffered electrolyte solutions, by using the OCP potential (Eq. 2), or by applying the Nernst equation (Eq. 3).

$$\eta = E_{OCP} - E_{cat/2} + (E_{O_2}^0 - E_{H^+}^0)$$

$$\eta = (E_{O_2}^0 - 0.0592pK_a) - E_{cat/2}$$

Here, $E_{cat/2}$ is the catalytic half-wave potential of the ORR by Cu-tmpa (Table 2), the standard reduction potential for the 4-electron reduction of O₂ in MeCN (E_{O₂}⁰ = 1.21 V vs. Fc⁺/Fc) was reported by Pegis *et al.*^[18] and the standard reduction potential of H⁺ in MeCN (E_H⁰ = −0.028 V vs. Fc⁺/Fc) was reported by Roberts *et al.*^[14] As shown in Table 4, good agreement is achieved between both methods for the HNEt₃⁺/NEt₃ system. However, a significant difference in results is obtained for HOAc/OAc⁺ as was expected based on the calculated E_H⁰. While this was not further investigated, it could indicate a concentration effect in combination with influence of HOAc/OAc⁺ homoconjugation on the OCP value.

Acid concentration and time-dependence studies

Under non-catalytic conditions, a double redox event was observed in CVs of Cu-tmpa in the presence of HOAc. Similar behavior was also observed for solutions containing HNEt₃PF₆ when an acid concentration below 50 mM was used. To investigate if the magnitude of the redox couples is dependent on the acid concentration in the electrolyte, CVs of electrolyte solutions containing 0.3 mM Cu-tmpa and acid in a range of concentrations between 5 and 100 mM were recorded, for both 1 atm Ar and O₂ (Figure 7). The main redox couple at −0.4 V shows a decreasing redox current with increasing acid concentration. At the same time, the second redox event becomes more pronounced yet also moves from −0.7 V to −0.6 V. The addition of the first 5 mM HOAc already results in a clear

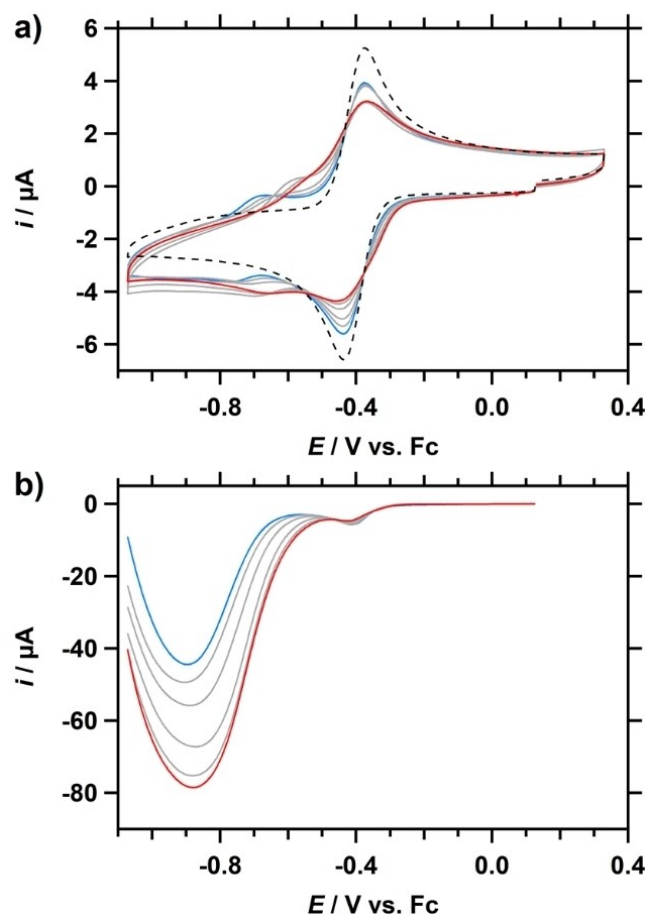


Figure 7. (a) CVs of Cu-tmpa (0.3 mM) in the presence of 1 atm Ar for different concentrations of HOAc, ranging from 5 mM (blue trace) to 100 mM (red trace), including a CV in the absence of acid (dashed trace). (b) Background-corrected LSVs of the ORR catalysed by Cu-tmpa over the same range of HOAc concentrations. Conditions: NBu₄PF₆ (100 mM) in MeCN, 100 mV s^{−1}, 293 K.

decrease of the oxidative and reductive current of the main redox couple and the appearance of the smaller second smaller redox couple mentioned before. Further increase of acid concentration does not seem to result in a linear decrease of the redox current. The effect of acid concentration is more pronounced for the ORR activity, as shown in Figure 7b. Here, the catalytic current increases linearly with the increased concentration (Figure S5). However, one has to consider that this may be merely an effect of the proton concentration on catalysis, and not specifically on the concentration of catalytic species that can be associated with the increasing current response from the second redox couple (see SI section S4).

The same approach was taken to study the effect of the concentration of HNEt₃PF₆ on the redox chemistry and the catalytic ORR activity of Cu-tmpa. The resulting CVs over a range of acid concentration between 5 and 100 mM are shown in Figure 8. While the previously mentioned redox couple at −0.61 V is present at acid concentrations higher than 20 mM, at lower concentrations the most prominent redox couple of Cu-tmpa has the same redox potential as that of the complex in

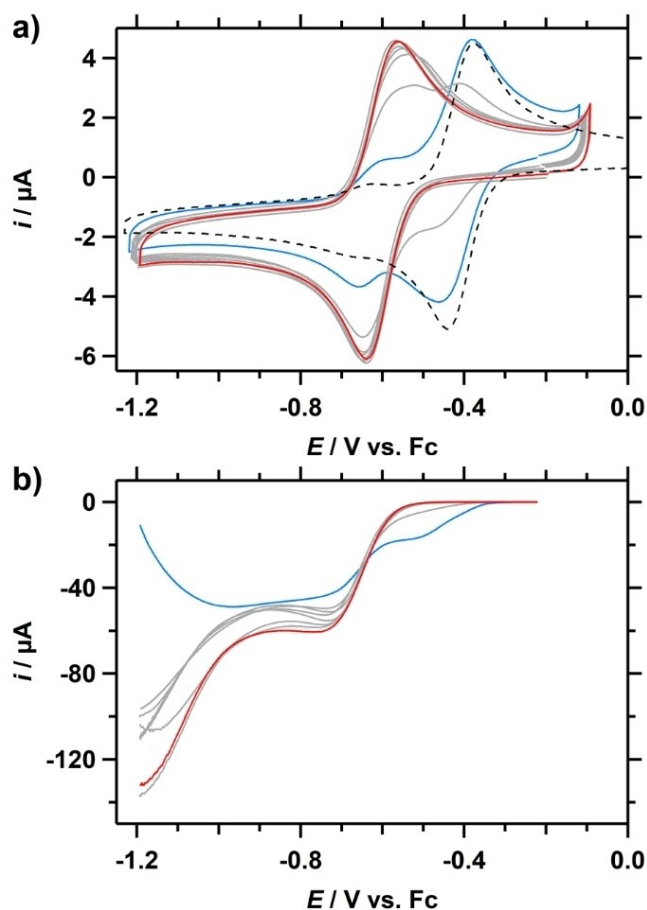


Figure 8. CVs of Cu-tmpa (0.3 mM) in the presence of 1 atm Ar for different concentrations of HNEt_3^+ , ranging from 10 mM (blue trace) to 100 mM (red trace), including a CV in the absence of acid (dashed trace). (b) Background-corrected LSV of the ORR by Cu-tmpa over the same range of HNEt_3^+ concentrations. Conditions: NBu_4PF_6 (100 mM) in MeCN, 100 mVs^{-1} , 293 K.

the absence of acid. However, several repeated CV measurements of Cu-tmpa in an electrolyte solution containing 50 mM HNEt_3PF_6 showed small fluctuations in the position and magnitude of the redox couple. This was initially thought to be caused by different water content in the solutions that were used in these experiments, but upon further investigation a time-based element was identified as a probable cause. To confirm this, every 5 minutes a CV was measured of an electrolyte solution containing 0.3 mM Cu-tmpa and 50 mM HNEt_3PF_6 under 1 atm of Ar. The resulting CVs are shown in Figure 9a. Over the course of 6 hours, a chemical conversion took place between two different redox-active compounds, which were previously observed in the concentration dependence results. A comparison of the first ($t=0.5 \text{ min}$) and last ($t=382 \text{ min}$) CVs with the CVs obtained without acid and with 100 mM HNEt_3PF_6 shows that almost full conversion took place of the species with the less negative redox potential into the species with the more negative redox potential (Figure 9b). However, an additional shoulder is still present on both the reduction and oxidation domain indicates an equilibrium between the two species. Further analysis of the data (SI section

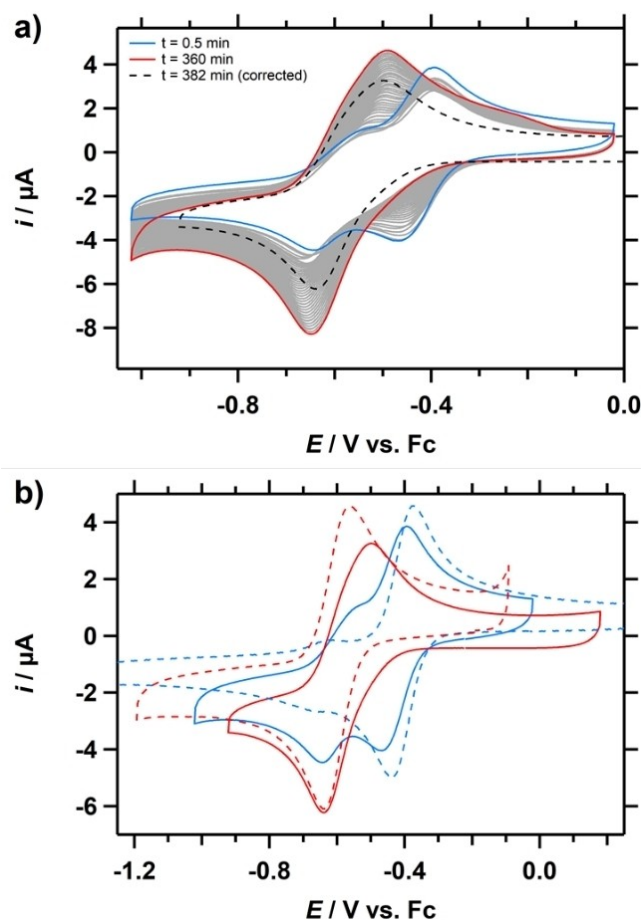


Figure 9. (a) CVs of Cu-tmpa (0.3 mM) in the presence of 50 mM HNEt_3PF_6 under 1 atm Ar, measured at 5 min time intervals after addition of the acid. (b) A comparison of CVs of 0.3 mM Cu-tmpa in the absence of acid (dashed blue trace), at $t=0.5 \text{ min}$ after addition of 50 mM HNEt_3^+ (blue trace), at $t=382 \text{ min}$ after addition of 50 mM HNEt_3^+ (red trace), and in a solution containing 100 mM HNEt_3^+ (dashed red trace). Conditions: NBu_4PF_6 (100 mM) in MeCN, 100 mVs^{-1} , 293 K.

S7) confirmed a species distribution ratio of 0.8 to 0.2. The combination of the HNEt_3^+ concentration dependence and the establishment of an equilibrium over time, indicates that protonation of the complex plays a role. By following the species distribution as a function of time, the reaction order of this chemical conversion was determined. A plot of the natural logarithm of the species concentration vs. time (Figure S9d) revealed that during the first 3 hours of the reaction it is governed by a first-order rate law. The resulting reaction rate was determined to be $8.27 \times 10^{-5} \text{ s}^{-1}$, with a half-life of 140 minutes.

In addition to the electrochemical measurements, a solution with the same composition was monitored separately using UV-vis spectroscopy. Upon addition of HNEt_3PF_6 (50 mM), the absorption band corresponding to the characteristic Cu^{II} d-d transition is blue-shifted by 25 nm (Figure S10). Over the course of 6 hours, a UV-vis spectrum was recorded every 5 minutes. However, the only change in the UV-vis spectrum over this period was a slight increase in the broad band around 300 nm,

as shown in the difference spectrum of the UV-vis absorbance spectra at the start and end of the experiment (Figure 10).

Catalyst concentration dependence

To get more insight into the catalytic mechanism for the ORR by Cu-tmpa in MeCN, the relationship between the catalytic current and the catalyst concentration was investigated in the presence of HOAc and HNET_3^+ . CVs were measured in the presence of 1 atm of O_2 over a range of Cu-tmpa concentrations (10–300 μM). After a background correction was applied to filter out the catalytic activity caused by the GC electrode itself, a linear first-order relationship between the catalytic current and the catalyst concentration was observed, both for HNET_3PF_6 and HOAc (Figure 11). The different acid concentrations, 50 mM HNET_3PF_6 and 100 mM HOAc, result in the same peak catalytic currents, indicating that the acid concentration does not have a significant current-limiting effect on the catalysis under these

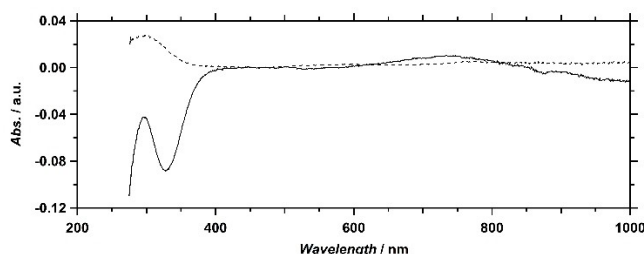


Figure 10. Difference spectrum after addition of HNET_3PF_6 (black trace) to the electrolyte solution containing 0.3 mM Cu-tmpa and 100 mM NBu_4PF_6 in MeCN, and between the start at $t=0$ min, and the end at $t=360$ min (dashed trace).

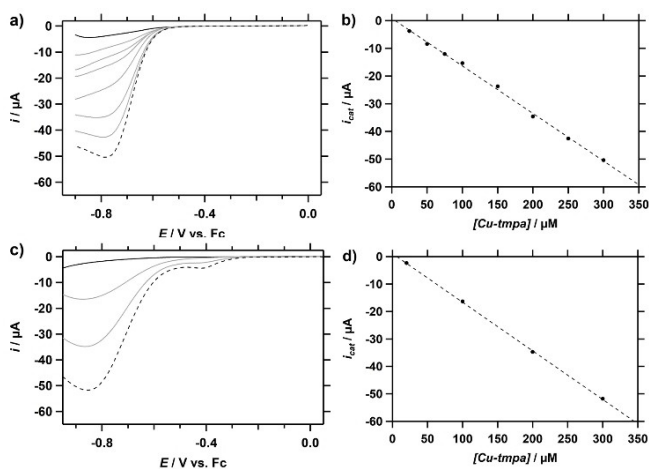


Figure 11. (a) Background-corrected LSVs of the catalytic ORR by Cu-tmpa in the presence of HNET_3PF_6 (50 mM) under 1 atm O_2 , for catalyst concentrations ranging from 25 (black) to 300 (dashed) μM . (b) Peak catalytic current i_{cat} at -0.78 V vs. Fc. (c) Background-corrected LSV of the catalytic ORR by Cu-tmpa in the presence of HOAc (100 mM) under 1 atm O_2 , for catalyst concentrations ranging from 20 to 300 μM . (d) Peak catalytic current i_{cat} at -0.85 V vs. Fc. Conditions: NBu_4PF_6 (100 mM) in MeCN, 100 mV s^{-1} , 293 K.

conditions. Additionally, it shows that the ORR is not limited in O_2 at a catalyst concentration of 0.3 mM, as good linearity of i_{cat} is maintained in this higher catalyst concentration range.

Quantification of catalyst performance

To compare the electrocatalytic performance of Cu-tmpa for ORR in MeCN under different conditions, the observed catalytic rate constant k_{obs} (or turnover frequency; TOF) was determined from the catalytic current enhancement by applying equation 4.^[19] The current enhancement was determined using the i_{cat} obtained over a range of catalyst concentrations (Figure 11), while i_p was calculated based on the diffusion coefficient of Cu-tmpa in the absence of any acid, using the Randles-Sevcik equation. Scan-rate dependence studies to obtain the diffusion coefficient in the presence of different acids and acid-conjugate base mixtures revealed that often two different redox couples were present (SI section S1), whose distribution are also both concentration and time-dependent. This prevented accurate determination of diffusion coefficients under these conditions. As this was not an issue in the absence of acid, the diffusion coefficient of Cu-tmpa in a MeCN solution without acid was used as an approximation to determine the i_p in the presence of acid. Applying Eq. 4.4 resulted in k_{obs} for the ORR by Cu-tmpa of $4.5 \pm 0.4 \text{ s}^{-1}$ and $5.0 \pm 0.3 \text{ s}^{-1}$ for solutions containing HNET_3PF_6 (50 mM) or HOAc (100 mM), respectively.

$$\frac{i_{\text{cat}}}{i_p} = 2.24n \sqrt{\frac{RT}{Fv}} k_{\text{obs}}$$

As described in above and as evidenced by the low k_{obs} , catalysis is not limited by O_2 concentration in the presence of 0.3 mM Cu-tmpa, which allows for the determination of the k_{obs} from any CV that was measured at this concentration and thus does not require a catalyst concentration dependence series. Thus, k_{obs} were determined for solutions containing either HNET_3^+ , $\text{HNET}_3^+/\text{NET}_3$, HOAc, or HOAc/OAc $^-$, using the same concentrations as were used for the determination of the E_{BH}^+ . This was done for both the ORR and HPORR catalysed by Cu-tmpa (0.3 mM). For this purpose, i_{cat} values were determined from background corrected LSVs (Figure S3). The resulting k_{obs} are shown in Table 5. For the $k_{\text{obs,ORR}}$ the catalytic electron transfer number used was 4, as under all four conditions both O_2 and H_2O_2 reduction take place at the potential where the k_{obs}

Table 5. Overview of k_{obs} obtained for the ORR and HPORR by Cu-tmpa under different catalytic conditions. Determined directly from CV measurements at 0.3 mM catalyst concentration.

Proton source	$k_{\text{obs,ORR}} \text{ (s}^{-1}\text{)}$	$k_{\text{obs,HPORR}} \text{ (s}^{-1}\text{)}$
HNET_3PF_6	4.6	35.9 ^[a] 11.3 ^[b]
$\text{HNET}_3\text{PF}_6/\text{NET}_3$	2.7	37.8 2.5 ^[c]
HOAc	5.6	42.9
HOAc/OAcNBu $_4$	1.5	4.5 2.2 ^[b]

[a] The maximum catalytic current was used as i_{cat} . [b] i_{cat} values were determined at -0.80 V vs. Fc. [c] i_{cat} values were determined at -0.75 V vs. Fc. For the ORR a catalytic electron transfer number of $n=4$ was used.

was determined (Figure S4, SI section S3). The $k_{\text{obs,ORR}}$ for HNET_3^+ and HOAc are in good agreement with the k_{obs} obtained at low catalyst concentration for these acids. For three of the four conditions, two different k_{obs} values are calculated for the HP RR, as multiple catalytic waves were observed in the CVs and LSVs. Under those conditions, two distinct catalytic waves were visible in the LSV, and the smallest k_{obs} value corresponds to the catalytic current of first, smaller reduction wave, while the larger value corresponds to the maximum catalytic current, which takes place at more negative potentials. Compared to the rate constants observed in aqueous solution, the rate constants obtained in MeCN are several orders of magnitude lower, particularly for the ORR. This is in line with the very low equilibrium constant of formation for $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$ that was observed in propionitrile (EtCN) previously.^[20]

Discussion

The redox behavior of Cu-tmpa in the absence of acids


The reaction of Cu^{I} -tmpa with O_2 in the non-protic solvents EtCN, THF, and acetone has been well-studied.^[5h,9c, 20] It has been shown that the initially formed Cu^{I} -tmpa complex reacts with O_2 to form an end-on Cu^{II} superoxide complex $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$. However, nitriles are strongly coordinating ligands for Cu^{I} .^[9c,21] In EtCN, the equilibrium constant of formation for $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$ at room temperature is only 0.38 M^{-1} due to competition of O_2 with EtCN as a ligand for the Cu^{I} -tmpa complex (Scheme 2).^[20] Additionally, the dimerization reaction of $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$ with $[\text{Cu}^{\text{I}}(\text{tmpa})(\text{EtCN})]^+$ to form $[\{\text{Cu}^{\text{II}}(\text{tmpa})\}_2(\mu\text{-O}_2)]^{2+}$ occurs more slowly than the formation of the initial monomeric superoxide species, with a formation rate constant of $6.7 \times 10^6 \text{ M}^{-1} \text{ s}^{-1}$ against $5.8 \times 10^7 \text{ M}^{-1} \text{ s}^{-1}$ for the latter, but has a much higher equilibrium constant of formation of $4.2 \times 10^3 \text{ M}^{-1}$, indicating better stability.

Unexpectedly, our electrochemical measurements of Cu-tmpa in MeCN in the presence of dioxygen show a significant degree of irreversibility (Figures 1b and 1c). This poor electrochemical reversibility is characterized by an increased ΔE_p , a lowered oxidative current, and an irreversible reduction at a potential below -0.8 V vs. Fc^+/Fc . The lower oxidative current of the $\text{Cu}^{\text{II/I}}$ redox couple is partially the result of the above

mentioned equilibrium constant of $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$, which is expected to be of a similar magnitude in MeCN. Due to the equilibrium between $[\text{Cu}^{\text{I}}(\text{tmpa})(\text{L})]^+$ and $[\text{Cu}^{\text{II}}(\text{O}_2^{\bullet-})(\text{tmpa})]^+$ part of the Cu^{I} is sequestered as the superoxido species upon reacting with O_2 , thus lowering the oxidation current of the $\text{Cu}^{\text{II/I}}$ redox couple. However, in the timeframe of the CV only a small or even negligible reduction in oxidative current should be expected due to the very fast rates associated with this equilibrium, which would pull the reaction out of equilibrium as the oxidation takes place. Additionally, formation of the dimeric peroxido species may explain the increase in ΔE_p , due to lower reversibility of the redox chemistry caused by sequential electrochemical and chemical reactions. This would also contribute to the reduced redox current over multiple scans (Figure 1c), as over time some of the dimer may accumulate near the electrode. A complicating factor is the presence of trace amounts of water, and thus protons, in MeCN. For the experiments shown in Figure 1, 0.5 mM of H_2O was detected using Karl-Fisher titration following drying of the solvent, which is close to a 1:2 ratio of catalyst to water. A proton-coupled electron transfer (PCET) step from the initially formed superoxido species would result in the formation of the hydroperoxide complex $[\text{Cu}^{\text{II}}(\text{OOH})(\text{tmpa})]^+$. This species could react further, resulting in the formation of H_2O , or even H_2O_2 following a simple protonation. Alternatively, the dimer, which has been shown to be able to catalyse the ORR in acetone using Fc as a reductant, can be further reduced to a $\text{Cu}^{\text{I}}\text{-OO-Cu}^{\text{II}}$ species. The irreversible reduction that is observed below -0.8 V can be the result of either of these proposed steps. While the magnitude of the reductive current is similar to that of the one-electron reduction of Cu^{I} -tmpa to Cu^{I} -tmpa, it cannot be excluded that this is actually a small catalytic wave resulting from the presence of trace amounts of water.

Redox behavior of Cu-tmpa in the presence of different acids

For several of the studied electrochemical conditions, multiple redox couples were observed during CV measurements of Cu-tmpa. Reproducibility of the redox couple of Cu-tmpa in acetonitrile in the presence of HNET_3^+ (50 mM) appeared to be poor, as in several experiments two redox couples with varying relative intensity were observed. Initially, it was assumed that perhaps variable water content in the electrolyte solution was the cause of the varying ratios of the two visible redox couples. However, the ultimate cause appeared to be a time-dependent chemical conversion that takes place in the electrolyte solution. Indeed, most experiments that were performed under these conditions show a different distribution of the two distinct redox couples, which seems to be an effect of the difference in time between preparation of the solution and the actual electrochemical measurement. The redox couple at the less negative potential overlaps to a large degree with the redox couple of Cu-tmpa in NBu_4PF_6 , which we assume can be assigned to $[\text{Cu}(\text{tmpa})(\text{CH}_3\text{CN})]^{2+}$. This is particularly clear at lower concentrations of HNET_3^+ concentrations (Figure 8a).

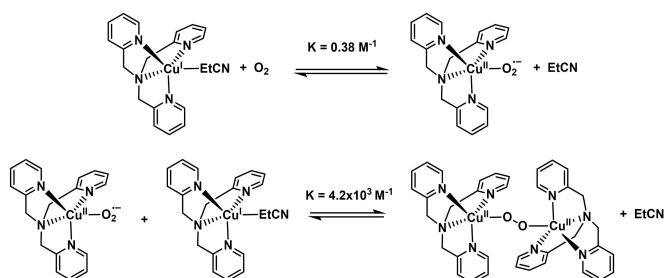

Scheme 2. Reaction scheme for the reaction of $[\text{Cu}^{\text{I}}(\text{tmpa})(\text{EtCN})]^+$ with O_2 , with equilibrium constant of formation as reported in the literature.^[9c,20]

We observed both a time-dependent conversion and a concentration-dependent effect, where higher initial HNET_3^+ concentrations resulted in an increased redox current of the species with the more negative $E_{1/2}$, which indicates that protonation of the ligand plays a role. This is also in line with the observed stability of the ratio between the two redox couples over time in the buffered electrolyte solution containing $\text{HNET}_3^+/\text{NET}_3$ in a 1:1 ratio, where no new equilibrium is established. Several considerations can be made on the nature of the redox-active species associated with the redox couple at more negative potentials. The possibility of coordination of the NET_3 conjugate base can largely be discounted as nitriles such as MeCN are much better ligands for Cu^{II} and Cu^{I} species. Protonation of one or multiple nitrogen atoms in the ligand could result in the dissociation of one of the N-donors. Dissociation of one of the pyridine arms of the ligand caused by the protonation of the pyridine seems unlikely, as NET_3 (conjugate acid $\text{pK}_a = 18.8$) is also a stronger base than pyridine (conjugate acid $\text{pK}_a = 12.5$) in MeCN.^[22] This would have resulted in an increase of the redox potential of the species, as opposed to the observed decrease, as observed for copper complexes containing the bis(2-pyridylmethyl)amine ligand.^[8b,23] Additionally, it has been shown the tertiary aliphatic amine in the free tmpa ligand is less basic than the pyridine N-atom, contrary to the generally expected higher basicity of tertiary aliphatic amines.^[24] While selective protonation of the tertiary amine of tmpa has been observed in a strained environment,^[25] it is not known whether the same would occur when coordinated to a copper ion. Most likely protonation would ultimately lead to reorganization of the κ^4 -tmpa ligand to a κ^3 -mer coordination mode, in which one of the pyridine ligands is protonated and non-coordinated, and allows for quite significantly shorter Cu–N bonds.^[23,26] This is accompanied by a change in geometry from a trigonal bipyramidal structure to a square pyramidal structure with a weakly coordinated second MeCN ligand at the apical position. For a wide range of copper complexes with multidentate ligands, it has been shown that the $\text{Cu}^{\text{II/I}}$ redox potential is mainly influenced by the stability of the Cu^{II} species, while the corresponding Cu^{I} species show near uniform stability.^[27] Despite the considerations above, it is not fully clear what the product of protonation of Cu-tmpa is. However, the slow kinetics in which the species is formed, together with the similar reactivity that was observed in acetate solutions wherein this species is not formed illustrate that the protonated species is not relevant for the catalytic reaction.

The $\text{Cu}^{\text{II/I}}$ redox couple of Cu-tmpa in the electrolyte solution containing HOAc is located at the same potential (-0.40 V) as in the acid-free electrolyte solution. This would indicate that no chemical conversion takes place upon addition of low (20 mM) amounts of acid and $[\text{Cu}(\text{tmpa})(\text{CH}_3\text{CN})]^{2+}$ is still the main species in solution. As the HOAc concentration is increased from 20 to 100 mM, the current of the redox couple decreases only slightly and a second smaller redox couple is observed at a more negative potential. However, HOAc is a weaker acid than HNET_3^+ (Table 1) and ligand protonation is therefore unlikely to play a role. As the CV of Cu-tmpa in the buffered acid-conjugate base HOAc/OAc[−] solution shows a single well-defined redox

couple at a more negative potential (-0.73 V), coordination of the anionic acetate is a more likely candidate for this observation. Acetate is a good ligand for copper and is not readily replaced by MeCN under standard conditions.^[28] Indeed, it has been previously shown that the addition of trifluoroacetic acid to $[\text{Cu}^{\text{II}}(\text{tmpa})]^{2+}$ in acetone resulted in the formation of $[\text{Cu}^{\text{II}}(\text{tmpa})(\text{CF}_3\text{COO}^-)]^+$, causing a -300 mV shift in the redox potential due to the increased electron density on the Cu centre.^[5b] Thus, the redox couple at -0.73 V is associated with the compound $[\text{Cu}^{\text{II}}(\text{OAc})(\text{tmpa})]^+$. In contrast, for unbuffered solutions containing HOAc, the concentration of available OAc[−] is not high enough to replace MeCN in the coordination sphere, which would explain why the intensity of the second redox event is low.

UV-vis measurements did not provide additional information, as no significant changes were observed in the UV-vis spectra, nor was any time-dependent conversion of the redox active species observed during UV-vis measurements. However, this does give us the insight that the addition of acids to the solution did not result in major changes in the coordination sphere that would affect Cu complex d–d transition.

Catalytic performance of Cu-tmpa for the ORR in MeCN

The electrocatalytic reduction of O_2 by Cu-tmpa in MeCN is significantly slower than in aqueous solution, despite oxygen having a six times higher solubility in MeCN than in water at 1 atm O_2 at room temperature.^[13a] The k_{obs} for ORR that were calculated based on the current enhancement in MeCN (1.5 – 5.6 s^{−1}) are a factor 10^5 lower than the TOF in a neutral aqueous solution (1.5×10^5 s^{−1}).^[5d,10] The overpotential (defined by $E_{\text{cat}/2}$) for the ORR with Cu-tmpa are lower in the buffered MeCN solutions (below 0.8 V) than in neutral aqueous solution (0.92 V), as shown in Table 4. For both HOAc and HNET_3^+ a linear relationship between the catalytic current and the Cu-tmpa concentration was observed, indicating a first-order catalytic reaction in catalyst, as was also observed in a neutral aqueous solution. Interestingly, a first-order dependence of the catalytic current on the acid concentration was found with HOAc in MeCN, while no direct relationship between the catalytic current and the HNET_3^+ concentration was found in MeCN (See SI section S4). These findings indicate that the rate-determining step of the catalytic reaction in the presence of HOAc does not only involve the catalyst, but also the acid (or H^+) species. For HNET_3^+ , the changing catalytic behavior can be directly linked to the concentration-induced change of the redox active species. Once this interconversion is fully completed, a further increase in acid concentration does not lead to an appreciable increase in catalytic current (Figure 8).

With these observations, the catalytic mechanism for the ORR in MeCN shows strong similarities to the mechanism observed in aqueous solution, as shown in Scheme 1, with some small modifications. As stated, the rate-determining step involves a single Cu centre, but also involves a protonation step, likely the H^+/e^- PCET step from $[\text{Cu}^{\text{II}}(\text{O}_2^{\cdot-})(\text{tmpa})]^+$ to $[\text{Cu}^{\text{II}}(\text{OOH})(\text{tmpa})]^+$. Despite the expected unfavorable thermo-

dynamic equilibrium for the binding of O_2 to $[Cu^I(MeCN)(tmpa)]^+$, the kinetic rate constant of formation (k_1) is very high ($5.8 \times 10^7 M^{-1} s^{-1}$ in EtCN).^[20] When a rapid equilibrium, like the reversible binding of O_2 to Cu^I , is followed by a slow step, the overall observed rate constant is a function of both the equilibrium constant and the rate constant of the subsequent slower reaction step, in accordance with the pre-equilibrium approximation.^[29] Thus, while the PCET step would be the rate-determining step, the binding of O_2 is still involved in the overall rate constant of the ORR catalysed by Cu-tmpa in MeCN.

Catalytic performance of Cu-tmpa towards the HPRR in MeCN

Like the reduction of O_2 , the reduction of H_2O_2 in MeCN ($k_{obs} = 2.2\text{--}43 s^{-1}$) is slower than in neutral aqueous solution ($k_{obs} = 4.8 \times 10^3 s^{-1}$),^[10] but only by a factor 100 to 1000. Additionally, in MeCN, the HPRR is generally faster than the ORR, whereas in water the opposite is the case. This behavior seems to point at $Cu^{II}\text{--}OOH$ being more readily formed from the reaction of $Cu^I\text{--}tmpa$ with H_2O_2 than with O_2 in MeCN, perhaps mediated by the presence of 30 mM of H_2O in the solution. Indeed, in the presence of a base and H_2O_2 $[Cu^{II}(OOH)(tmpa)]^+$ is spontaneously formed from $[Cu^{II}(tmpa)(L)]^{2+}$ (SI section S9).

A comparison of the maximum HPRR k_{obs} under different conditions shows similar values in solutions containing $HNEt_3^+$, $HNEt_3^+/NEt_3$, or $HOAc$ (Table 5). However, the k_{obs} (of the first and second catalytic wave) is at least one order of magnitude lower in the presence of the acid-conjugate base pair $HOAc/OAc^-$ than for the other conditions. This behavior validates the previously discussed formation of $[Cu^{II}(tmpa)(OAc)]^+$ when $HOAc/OAc^-$ is present in solution. Formation of this species results in a lowered catalytic activity for the HPRR caused by the stronger coordination of acetate compared to MeCN, in essence blocking the active site of the catalyst for H_2O_2 binding. While spontaneous formation of the $Cu^{II}\text{--}OOH$ species was detected under non-catalytic conditions in MeCN, the UV-vis absorbance around 400 nm associated with this species was almost three times lower in the presence of $HOAc/OAc^-$ versus $HNEt_3^+/NEt_3$. Furthermore, the absorption band at 400 nm was also only visible 22 hours after addition of H_2O_2 to the solution containing $HOAc/OAc^-$, as opposed to the immediate appearance of this band in with $HNEt_3^+/NEt_3$. This again shows that the formation of the $Cu^{II}\text{--}OOH$ species is slower for $[Cu^{II}(OAc)(tmpa)]^+$. However, the effect of the strong homoconjugation of acetic acid cannot be excluded in this discussion, as the lowered proton availability could also explain part of the lowered catalytic activity of Cu-tmpa towards HPRR in presence of $HOAc$. The second catalytic wave in the presence of $HOAc/OAc^-$, might be the result of H_2O acting as the proton source, which would require a higher driving force, and thus a higher overpotential.

Conclusion

The influence of different acids and acid-conjugate base mixtures on the electrocatalytic O_2 and H_2O_2 reduction by Cu-tmpa was investigated in acetonitrile. It was shown that the use of proton donors with a lower pK_a resulted in destabilisation of the Cu-tmpa compound. This was apparent from the lack of reversible redox couples in the presence of HTFA and $HDMF^+$, something which was also observed for Cu-tmpa at lower pH (<4) in aqueous electrolyte solution. In all cases, higher catalytic k_{obs} were observed for the ORR in the unbuffered electrolyte solutions containing only the acid species, which is expected based on the homoconjugation effect for the buffered electrolyte solutions. In contrast to the catalytic behavior of Cu-tmpa in neutral aqueous solutions, higher TOFs were observed for the HPRR than for the ORR in MeCN for all the different conditions that were investigated. This points to a more positive formation constant for the $LCu^{II}\text{--}OOH$ complex than for $LCu^{II}\text{--}OO^*$. As was observed under aqueous conditions, the catalytic rate showed a first-order dependence in catalyst concentration, confirming a mononuclear catalytic mechanism for Cu-tmpa under electrochemical conditions. Interestingly, the k_{obs} for the ORR shows a first-order dependence on the acid concentration in the electrolyte solution containing $HOAc$. These results confirm that the catalytic mechanism for ORR in MeCN is largely the same as in water, although the rate-determining step in MeCN is the PCET step from $[Cu^{II}(O_2^*)(tmpa)]^+$ to form $[Cu^{II}(OOH)(tmpa)]^+$.

Experimental Section

General: Tetrabutylammonium hexafluoridophosphate ($\geq 99.0\%$, for electrochemical analysis) tetrabutylammonium hydroxide (1.1 M in MeOH), ammonium hexafluoridophosphate, and acetic acid (99.99% trace metal basis) were obtained from Sigma-Aldrich. Triethylamine ($\geq 99.8\%$, for LC-MS) was obtained from VWR and ferrocene ($>98\%$) was obtained from Fluka. The copper complex $[Cu(tmpa)(MeCN)](OTf)_2$ was synthesized as described previously.^[5d] Acetonitrile (99.9%, HPLC grade, BioSolve) was further dried over activated molecular sieves for 4 days. Molecular sieves (3 Å, Sigma Aldrich) were first rinsed with acetonitrile to remove impurities and loose solid particles, and activated by drying at $140^\circ C$ in a vacuum oven at <10 mbar for 2 days.

Electrochemical measurements: Autolab PGSTAT 12, 204, and 128 N potentiostats in combination with Autolab NOVA 2 software were used for all measurements. Electrochemical measurements were performed in a custom-build 10 mL glass single-compartment cell with a three-electrode setup, or a single compartment cell based on single-use 20 mL glass vials, allowing for a four-electrode setup, in the same approach as reported by Roberts and Bullock.^[14]

The 10 mL single-compartment cell used during the electrochemical measurements was regularly cleaned to remove impurities by overnight submersion in an aqueous 0.5 M H_2SO_4 solution containing 1 mg/mL (6.3 mM) $KMnO_4$, followed by removal of excess $KMnO_4$ and MnO_2 from the glassware with diluted H_2SO_4 and H_2O_2 . Finally, the glassware was rinsed five times and subsequently boiled two times in Milli-Q water. Prior to each experiment all glassware was boiled once in Milli-Q water and oven-dried overnight at $120^\circ C$. A PEEK encapsulated glassy carbon ($A=0.0707 cm^2$, Met-

rohm) was used as the working electrode in a submerged setup. Before every experiment, the GC electrodes were manually polished for 5 mins each with 1.0, 0.3, and 0.05 μm alumina suspensions on Buehler cloth polishing pads, followed by sonication in MeCN for 10 minutes. A gold wire was used as the counter electrode and was flame annealed and rinsed with Milli-Q water before each experiment. A double-junction reference electrode (Methrohm) was used, either used as a 0.3 M Ag/AgCl reference, or as a Ag/AgNO₃ reference. For the Ag/AgNO₃ solution, the inner junction was filled with 10 mM AgNO₃ in MeCN, while the outer junction was filled with 100 mM NBu₄PF₆ in MeCN. The potential and stability of the Ag/AgNO₃ reference electrode was carefully monitored, and the solution was refreshed when necessary (SI section S6). All measurements were referenced to the Fc⁺/Fc redox couple.

All gasses used during electrochemical measurements, O₂ (5.0 grade), and argon (5.0 grade), were supplied by Linde. Oxygen-free electrolyte solutions were prepared by sparging the solution for 30 minutes with argon, after which a 1 atm argon atmosphere was maintained. Oxygen-saturated electrolyte solutions were obtained by sparging the cell for 20 minutes with O₂, after which a 1 atm O₂ atmosphere was maintained. All gases were pre-saturated with MeCN through a pre-bubbler before being passed through the electrochemical cell.

OCP measurements: A Pt wire was used for the determination of the open circuit potential (OCP). The Pt wire was flame-annealed and subsequently electropolished in a 0.1 M H₂SO₄ aqueous solution for 25 to 50 cycles at 500 mVs⁻¹ between -0.05 and 1.9 V vs. RHE before every experiment. For every different electrolyte mixture, a new 20 mL glass vial was used thoroughly rinsed with MeCN and dried in the oven. The hydrogen and argon gas were pre-saturated with solvent by bubbling through acetonitrile, which was dried over activated molecular sieves (3 Å). 5 mL of the desired MeCN electrolyte solution, containing both NBu₄PF₆ (100 mM) and the desired acid-conjugated base mixture, was added to the glass vial, followed by bubbling with a MeCN saturated flow of H₂ for 2–5 minutes. The OCP was measured by the Pt wire electrode over a period of 60 seconds, while vigorously bubbling the solution with H₂. This was repeated until a stable OCP value was found. Subsequently Fc was added to the solution, and under a H₂ flow over the solution, a CV was measured with a GC electrode to obtain the $E_{1/2}$ of Fc⁺/Fc.

Catalyst concentration dependence studies: For the determination of the catalytic current i_{cat} as a function of Cu-tmpa concentration, the GC electrode was polished with 0.05 μm alumina suspension for 5 minutes, rinsed with MilliQ and subsequently sonicated in MeCN for 10 minutes for every different catalyst concentration. Upon addition of aliquots of Cu-tmpa (10 mM in MeCN), the electrolyte solution was mixed thoroughly in both cell compartments and the solution was saturated with oxygen by bubbling the solution for 10 minutes with O₂ pre-saturated with MeCN. After the last measurement, Fc was added to the solution and the $E_{1/2}$ of Fc⁺/Fc was measured. Additionally, a blank CV was measured of the GC electrode in an oxygen-saturated electrolyte solution in the absence of Cu-tmpa. The catalytic currents from CV measurements obtained in the presence of Cu-tmpa were corrected using this blank measurement, giving the catalytic current without any contribution from the GC electrode.

Acid concentration dependence studies: For the determination of the catalytic current i_{cat} as a function of acid concentration, the GC electrode was polished with 0.05 μm alumina suspension for 5 minutes, rinsed with MilliQ and subsequently sonicated in MeCN for 10 minutes for each different catalyst concentration. Cu-tmpa (0.3 mM) and Fc were dissolved in the electrolyte solution (100 mM NBu₄PF₆) and transferred to the electrochemical cell. Of this

solution, 1 mL was used to dissolve the solid HNEt₃PF₆, kept under argon, which was transferred back into the electrochemical cell to reach the required acid concentration. The solution was thoroughly mixed and subsequently saturated with argon by bubbling for 10 minutes with 1 atm Ar pre-saturated with MeCN. A CV was measured to obtain the redox couple of Cu-tmpa, after which the solution was saturated with oxygen by bubbling for 10 minutes with O₂ pre-saturated with MeCN. After a CV was measured to obtain the catalytic current, a CV was measured in a potential window between 0.1 to 0.8 V vs. Ag/AgCl to obtain the $E_{1/2}$ of Fc. This process was repeated for all the different acid concentrations. The same methodology was followed to measure blank CVs of the GC electrode in the absence of Cu-tmpa.

Synthesis

Synthesis of triethylammonium hexafluoridophosphate (HNEt₃PF₆): NH₄PF₆ (6.52 g, 40 mmol) was suspended in toluene (40 mL), followed by the addition of triethylamine (5.58 mL, 40 mmol). The mixture was stirred and refluxed for 2 hours, after which the solution was allowed to cool down. The precipitate was filtered by vacuum filtration and washed with toluene (4 × 15 mL). After drying in air, the product was obtained as a white crystalline solid. The NMR is in good agreement with those reported in the literature.^[30] Yield: 99% (9.78 g, 39.6 mmol). ¹H NMR (400 MHz, DMSO-d₆) δ 3.37 (br), 3.09 (q, J = 7.3 Hz, 6H), 1.17 (t, J = 7.3 Hz, 9H).

Synthesis of tetrabutylammonium acetate: Tetrabutylammonium acetate was prepared in methanol (MeOH) as described in literature.^[31] Acetic acid (630 μL , 11 mmol) was dissolved in MeOH (10 mL). NBu₄OH in MeOH (7.9 mL, 11 mmol) was added. The reaction was stirred over night at room temperature. The solvents were evaporated at reduced pressure (65 °C) and the resulting product was liquid at high temperatures (65 °C). When cooled to room temperature the product crystallizes. The solid was washed twice with hexane (10 mL). Recrystallisation was done by dissolving the product in toluene (5 mL) and was crashed out by adding an excess amount of hexane. The hexane was removed by decantation and additional hexane was added twice leaving the product on the bottom of the round bottom flask. The product was dissolved in toluene (10 mL). The toluene was removed at reduced pressure. The product (quantitative yield) was further dried at low vacuum (< 1 mbar) overnight. ¹H NMR (300 MHz, Chloroform-d) δ 3.38–3.29 (m, 9H), 1.94 (s, 3H), 1.72–1.57 (m, 9H), 1.42 (h, J = 7.3 Hz, 9H), 0.99 (t, J = 7.3 Hz, 12H).

Synthesis of dimethylformamidium trifluoromethanesulfonate ([HDMF]OTf): Dimethylformamidium trifluoromethanesulfonate ([HDMF]OTf) was synthesized following the reported procedure. Dimethylformamide (DMF) (0.87 mL, 11.3 mmol) was added to dichloromethane (DCM) (30 mL) using a glass pipette. The mixture was stirred and triflic acid (HOTf) (1.0 mL, 11.3 mmol) was added dropwise to the mixture using a glass pipette. The mixture was stirred for 10 minutes for the reactants to react in a one-step protonation. After 10 minutes a clear solution was obtained and the solvents were evaporated: first DCM was removed (40 °C, 700 mbar). After DCM was evapo-

rated the temperature was increased and the pressure lowered (70 °C, 10 mbar). After 30 minutes about 1–2 mL of clear solution was left in the round-bottom flask. The solution crystallized into a white crystalline solid after cooling to room temperature at normal pressure. The crystalline solid was dried overnight at low vacuum, yielding a white crystalline solid (2.5 g, quantitative yield). The crystals were stored under inert atmosphere. ¹H NMR (400 MHz, Chloroform-d) δ 8.89 (br s, 1H), 8.49 (s, 1H), 3.32 (s, 3H), 3.16 (s, 3H).

Supporting Information

Additional references cited within the Supporting Information.^[32–35]

Acknowledgements

The authors thank Phebe van Langevelde for help with the catalyst deposition checks. This work has been financially supported by the European Research Council (ERC starting grant 637556 Cu4Energy to dr. D. G. H. Hetterscheid).

Conflict of Interests

The authors declare no conflict of interest.

Data Availability Statement

The data that support the findings of this study are available in the supplementary material of this article.

Keywords: copper • electrocatalysis • organic solvent • oxygen reduction • reaction mechanisms

- [1] a) H. A. Gasteiger, S. S. Kocha, B. Sompalli, F. T. Wagner, *Appl. Catal. B* **2005**, *56*, 9–35; b) O. Gröger, H. A. Gasteiger, J.-P. Suchsland, *J. Electrochem. Soc.* **2015**, *162*, A2605–A2622; c) A. Kongkanand, M. F. Mathias, *J. Phys. Chem. Lett.* **2016**, *7*, 1127–1137.
- [2] a) M. Wikström, K. Krab, V. Sharma, *Chem. Rev.* **2018**, *118*, 2469–2490; b) E. I. Solomon, U. M. Sundaram, T. E. Machonkin, *Chem. Rev.* **1996**, *96*, 2563–2605.
- [3] a) S. M. Jones, E. I. Solomon, *Cell. Mol. Life Sci.* **2015**, *72*, 869–883; b) E. I. Solomon, U. M. Sundaram, T. E. Machonkin, *Chem. Rev.* **1996**, *96*, 2563–2606; c) S. Yoshikawa, A. Shimada, *Chem. Rev.* **2015**, *115*, 1936–1989; d) D. den Boer, H. C. de Heer, F. Buda, D. G. H. Hetterscheid, *ChemCatChem* **2022**.
- [4] a) E. A. Lewis, W. B. Tolman, *Chem. Rev.* **2004**, *104*, 1047–1076; b) J. Serrano-Plana, I. García-Bosch, A. Company, M. Costas, *Acc. Chem. Res.* **2015**, *48*, 2397–2406; c) S. Hong, Y.-M. Lee, K. Ray, W. Nam, *Coord. Chem. Rev.* **2017**, *334*, 25–42; d) C. E. Elwell, N. L. Gagnon, B. D. Neisen, D. Dhar, A. D. Spaeth, G. M. Yee, W. B. Tolman, *Chem. Rev.* **2017**, *117*, 2059–2107; e) L. M. Mirica, X. Ottenwaelder, T. D. P. Stack, *Chem. Rev.* **2004**, *104*, 1013–1046; f) L. M. Mirica, X. Ottenwaelder, T. D. P. Stack, *Chem. Rev.* **2004**, *104*, 1013–1045; g) C. E. Elwell, N. L. Gagnon, B. D. Neisen, D. Dhar, A. D. Spaeth, G. M. Yee, W. B. Tolman, *Chem. Rev.* **2017**, *117*, 2059–2107; h) J. Serrano-Plana, I. García-Bosch, A. Company, M. Costas, *Acc. Chem. Res.* **2015**, *48*, 2397–2406.
- [5] a) C. J. Cramer, W. B. Tolman, *Acc. Chem. Res.* **2007**, *40*, 601–608; b) S. Kakuda, R. L. Peterson, K. Ohkubo, K. D. Karlin, S. Fukuzumi, *J. Am. Chem. Soc.* **2013**, *135*, 6513–6522; c) S. Itoh, *Acc. Chem. Res.* **2015**, *48*, 2066–2074; d) M. Langerman, D. G. H. Hetterscheid, *Angew. Chem. Int. Ed.* **2019**, *58*, 12974–12978; e) N. W. G. Smits, B. van Dijk, I. de Bruin, S. L. T. Groeneveld, M. A. Siegler, D. G. H. Hetterscheid, *Inorg. Chem.* **2020**, *59*, 16398–16409; f) H. Oh, S. Choi, J. Y. Kim, H. S. Ahn, S. Hong, *Chem. Commun.* **2019**, *55*, 12659–12662; g) P. Vasudevan, Santosh, N. Mann, S. Tyagi, *Transition Met. Chem.* **1990**, *15*, 81–90; h) S. Fukuzumi, H. Kotani, H. R. Lucas, K. Doi, T. Suenobu, R. L. Peterson, K. D. Karlin, *J. Am. Chem. Soc.* **2010**, *132*, 6874–6875; i) M. S. Thorum, J. Yadav, A. A. Gewirth, *Angew. Chem. Int. Ed.* **2009**, *48*, 165–167; j) M. S. Thorum, C. A. Anderson, J. J. Hatch, A. S. Campbell, N. M. Marshall, S. C. Zimmerman, Y. Lu, A. A. Gewirth, *J. Phys. Chem. Lett.* **2010**, *1*, 2251–2254; k) G. A. Goenaga, A. Belapure, C. Zhang, A. Papandrew, S. Foister, T. Zawodzinski, *ECS Trans.* **2011**, *41*, 1193–1205; l) M. Kato, N. Oyaizu, K. Shimazu, I. Yagi, *J. Phys. Chem. C* **2016**, *120*, 15814–15822; m) R. Venegas, K. Munoz-Becerra, L. Lemus, A. Toro-Labbe, J. H. Zagal, F. J. Recio, *J. Phys. Chem. C* **2019**, *123*, 19468–19478; n) J. Zhang, F. C. Anson, *Electrochim. Acta* **1993**, *38*, 2423–2429; o) C. C. L. McCrory, X. Ottenwaelder, T. D. P. Stack, C. E. D. Chidsey, *J. Phys. Chem. A* **2007**, *111*, 12641–12650; p) M. A. Thorseth, C. E. Tornow, E. C. M. Tse, A. A. Gewirth, *Coord. Chem. Rev.* **2013**, *257*, 130–139.
- [6] a) M. S. Thorum, J. Yadav, A. A. Gewirth, *Angew. Chem. Int. Ed.* **2009**, *48*, 165–167; b) M. A. Thorseth, C. S. Letko, T. B. Rauchfuss, A. A. Gewirth, *Inorg. Chem.* **2011**, *50*, 6158–6162; c) M. A. Thorseth, C. S. Letko, E. C. M. Tse, T. B. Rauchfuss, A. A. Gewirth, *Inorg. Chem.* **2013**, *52*, 628–634.
- [7] B. van Dijk, J. P. Hofmann, D. G. H. Hetterscheid, *Phys. Chem. Chem. Phys.* **2018**, *20*, 19625–19634.
- [8] a) K. D. Karlin, S. Kaderli, A. D. Zuberbühler, *Acc. Chem. Res.* **1997**, *30*, 139–147; b) M. Asahi, S.-i. Yamazaki, S. Itoh, T. Ioroi, *Dalton Trans.* **2014**, *43*, 10705–10709; c) M. Asahi, S.-i. Yamazaki, S. Itoh, T. Ioroi, *Electrochim. Acta* **2016**, *211*, 193–198; d) M. Langerman, D. G. H. Hetterscheid, *Angew. Chem. Int. Ed.* **2019**, *58*, 12974–12978.
- [9] a) K. D. Karlin, J. C. Hayes, S. Juen, J. P. Hutchinson, J. Zubieta, *Inorg. Chem.* **1982**, *21*, 4106–4108; b) A. Wada, Y. Honda, S. Yamaguchi, S. Nagatomo, T. Kitagawa, K. Jitsukawa, H. Masuda, *Inorg. Chem.* **2004**, *43*, 5725–5735; c) H. C. Fry, D. V. Scaltrito, K. D. Karlin, G. J. Meyer, *J. Am. Chem. Soc.* **2003**, *125*, 11866–11871; d) C. Costentin, J.-M. Savéant, *ChemElectroChem* **2014**, *1*, 1226–1236.
- [10] M. Langerman, D. G. H. Hetterscheid, *ChemElectroChem* **2021**, *8*, 2783–2791.
- [11] a) L. Tahsini, H. Kotani, Y. M. Lee, J. Cho, W. Nam, K. D. Karlin, S. Fukuzumi, *Chem. Eur. J.* **2012**, *18*, 1084–1093; b) S. Fukuzumi, L. Tahsini, Y.-M. Lee, K. Ohkubo, W. Nam, K. D. Karlin, *J. Am. Chem. Soc.* **2012**, *134*, 7025–7035; c) D. Das, Y.-M. Lee, K. Ohkubo, W. Nam, K. D. Karlin, S. Fukuzumi, *J. Am. Chem. Soc.* **2013**, *135*, 2825–2834.
- [12] N. Le Poul, B. n. d. Douziech, J. Zeitouny, G. G. Thiabaud, H. I. N. Colas, F. o. Conan, N. Cosquer, I. Jabin, C. Lagrost, P. Hapiot, O. Renaud, Y. Le Mest, *J. Am. Chem. Soc.* **2009**, *131*, 17800–17807.
- [13] a) M. L. Pegis, C. F. Wise, D. J. Martin, J. M. Mayer, *Chem. Rev.* **2018**, *118*, 2340–2391; b) M. König, J. Vaes, E. Klemm, D. Pant, *iScience* **2019**, *19*, 135–160; c) S. Garg, M. Li, A. Z. Weber, L. Ge, L. Li, V. Rudolph, G. Wang, T. E. Rufford, *J. Mater. Chem. A* **2020**, *8*, 1511–1544; d) L. Sun, V. Reddu, A. C. Fisher, X. Wang, *Energy Environ. Sci.* **2020**, *13*, 374–403.
- [14] J. A. S. Roberts, R. M. Bullock, *Inorg. Chem.* **2013**, *52*, 3823–3835.
- [15] M. L. Pegis, J. A. S. Roberts, D. J. Wasylenko, E. A. Mader, A. M. Appel, J. M. Mayer, *Inorg. Chem.* **2015**, *54*, 11883–11888.
- [16] a) I. M. Koltzoff, M. K. Chantooni, *J. Am. Chem. Soc.* **1963**, *85*, 426–430; b) J. F. Coetzee, G. R. Padmanabhan, *J. Am. Chem. Soc.* **1965**, *87*, 5005–5010; c) Z. Pawlak, G. Zundel, J. Fritsch, A. Wawrzynów, S. Kuna, M. Tusk, *Electrochim. Acta* **1984**, *29*, 391–395.
- [17] a) F. Eckert, I. Leito, I. Kaljurand, A. Kutt, A. Klamt, M. Diedenhofen, *J. Comput. Chem.* **2009**, *30*, 799–810; b) B. D. McCarthy, D. J. Martin, E. S. Rountree, A. C. Ullman, J. L. Dempsey, *Inorg. Chem.* **2014**, *53*, 8350–8361.
- [18] M. L. Pegis, B. A. McKeown, N. Kumar, K. Lang, D. J. Wasylenko, X. P. Zhang, S. Rauegi, J. M. Mayer, *ACS Cent. Sci.* **2016**, *2*, 850–856.
- [19] R. M. Bullock, A. M. Appel, M. L. Helm, *Chem. Commun.* **2014**, *50*, 3125–3143.
- [20] C. X. Zhang, S. Kaderli, M. Costas, E.-i. Kim, Y.-M. Neuhold, K. D. Karlin, A. D. Zuberbühler, *Inorg. Chem.* **2003**, *42*, 1807–1824.
- [21] F. H. Jardine, in *Advances in Inorganic Chemistry and Radiochemistry*, Vol. 17 (Eds.: H. J. Emeléus, A. G. Sharpe), Academic Press, **1975**, pp. 115–163.

- [22] S. Tshepelevitsh, A. Kütt, M. Lõkov, I. Kaljurand, J. Saame, A. Heering, P. G. Plieger, R. Vianello, I. Leito, *Eur. J. Org. Chem.* **2019**, 2019, 6735–6748.
- [23] A. Kunishita, J. D. Scanlon, H. Ishimaru, K. Honda, T. Ogura, M. Suzuki, C. J. Cramer, S. Itoh, *Inorg. Chem.* **2008**, 47, 8222–8232.
- [24] a) G. Anderegg, K. Popov, P. S. Pregosin, *Helv. Chim. Acta* **1986**, 69, 329–332; b) A. Hazell, J. McGinley, H. Toftlund, *J. Chem. Soc. Dalton Trans.* **1999**, 1271–1276; c) G. Anderegg, E. Hubmann, N. G. Podder, F. Wenk, *Helv. Chim. Acta* **1977**, 60, 123–140.
- [25] a) L. Zhiquan, H. Xie, S. E. Border, J. Gallucci, R. Z. Pavlović, J. D. Badjić, *J. Am. Chem. Soc.* **2018**, 140, 11091–11100; b) G. Qiu, C. Colombari, N. Vanthuyne, M. Giorgi, A. Martinez, *Chem. Commun.* **2019**, 55, 14158–14161.
- [26] B. S. Lim, R. H. Holm, *Inorg. Chem.* **1998**, 37, 4898–4908.
- [27] a) E. A. Ambundo, M.-V. Deydier, A. J. Grall, N. Agüera-Vega, L. T. Dressel, T. H. Cooper, M. J. Heeg, L. A. Ochrymowycz, D. B. Rorabacher, *Inorg. Chem.* **1999**, 38, 4233–4242; b) D. B. Rorabacher, *Chem. Rev.* **2004**, 104, 651–698.
- [28] a) M. Vaidyanathan, R. Viswanathan, M. Palaniandavar, T. Balasubramanian, P. Prabhakaran, P. Muthiah, *Inorg. Chem.* **1998**, 37, 6418–6427; b) H. Adams, N. A. Bailey, C. O. R. de Barbarin, D. E. Fenton, Q.-Y. He, *J. Chem. Soc. Dalton Trans.* **1995**, 2323–2331; c) S. Meghdadi, M. Amiras, A. Amiri, Z. Musavizadeh Mobarakeh, Z. Azarkamanzad, *C. R. Chim.* **2014**, 17, 477–483.
- [29] M. Rae, M. N. Berberan-Santos, *Chem. Phys.* **2002**, 280, 283–293.
- [30] B. M. Trost, R. C. Livingston, *J. Am. Chem. Soc.* **2008**, 130, 11970–11978.
- [31] a) S. E. Denmark, M. T. Burk, A. J. Hoover, *J. Am. Chem. Soc.* **2010**, 132, 1232–1233; b) P. Hamankiewicz, J. M. Granda, J. Jurczak, *Tetrahedron Lett.* **2013**, 54, 5608–5611; c) H. Nagae, R. Aoki, S.-n. Akutagawa, J. Kleemann, R. Tagawa, T. Schindler, G. Choi, T. P. Spaniol, H. Tsurugi, J. Okuda, K. Mashima, *Angew. Chem. Int. Ed.* **2018**, 57, 2492–2496.
- [32] a) M. Yamada, K. D. Karlin, S. Fukuzumi, *Chem. Sci.* **2016**, 7, 2856–2863; b) J. Wang, M. P. Schopfer, S. C. Pui, A. A. N. Sarjeant, K. D. Karlin, *Inorg. Chem.* **2010**, 49, 1404–1419.
- [33] a) A. Wada, M. Harata, K. Hasegawa, K. Jitsukawa, H. Masuda, M. Mukai, T. Kitagawa, H. Einaga, *Angew. Chem. Int. Ed.* **1998**, 37, 798–799; b) T. Fujii, A. Naito, S. Yamaguchi, A. Wada, Y. Funahashi, K. Jitsukawa, S. Nagatomo, T. Kitagawa, H. Masuda, *Chem. Commun.* **2003**, 2700–2701; c) S. Yamaguchi, H. Masuda, *Sci. Technol. Adv. Mater.* **2005**, 6, 34–47; d) S. Kim, J. W. Ginsbach, J. Y. Lee, R. L. Peterson, J. J. Liu, M. A. Siegler, A. A. Sarjeant, E. I. Solomon, K. D. Karlin, *J. Am. Chem. Soc.* **2015**, 137, 2867–2874; e) A. Kunishita, J. D. Scanlon, H. Ishimaru, K. Honda, T. Ogura, M. Suzuki, C. J. Cramer, S. Itoh, *Inorg. Chem.* **2008**, 47, 8222–8232.
- [34] Y. Syuhei, W. Akira, N. Shigenori, K. Teizo, J. Koichiro, M. Hideki, *Chem. Lett.* **2004**, 33, 1556–1557.
- [35] E. P. Crowell, W. A. Powell, C. J. Varsel, *Anal. Chem.* **1963**, 35, 184–189.

Manuscript received: April 14, 2023
Revised manuscript received: May 26, 2023
Accepted manuscript online: June 6, 2023