



Universiteit
Leiden
The Netherlands

Operando methods for the elucidation of electrolyte effects in electrocatalysis

Kolmeijer, K.E.; Mom, R.V.

Citation

Kolmeijer, K. E., & Mom, R. V. (2025). Operando methods for the elucidation of electrolyte effects in electrocatalysis. *Current Opinion In Electrochemistry*, 51.
doi:10.1016/j.coelec.2025.101700

Version: Publisher's Version

License: [Creative Commons CC BY 4.0 license](#)

Downloaded from: <https://hdl.handle.net/1887/4262431>

Note: To cite this publication please use the final published version (if applicable).

Review Article

Operando methods for the elucidation of electrolyte effects in electrocatalysis

Kees E. Kolmeijer and Rik V. Mom



The electrolyte pH, ion composition, and solvent are important design parameters in electrocatalytic systems, which directly impact the system's catalytic activity, selectivity and stability. However, the relationship between the electrolyte composition and electrocatalytic performance is complex, and at present difficult to predict. To elucidate the underlying principles that govern electrolyte effects in electrocatalysis, *operando* techniques capable of resolving the active site structures at the electrode–electrolyte interface play a crucial role. Here, we review the current capabilities of these *operando* techniques and analyze how they can be used to find the rules of the game for electrolyte engineering.

Addresses

Leiden Institute of Chemistry, Leiden University, Einsteinweg 55, 2333 CC, Leiden, the Netherlands

Corresponding author: Mom, Rik V. (r.v.mom@lic.leidenuniv.nl)

Current Opinion in Electrochemistry 2025, 51:101700

This review comes from a themed issue on **Electrocatalysis (2025)**

Edited by **Angel Cuesta** and **Tharangattu N. Narayanan**

For complete overview about the section, refer [Electrocatalysis \(2025\)](#)

Available online 17 April 2025

<https://doi.org/10.1016/j.coelec.2025.101700>

2451-9103/© 2025 The Author(s). Published by Elsevier B.V. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

Introduction


In electrocatalytic processes such as water electrolysis, chlorine production, or the conversion of CO₂ to useful chemicals, the catalytic turnover almost invariably occurs at the electrode–electrolyte interface. From this, it follows that the interfacial electrolyte is an integral part of the active sites, which can be used to modulate the activity, stability, and selectivity of electrocatalytic systems. Indeed, it has been found that the choice of ions [1–8], pH(9–12), and solvent [13–15] in the electrolyte has a significant impact on the catalytic performance of a wide variety of reactions, including the oxygen evolution reaction [2,3,11,16], oxygen reduction reaction [6,8], hydrogen evolution reaction [4,7,12], nitrate reduction reaction [5], methanol oxidation reaction [6], and CO₂ reduction reaction [1,13,15,17].

While this makes it clear that electrolyte engineering is a useful tool to optimize electrochemical reactions, the electrolyte effects on performance show a complex dependence on the electrolyte composition and electrode structure. For example, the effect of cations on the hydrogen evolution reaction (HER) can be inhibiting or promoting, depending on the pH of the electrolyte [10]. Similarly, the optimal choice of cations depends on the choice of electrode material, showing a performance trend of Cs⁺>K⁺>Na⁺>Li⁺ for Pt electrodes, but Li⁺>Na⁺>K⁺>Cs⁺ for Au electrodes [17]. This interrelation between practical design parameters creates a complex parameter space, making electrolyte optimization a trial-and-error process. To create simple, generally applicable design rules to navigate the parameter space in electrolyte engineering, it is therefore important to understand the underlying molecular-level mechanisms that cause electrolyte effects in electrocatalysis.

The main challenge in identifying these mechanisms is that the structure of the interfacial electrolyte strongly deviates from that of the bulk electrolyte, due to the electrostatic and chemical interactions of the interfacial electrolyte species with the electrode surface [18]. These interactions generally result in the attraction of either cations or anions towards the surface, forming an electric double layer (Figure. 1). Meanwhile, also the solvent restructures at the interface in order to optimally solvate both the interfacial ions and the electrode surface [18,19]. Lastly, the interfacial electrolyte structure has an interplay with the electrode surface structure [20,21]. At present, no model can fully capture this ion–solvent–surface restructuring. Therefore, a key challenge is to analyze how the choice of bulk electrolyte composition translates into changes in the active site structure during electrocatalytic reactions, and in turn how tuning this active site structure affects the catalytic performance.

To address this challenge, *operando* techniques capable of resolving (parts of) the electrode–electrolyte interface structure under operating conditions play an essential role. Using *operando* spectro-electrochemistry, structural details such as the interfacial hydrogen bonding network [19,22], interfacial electric field [23], and ion-adsorbate coordination [24,25] have been identified as critical parameters, which can be indirectly

Figure. 1

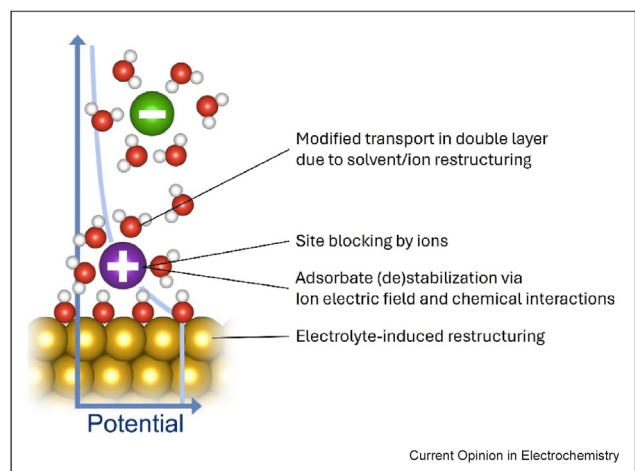

Interfacial electrolyte structure and its potential effects on electrocatalytic performance.

tuned via the bulk electrolyte composition. These structural features can influence the catalytic performance in several ways, as summarized in Figure. 1. Here, we summarize the current capabilities of *operando* techniques in resolving the nature of electrolyte effects. We will focus on vibrational spectroscopy, X-ray spectroscopy, and surface X-ray diffraction, which have been used under true *operando* conditions, i.e. while electrocatalytic turnover is taking place at the interface. However, we note that *in situ* techniques, which only probe the double layer under static, non-catalytic conditions, such as laser-induced current transient (LICT) [3,9] and scanning probe microscopy (AFM/STM) [26–28] have also delivered valuable insight to the topic.

Vibrational spectroscopy

The vast majority of spectro-electrochemical studies on electrolyte effects have been carried out using vibrational spectroscopies. Indeed, vibrational techniques are comparatively easy to use and can be applied to a variety of electrochemical systems. To create interface sensitivity in the measurements, the vibrational signal is locally enhanced at the electrode surface using plasmonic hotspots, facilitating the detection of surface and near-surface species [29–34]. Ag, Cu, or Au electrodes with nanometer-scale roughness have suitable plasmonic properties for this purpose and are therefore widely used in surface-enhanced Raman spectroscopy (SERS) and surface-enhanced infrared spectroscopy (SEIRAS) [30,34–36]. For non-plasmonic electrodes, core-shell nanoparticles with tailored plasmonic properties can be utilised as implemented in shell-isolated nanoparticle-enhanced Raman spectroscopy (SHINERS) [33,37–39]. An alternative approach is


infrared reflection absorption spectroscopy (IRRAS) using polarised light at grazing incidence. By subtractive normalisation of spectra obtained with s- and p-polarised light, a highly interface-sensitive interferogram is obtained [40–43]. Lastly, high interface sensitivity can also be achieved by non-linear spectroscopic techniques with symmetry-breaking selection rules, such as second or third harmonic generation, sum/difference frequency generation and 2D IR spectroscopy [44–49].

These interface-sensitive techniques make it possible to track reaction intermediates, electrolyte species and interfacial water-based features (Figure. 2). Changes in the intensity and position of ion or adsorbate peaks as a function of potential provide a rough indication of the surface concentration and local electric field strength (Figure. 2a) [41,47,50,51]. Meanwhile, tracking the intensity of adsorbate peaks can be used to probe the (de)stabilising effect of interfacial ions on reaction intermediates [10,32,39,52–54]. For example, a time-resolved CO₂RR SERS study by Lee et al. showed the requirement of cations to capture a CO_(ads) reaction intermediate (Figure. 2b) [54]. Another essential aspect that vibrational spectroscopy techniques can resolve is the effect of ions on the local water structure, often determined through the deconvolution of water-based features [12,33,53,55]. In an *operando* SHINERS study on a Pd single crystal, Wang et al. showed the increased contribution of water coordinated to cations at the electrode–electrolyte interface when approaching hydrogen evolution potentials, which facilitate hydrogen evolution by their closer proximity to the electrode [33]. This cation-induced water restructuring is affected by the identity of the cation. Huang et al. showed that smaller cations with large hydration shells create a rigid local water structure as opposed to larger cations that allow for more free water close to the electrode's surface (Figure. 2c) [12]. As revealed in recent studies, these subtle differences can majorly impact surface-reactions that require hydrogenation steps [12,32,53].

As discussed above, vibrational spectroscopy is highly capable of resolving structural trends to explain electrolyte effects in electrocatalysis. Its dominance in *operando* electrolyte effect studies originates from its comparatively simple instrumentation, which is compatible with almost any electrolyte and electrocatalytic process. Another advantage of vibrational spectroscopy is the time resolution. In optimised configurations, spectral acquisition times can reach sub-second to sub-picosecond intervals, which is excellent for resolving complex reaction mechanisms and determining the presence and role of adsorbates with short lifetimes and their interactions with electrolyte species [30,34,48,49,56,57].

However, vibrational spectroscopy techniques also have limitations. For example, substrates with the

Figure. 2

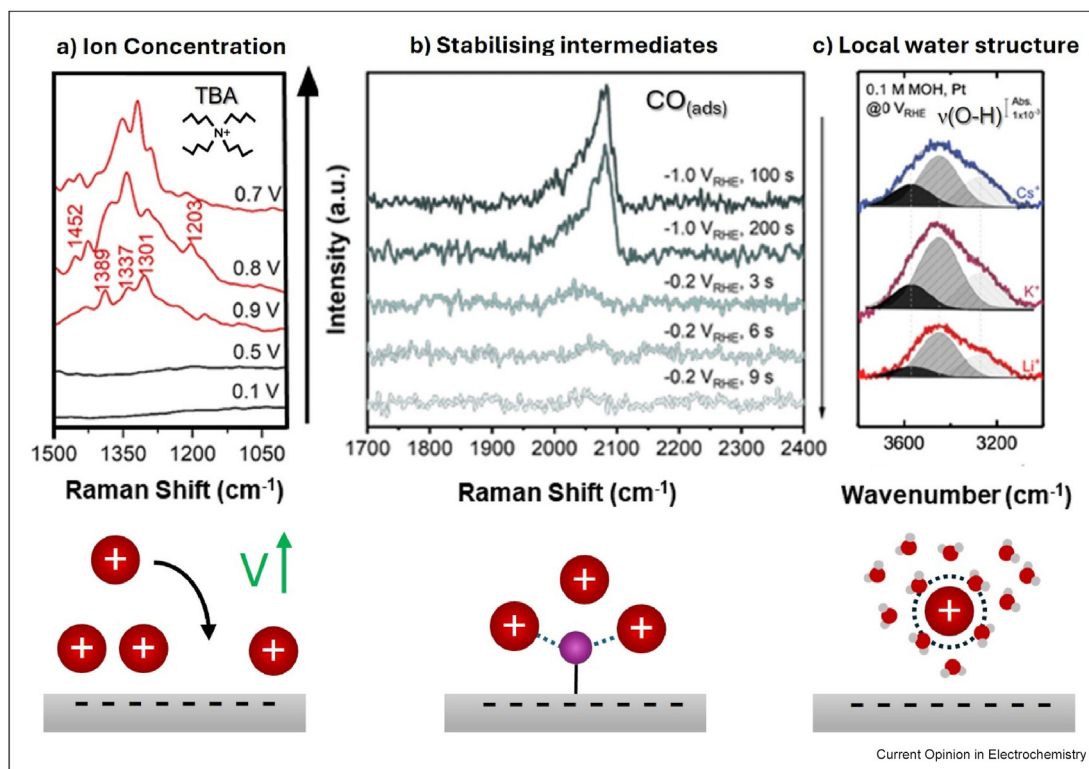

a) Potential dependent *in situ* SHINERS spectra of Pt(111) in TBAOH pH 12 electrolyte (figure adapted from Ref. [51]. **b)** Time resolved *operando* CO₂RR SERS spectrum after changing the potential from -1.0 V to 0.2 V vs RHE in CO₂ saturated 0.1 M KHCO₃ electrolyte. Figure adapted from Ref. [54]. **c)** Deconvoluted OH stretching peak at 0 V vs RHE into three components: Ion coordinated water (3570 cm^{-1}), weakly hydrogen-bonded water (3450 cm^{-1}) and free water (3270 cm^{-1}) from *in-situ* SEIRAS spectra on Pt. Figure adapted from Ref. [12].


appropriate plasmonic properties are usually limited to gold, silver and copper. To achieve sufficient enhancement, the surface of these metals must consist of nanostructures with specific sizes ($50\text{--}100\text{ nm}$) [58,59], preventing the use of smaller nanoparticles or flat surfaces such as single crystals. While the SHINERS strategy provides an attractive approach for using a wider range of substrates, synthesising intact thin-shelled particles is challenging. Improperly isolated particles can give an unwanted contribution to the electrochemical process of interest. In addition, the created plasmonic hotspots that dominate the recorded signal might not represent the whole electrode surface. Another limitation for electrolyte studies is that the direct measurement of cations is limited to complex ion structures, as traditionally used alkali cations don't have any vibrational mode that can be excited.

X-ray spectroscopy

While X-ray spectroscopies are widely used in electrochemistry to track changes in the oxidation state and ligand environment in electrodes [60], their application to electrolyte effects has only recently begun [11,20,25,61–63]. The main attractive feature of this

branch of techniques is their element-sensitivity, which makes it possible to separately inspect the interfacial chemistry of ions [20,25,61,64,65], water molecules [20,66–68], and the electrode surface [11,60,62,69–71] based on the different elements they contain. This is exemplified using a recent study from van der Heijden et al. [20], in which the promoting effect of small amounts of Li⁺ in NaOH for the oxygen evolution reaction on NiFeO_x was investigated. Using Na K-edge, O K-edge, and Ni L-edge X-ray absorption spectroscopy, the authors were able to simultaneously track the Na⁺ ions, interfacial water molecules, and Ni catalyst atoms (Figure. 3). In this way, they were able to show that the addition of Li⁺ induces better electrolyte penetration into the layered NiFeO_x structure, as evidenced by the increased Na⁺ and H₂O signals (Figure. 3a and b). This improves the mass transport of reactants within the catalyst layer, and makes more Ni sites available for catalysis, as evidenced by the increased fraction of Ni in the active $3+/4+$ state observed in the Ni L-edge (Figure. 3c). The study thus shows the capability of X-ray spectroscopy to unravel the interplay between different electrode–electrolyte interface components. On a more detailed level, X-ray absorption spectroscopy can also be

Figure. 3

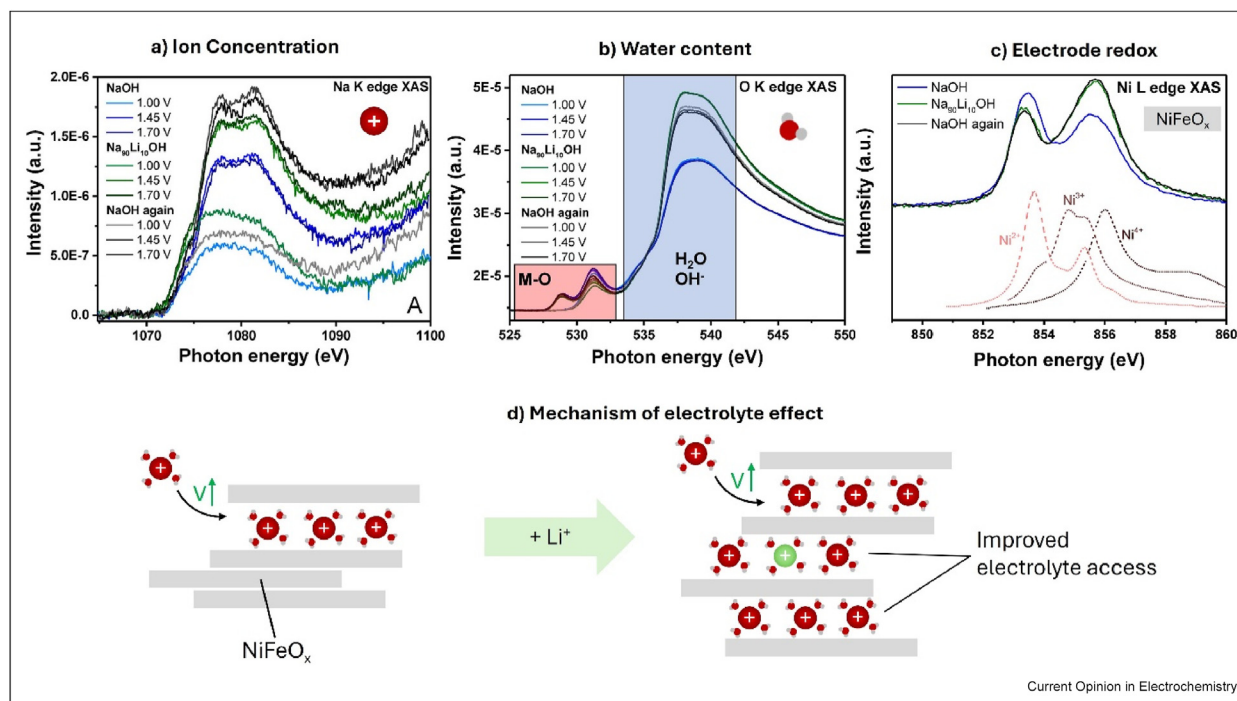

Operando soft X-ray absorption spectroscopy showing the interplay between ions, water, and electrode during the oxygen evolution reaction on NiFeO_x at pH 13. **a)** Na K-edge spectra showing potential dependent Na⁺ intercalation, which increases upon Li⁺ addition. **b)** O K-edge spectra showing increased water uptake into the catalyst film upon Li⁺ addition. **c)** Ni L-edge spectra showing an increased fraction of Ni in the active Ni^{3+/4+} state upon Li⁺ addition. a-c adapted from Ref. [20]. **d)** Overall effect of Li⁺ addition inferred from X-ray spectroscopy and activity measurements.

used to resolve interfacial water structures [66,68], the hydration shell structure of ions [25,72,73], and the ion protonation state (e.g. HSO₄⁻ vs SO₄²⁻) [74,75].

Complementary to X-ray absorption spectroscopy, a recent development in the field is *operando* X-ray photoelectron spectroscopy (XPS) [64,76,77]. *Operando* XPS offers the possibility to see not only the concentration and chemical state of all components of the electrode–electrolyte interface, but also the potential they experience [64,67,69,78]. Favaro et al. showed that this can be used to extract the potential profile of the double layer [67]. In the context of electrocatalysis, Hübner et al. recently used *operando* XPS to resolve the role of K⁺ ions in the 2- electron oxygen reduction reaction on carbon electrodes [61].


Compared to the more widely used vibrational spectroscopies, X-ray spectroscopy offers a few pros and cons. On the upside, X-ray spectroscopies are in principle compatible with all electrode materials and electrolytes. It also has the capability to resolve all components of the electrode–electrolyte interface in one experiment, including mono-atomic ions (e.g. Na⁺) that are invisible to vibrational spectroscopy. The downsides of *operando* X-ray spectroscopy are its risk of beam-damage (most

pronounced for systems containing organics) and its technical complexity. In general, interface-sensitive X-ray spectroscopy experiments require specialized setups that make use of grazing incidence X-rays [71] or vacuum-based spectroscopic techniques [64] with an advanced spectro-electrochemical cell design. While these methodologies are becoming increasingly mature and user-friendly, for the moment *operando* X-ray spectroscopy studies on electrolyte effects require some level of specialism.

Surface X-ray diffraction

Using surface X-ray diffraction, it is possible to derive the atomic positions of water molecules and ions at the interface between single crystals and electrolytes [21,24,40,79–83]. The technique is primarily sensitive to the position of (heavy) ions, but can also resolve the distance between the electrode and the first water layer [40,80,82]. In situations where the interfacial ions form an ordered structure, also the in-plane positions of the ions can be obtained [80,82]. In the context of electrolyte effects, this information can be very useful to judge how interfacial ions influence electrocatalytic reactions. For example, Strmnik et al. [24] used the measured ion-electrode distance to determine whether the hydration shell of the interfacial ions opens up, so

Figure. 4

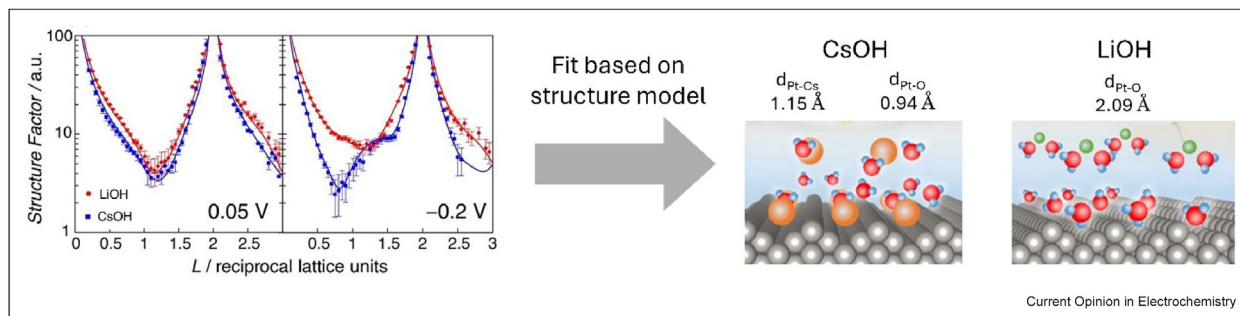

Operando surface X-ray diffraction on Pt(110) during the hydrogen evolution reaction at pH 13. Specular crystal truncation rod data is shown on the left, while the right side shows the structural parameters extracted using curve fitting. Data and ball model adapted from Ref. [80].

that the ions can directly interact with the reaction intermediates on the surface, modulating their reactivity. In a similar way, the formation of an ordered Cs^+ overlayer with a short distance to the Pt(110) substrate was identified by Tanaka et al. as a barrier for water transport/dissociation during the hydrogen evolution reaction in CsOH(80) (Figure. 4). Surface X-ray diffraction also provides insight into how ions affect the electrode surface structure. For example, Kumeda et al. [21] found that Li^+ ions reduce the surface roughening that develops during the surface oxidation of Au(111).

The structural information in these examples is extracted by fitting crystal truncation rod curves using a structural model. From this, three challenges arise: 1) Recording crystal truncation rod curves with a sufficient signal-to-noise ratio is time consuming, meaning that only a few electrolytes can be tested per synchrotron beam time. 2) A model for the interfacial electrolyte must be built and systematically varied to find the optimal fit. While software exists to aid with this (e.g. ROD [84]), the procedure requires expertise. 3) Light atoms such as the oxygen from water have a relatively small influence on the fitting curve due to their low X-ray scattering probability. Therefore, determining their position is comparatively difficult, putting further demands on the quality of the data and analysis. Due to these experimental and analytical challenges involved in surface X-ray diffraction studies on interfacial electrolytes, only a few groups have published on this topic so far. However, given the promise of the technique, several groups are currently picking up the gauntlet.

From structure to mechanism

A critical step in the analysis of electrolyte effects using *operando* techniques is to understand the link between the structure that is measured and the observed catalytic performance. The most widespread methodology adopted for this is to create structure–performance

correlations, i.e. to link differences in the *operando* interface structure in different electrolytes to differences in catalytic performance. For example, the much more ordered, ion-rich structure observed in CsOH in Figure. 4 compared to LiOH was linked to the lower catalytic activity in the hydrogen evolution reaction [80]. However, the interpretation of such correlations can be challenging, because a structural change can affect catalysis in many ways. For example, if more cations are attracted to the surface, this influences the transport of reactants through the double layer, the interfacial electric field (activation energy), and in some cases also ion-adsorbate interactions (activation energy). To distinguish these effects, an attractive method is to also consider *how* the activity is affected by the structure change. In the case study in Figure. 3, the onset potential in NaOH and NaOH + LiOH was the same and differences only appeared at higher overpotential, clearly indicating that the cation effect was related to transport [20]. In contrast, the necessity of a cation-containing electrolyte to attain any conversion during CO_2 reduction implies an effect on the activation energy [54,85].

An alternative methodology to solidify the analysis is to combine *operando* measurements with theory. Through simulated spectra, energetics, and atomic structures, calculations aid in both the assignment of spectral features and in the identification of the mechanisms through which the identified structures influence the catalysis. Both aspects are very well exemplified by a recent study from Li et al. [19]. By calculating the vibrational density of states of water at the Pt(111)-electrolyte interface, they were able to assign the water vibration peaks in their SEIRAS spectra. Meanwhile, the atomic structures identified in the same calculations provided a rationalization for the relationship between the spectroscopically observed H-bonding and the activity through the identification of an H-bond gap that limits proton transport to the electrode during the hydrogen evolution reaction.

Outlook

Over the past years, the combination of *operando* spectroscopy, systematic experiments and theory has revealed many key mechanisms through which the interfacial electrolyte influences electrocatalysis. An important next step will be to understand under what conditions which mechanism dominates, or if multiple mechanisms occur simultaneously [86]. The latter is a particularly pressing question for complex reactions such as CO₂ reduction, because the many adsorbates and electrolyte species involved lead to interrelated effects. *Operando* spectroscopy can play a key role in untangling these, but an increased focus on resolving the chemistry of *all* components of the electrode–electrolyte interface is necessary. For example, in the CO₂ reduction reaction, tracking of the adsorbates, electrode surface structure, interfacial pH, cation positions/concentration and water structure is key, as it is now clear that each of these components plays a role in the activity and selectivity, but not how the components work together to create the activity/selectivity effects. Collaborative efforts to combine multiple spectroscopy, diffraction, and microscopy techniques may prove to be essential to achieve this.

From a more practical point of view, the next frontier for the field will be to move from explaining electrolyte effects after the fact, towards (roughly) predicting electrolyte effects given a combination of electrode, electrolyte and reaction. This requires a more generalized understanding of 1) how the bulk electrolyte composition relates to the electrolyte structure formed at the interface and 2) how the interfacial electrolyte structure affects the electrocatalysis. With the increasingly large volume of case studies available in the literature, the field is now moving closer to attaining such a more general view.

Declaration of competing interest

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: Rik Mom reports financial support was provided by Dutch Research Council. If there are other authors, they declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

RVM acknowledges the Dutch Research Council (NWO) for funding under grant number ECCM.TT.001.

Data availability

No data was used for the research described in the article.

References

Papers of particular interest, published within the period of review, have been highlighted as:

* of special interest

** of outstanding interest

1. Gao D, Mccrum IT, Deo S, Choi Y, Scholten F, Wan W, *et al.*: **Activity and selectivity control in CO₂ electroreduction to multicarbon products over CuO_x catalysts via electrolyte design.** *ACS Catal* 2018, **8**:10012–10020.
2. Yang C, Fontaine O, Tarascon JM, Grimaud A: **Chemical recognition of active oxygen species on the surface of oxygen evolution reaction electrocatalysts.** *Angew Chem Int Ed* 2017, **56**:8652–8656.
3. Hou S, Xu L, Ding X, Kluge RM, Sarpey TK, Haid RW, *et al.*: **Dual in situ laser techniques underpin the role of cations in impacting electrocatalysts.** *Angew Chem Int Ed* 2022, **61**, e202201610.
4. Xue S, Garlyyev B, Watzele S, Liang Y, Fichtner J, Pohl MD, *et al.*: **Influence of alkali metal cations on the hydrogen evolution reaction activity of Pt, Ir, Au, and Ag electrodes in alkaline electrolytes.** *Chemelectrochem* 2018, **5**:2326–2329.
5. Katsounaros I, Kyriacou G: **Influence of the concentration and the nature of the supporting electrolyte on the electrochemical reduction of nitrate on tin cathode.** *Electrochim Acta* 2007, **52**:6412–6420.
6. Strmcnik D, Kodama K, Van Der Vliet D, Greeley J, Stamenkovic VR, Marković NM: **The role of non-covalent interactions in electrocatalytic fuel-cell reactions on platinum.** *Nat Chem* 2009, **1**:466–472.
7. Bender JT, Petersen AS, Østergaard FC, Wood MA, Heffernan SMJ, Milliron DJ, *et al.*: **Understanding cation effects on the hydrogen evolution reaction.** *ACS Energy Lett* 2023, **8**: 657–665.
8. Suntivich J, Perry EE, Gasteiger HA, Shao-Horn Y: **The influence of the cation on the oxygen reduction and evolution activities of oxide surfaces in alkaline electrolyte.** *Electrocatal* 2013, **4**: 49–55.
9. Ding X, Scieszka D, Watzele S, Xue S, Garlyyev B, Haid RW, *et al.*: **A systematic study of the influence of electrolyte ions on the electrode activity.** *Chemelectrochem* 2022, **9**, e202101088.
10. Goyal A, Koper MTM: **The interrelated effect of cations and electrolyte pH on the hydrogen evolution reaction on gold electrodes in alkaline media.** *Angew Chem Int Ed* 2021, **60**: 13452–13462.
11. Liang C, Katayama Y, Tao Y, Morinaga A, Moss B, Ryan M, *et al.*: **Role of electrolyte pH on water oxidation for iridium oxides.** *J Am Chem Soc* 2024, **146**:8928–8938.
12. Huang B, Rao RR, You S, Hpone Myint K, Song Y, Wang Y, *et al.*: **Cation- and pH-dependent hydrogen evolution and oxidation reaction kinetics.** *JACS Au* 2021, **1**:1674–1687.
13. Mohandas N, Narayanan TN, Cuesta A: **Tailoring the interfacial water structure by electrolyte engineering for selective electrocatalytic reduction of carbon dioxide.** *ACS Catal* 2023, **13**: 8384–8393.
14. Rosen BA, Salehi-khojin A, Thorson MR, Zhu W, Whipple DT, Kenis PJA, *et al.*: **Ionic liquid – mediated selective conversion of CO₂ to CO at low overpotentials.** *Science* 2011, **334**: 643–645.
15. Golru SS, May AS, Biddinger EJ: **Modifying copper local environment with electrolyte additives to alter CO₂ electroreduction vs hydrogen evolution.** *ACS Catal* 2023, **13**: 7831–7843.
16. del Rosario JAD, Li G, Francis M, Labata M, Ocon JD, Chuang YA: **Unravelling the roles of alkali-metal cations for the enhanced oxygen evolution reaction in alkaline media.**

- Appl Catal B Environ* 2021, **288**, 119981, <https://doi.org/10.1016/j.apcatb.2021.119981>. Available from:.
17. Ringe S, Clark EL, Resasco J, Walton A, Seger B, Bell AT, *et al.*: **Understanding cation effects in electrochemical CO₂ reduction.** *Energy Environ Sci* 2019, **12**:3001–3014.
 18. Li P, Jiao Y, Huang J, Chen S: **Electric double layer effects in electrocatalysis : insights from Ab initio simulation and hierarchical continuum modeling.** *JACS Au* 2023, **3**:2640–2659.
 19. Li P, Jiang Y, Hu Y, Men Y, Liu Y, Cai W, *et al.*: **Hydrogen bond network connectivity in the electric double layer dominates the kinetic pH effect in hydrogen electrocatalysis on Pt.** *Nat Catal* 2022, **5**:900–911.
- Shows how the interplay between theory and SEIRAS can be used to create a detailed reconstruction of interfacial water structures.
20. van der Heijden O, Eggebeen JJJ, Trziesniowski H, Deka N, Golnak R, Xiao J, *et al.*: **Li⁺ cations activate NiFeOOH for oxygen evolution in sodium and potassium hydroxide.** *Angew Chem Int Ed* 2024, 202318692.
- Resolves the interplay between water, ions, and electrode using operando X-ray spectroscopy
21. Kumeda T, Kondo K, Tanaka S, Sakata O, Hoshi N, Nakamura M: **Surface extraction process during initial oxidation of Pt(111): effect of hydrophilic/hydrophobic cations in alkaline media.** *J Am Chem Soc* 2024, **146**:10312–10320.
 22. Shen L fan, Lu B an, yang Li Y, Liu J, Huang-fu Z chao, Peng H, *et al.*: **Interfacial structure of water as a new descriptor of the hydrogen evolution reaction.** *Angew Chem Int Ed* 2020, **59**: 22397–22402.
 23. Gunathunge CM, Ovalle VJ, Waeghele MM: **Probing promoting effects of alkali cations on the reduction of CO at the aqueous electrolyte/copper interface.** *Phys Chem Chem Phys* 2017, **19**: 30166–30172.
 24. Strmcnik D, Van Der Vliet D, Chang K-C, Komanicky V, Kodama K, You H, *et al.*: **Effects of Li⁺, K⁺, and Ba²⁺ cations on the ORR at model and high surface area Pt and Au surfaces in alkaline solutions.** *J Phys Chem Lett* 2011, **2**:2733–2736.
 25. Ji SG, Kim MM, Han MH, Cho J, Son Y, Kim YY, *et al.*: **Alkali metal cations act as homogeneous cocatalysts for the oxygen reduction reaction in aqueous electrolytes.** *Nat Catal* 2024, **7**:1330–1338, <https://doi.org/10.1038/s41929-024-01241-1>. Available from:.
- Uncovers cation stabilization of a reaction intermediate in the interfacial electrolyte as a new type of electrolyte effect using X-ray spectroscopy and SEIRAS.
26. Wang Y, Dan X, Wang X, Yi Z, Fu J, Feng Y, *et al.*: **Probing the synergistic effects of Mg²⁺ on CO₂ reduction reaction on CoPc by in situ electrochemical scanning tunneling microscopy.** *J Am Chem Soc* 2022, **144**:20126–20133.
 27. Wang Y, Fu J, Feng Y, Zhao K, Wang L, Cai J, *et al.*: **Alkali metal cations induce structural evolution on Au(111) during cathodic polarization.** *J Am Chem Soc* 2024, **146**:27713–27724.
 28. Uhlig MR, Martin-jimenez D, Garcia R: **Atomic-scale mapping of hydrophobic layers on graphene and few-layer MoS₂ and WSe₂ in water.** *Nat Commun* 2019, **10**:2606.
 29. Pérez-Martínez L, de los Toyos LMM, Shibuya JTT, Cuesta A: **Methanol dehydrogenation on Pt electrodes: active sites and role of adsorbed spectators revealed through time-resolved ATR-SEIRAS.** *ACS Catal* 2021, **11**:13483–13495.
 30. An H, Wu L, Mandemaker LDB, Yang S, de Ruiter J, Wijten JHJ, *et al.*: **Sub-second time-resolved surface-enhanced Raman spectroscopy reveals dynamic CO intermediates during electrochemical CO₂ reduction on copper.** *Angew Chem Int Ed* 2021, **60**:16576–16584.
 31. Ru EC Le, Blackie E, Meyer M, Etchegoint PG: **Surface enhanced Raman scattering enhancement factors: a comprehensive study.** *J Phys Chem C* 2007, **111**:13794–13803.
 32. Zhang ZM, Wang T, Cai YC, Li XY, Ye JY, Zhou Y, *et al.*: **Probing electrolyte effects on cation-enhanced CO₂ reduction on copper in acidic media.** *Nat Catal* 2024, **7**:807–817.
- Shows the correlation between intermediates, cation stabilization and local water structure on CO₂ electrolysis.
33. Wang YH, Zheng S, Yang WM, Zhou RY, He QF, Radjenovic P, *et al.*: **In situ Raman spectroscopy reveals the structure and dissociation of interfacial water.** *Nature* 2021, **600**:81–85.
- Shows the migration of ions to the electrode surface and their effect on the local water structure on water electrolysis.
34. An H, de Ruiter J, Wu L, Yang S, Meirer F, van der Stam W, *et al.*: **Spatiotemporal mapping of local heterogeneities during electrochemical carbon dioxide reduction.** *JACS Au* 2023, **3**: 1890–1901. Available from: <https://pubs.acs.org/doi/full/10.1021/jacsau.3c00129>.
 35. Lima RNS, Souza-Garcia J, Angelucci CA: **Electrochemical surface-enhanced Raman spectroscopy (EC-SERS) study of C3 polyalcohols oxidation catalyzed by a Ag roughened electrode with low platinum content.** *J Phys Chem C* 2023, **127**:16374–16384. Available from: <https://pubs.acs.org/doi/full/10.1021/acs.jpcc.3c03039>.
 36. Wang W, Huang YF, Liu DY, Wang FF, Tian ZQ, Zhan D: **Electrochemically roughened gold microelectrode for surface-enhanced Raman spectroscopy.** *J Electroanal Chem* 2016, **779**:126–130.
 37. Raciti D, Cockayne E, Vinson J, Schwarz K, Walker ARH, Moffat TP: **SHINERS study of chloride order-disorder phase transition and solvation of Cu(100).** *J Am Chem Soc* 2024, **146**: 1588–1602. Available from: <https://pubs.acs.org/doi/full/10.1021/jacs.3c11812>.
 38. Rizo R, Fernández-Vidal J, Hardwick LJ, Attard GA, Vidal-Iglesias FJ, Climent V, *et al.*: **Investigating the presence of adsorbed species on Pt steps at low potentials.** *Nat Commun* 2022, **13**:1–7. Available from: <https://www.nature.com/articles/s41467-022-30241-7>.
 39. Shao F, Xia Z, You F, Wong JK, Low QH, Xiao H, *et al.*: **Surface water as an initial proton source for the electrochemical CO reduction reaction on copper surfaces.** *Angew Chem* 2023, **135**, e202214210. Available from: <https://onlinelibrary.wiley.com/doi/full/10.1002/ange.202214210>.
 40. Kumeda T, Tajiri H, Sakata O, Hoshi N, Nakamura M: **Effect of hydrophobic cations on the oxygen reduction reaction on single-crystal platinum electrodes.** *Nat Commun* 2018, **9**: 4378, <https://doi.org/10.1038/s41467-018-06917-4>. Available from:.
 41. Kumeda T, Kubo R, Hoshi N, Nakamura M: **Activation of oxygen reduction reaction on well-defined Pt electrocatalysts in alkaline media containing hydrophobic organic cations.** *ACS Appl Energy Mater* 2019, **2**:3904–3909.
- Shows the relationship between organic cations and oxygen reduction reaction intermediates.
42. K NA, Alzate-Carvajal N, Nallayagari AR, Monyoncho EA, Zulevi B, Serov A, *et al.*: **In-situ polarization modulation IRRAS investigation of ammonia electrooxidation on Pt-Ir and Pt-Ru nanoparticles prepared on engineered catalyst supports.** *Electrochim Acta* 2024, **507**, 145046.
 43. Su ZF, Quintal J, Al-Jeda M, Thiruppathi AR, Lipkowski J, Chen A: **Electrochemical reduction of graphene oxide on the gold surface: localized electrochemical impedance and in situ polarization modulation infrared reflection absorption spectroscopic studies.** *J Phys Chem C* 2023, **127**:21644–21655. Available from: <https://pubs.acs.org/doi/full/10.1021/acs.jpcc.3c05839>.
 44. Xu P, Wang R, Zhang H, Camevale V, Borguet E, Suntivich J: **Cation modifies interfacial water structures on platinum during alkaline hydrogen electrocatalysis.** *J Am Chem Soc* 2024, **146**:2426–2434.
 45. Rebstock JA, Zhu Q, Baker LR: **Exploring the influence of interfacial solvation on electrochemical CO₂ reduction using plasmon-enhanced vibrational sum frequency generation spectroscopy.** *ChemCatChem* 2024, **16**, e202301301.
 46. Ge A, Rudshteyn B, Videla PE, Miller CJ, Kubiak CP, Batista VS, *et al.*: **Heterogenized molecular catalysts: vibrational sum-frequency spectroscopic, electrochemical, and theoretical investigations.** *Acc Chem Res* 2019, **52**:1289–1300.
 47. Patrow JG, Sorenson SA, Dawlaty JM: **Direct spectroscopic measurement of interfacial electric fields near an electrode**

- under polarizing or current-carrying conditions. *J Phys Chem C* 2017, **121**:11585–11592.
48. Lotti D, Hamm P, Kraack JP: **Surface-sensitive spectro-electrochemistry using ultrafast 2D ATR IR spectroscopy.** *J Phys Chem C* 2016, **120**:2883–2892.
 49. Yang N, Ryan MJ, Son M, Mavrić A, Zanni MT: **Voltage-dependent FTIR and 2D infrared spectroscopies within the electric double layer using a plasmonic and conductive electrode.** *J Phys Chem B* 2023, **127**:2083–2091.
 50. Ovalle VJ, Hsu YS, Agrawal N, Janik MJ, Waegle MM: **Correlating hydration free energy and specific adsorption of alkali metal cations during CO₂ electroreduction on Au.** *Nat Catal* 2022, **5**:624–632. Available from: <https://www.nature.com/articles/s41929-022-00816-0>.
 51. Fernández-Vidal J, Koper MTM: **Effect of a physisorbed tetra-butylammonium cation film on alkaline hydrogen evolution reaction on Pt single-crystal electrodes.** *ACS Catal* 2024, **14**: 8130–8137.
 52. Liu H, Liu J, Yang B: **Promotional role of a cation intermediate complex in C₂Formation from electrochemical reduction of CO₂ over Cu.** *ACS Catal* 2021, **11**:12336–12343. Available from: <https://pubs.acs.org/doi/full/10.1021/acscatal.1c01072>.
 53. Rao RR, Huang B, Katayama Y, Hwang J, Kawaguchi T, Lunger JR, *et al.*: **PH-And cation-dependent water oxidation on rutile RuO₂(110).** *J Phys Chem C* 2021, **125**:8195–8207. Available from: <https://pubs.acs.org/doi/full/10.1021/acs.jpcc.1c00413>.
 54. Lee SY, Kim J, Bak G, Lee E, Kim D, Yoo S, *et al.*: **Probing cation effects on *CO intermediates from electroreduction of CO₂ through operando Raman spectroscopy.** *J Am Chem Soc* 2023, **145**:23068–23075.
- Shows the stabilizing relationship between cations and surface adsorbed CO intermediate.
55. Tong Y, Lapointe F, Thämer M, Wolf M, Campen RK: **Hydrophobic water probed experimentally at the gold electrode/ aqueous interface.** *Angew Chem Int Ed* 2017, **56**:4211–4214. Available from: <https://onlinelibrary.wiley.com/doi/full/10.1002/anie.201612183>.
 56. Pérez-Martínez L, de los Toyos LMM, Shibuya JJT, Cuesta A: **Methanol dehydrogenation on Pt electrodes: active sites and role of adsorbed spectators revealed through time-resolved ATR-SEIRAS.** *ACS Catal* 2021, **11**:13483–13495. Available from: <https://pubs.acs.org/doi/abs/10.1021/acscatal.1c03870>.
 57. Cuesta A: **ATR-SEIRAS for time-resolved studies of electrode–electrolyte interfaces.** *Curr Opin Electrochem* 2022, **35**. Elsevier B.V.
 58. Le F, Brandl DW, Urzhumov YA, Wang H, Kundu J, Halas NJ, *et al.*: **Metallic nanoparticle arrays: a common substrate for both surface-enhanced Raman scattering and surface-enhanced infrared absorption.** *ACS Nano* 2008, **2**:707–718. Available from: <https://pubs.acs.org/doi/full/10.1021/nr800047e>.
 59. Mueller NS, Pfitzner E, Okamura Y, Gordeev G, Kusch P, Lange H, *et al.*: **Surface-enhanced Raman scattering and surface-enhanced infrared absorption by plasmon polaritons in three-dimensional nanoparticle supercrystals.** *ACS Nano* 2021, **15**:5523–5533. Available from: <https://pubs.acs.org/doi/full/10.1021/acsnano.1c00352>.
 60. Timoshenko J, Roldan Cuenya B: **In situ/operando electrocatalyst characterization by X-ray absorption spectroscopy.** *Chem Rev* 2021, **121**:882–961.
 61. Hübner JL, Lucchetti LEB, Nong HN, Sharapa DI, Paul B, Kroschel M, *et al.*: **Cation effects on the acidic oxygen reduction reaction at carbon surfaces.** *ACS Energy Lett* 2024, **9**: 1331–1338.
 62. Görlin M, Stenlid JH, Koroidov S, Wang H, Börner M, Shipilin M, *et al.*: **Key activity descriptors of nickel-iron oxygen evolution electrocatalysts in the presence of alkali metal cations.** *Nat Commun* 2020, **11**:6181. <https://doi.org/10.1038/s41467-020-19729-2>. Available from:.
 63. Ostervold L, Smerigan A, Liu MJ, Filardi LR, Vila FD, Perez-aguilar JE, *et al.*: **Cation incorporation into copper oxide lattice at highly oxidizing potentials.** *ACS Appl Mater Interfaces* 2023, **15**:47025–47036.
 64. Velasco-Velez J-J, Falling LJ, Bernsmeier D, Sear MJ, Clark PCJ, Chan T-S, *et al.*: **A comparative study of electrochemical cells for in situ x-ray spectroscopies in the soft and tender x-ray range.** *J Phys D Appl Phys* 2021, **54**, 124003.
 65. Trzesniowski H, Deka N, van der Heijden O, Golnak R, Xiao J, Koper MTM, *et al.*: **Reversible and irreversible cation intercalation in NiFeOx oxygen evolution catalysts in alkaline media.** *J Phys Chem Lett* 2023, **14**:545–551.
 66. Velasco-Velez JJ, Wu CH, Pascal TA, Wan LF, Guo J, Prendergast D, *et al.*: **The structure of interfacial water on gold electrodes studied by x-ray absorption spectroscopy.** *Science* 2014, **346**:831–834.
 67. Favaro M, Jeong B, Ross PN, Yano J, Hussain Z, Liu Z, *et al.*: **Unravelling the electrochemical double layer by direct probing of the solid/liquid interface.** *Nat Commun* 2016, **7**:1–8.
 68. Wu CH, Pascal TA, Baskin A, Wang H, Fang HT, Liu YS, *et al.*: **Molecular-scale structure of electrode-electrolyte interfaces: the case of platinum in aqueous sulfuric acid.** *J Am Chem Soc* 2018, **140**:16237–16244.
 69. Mom R, Frevel L, Velasco-Velez JJ, Plodinec M, Knop-gericke A, Schlögl R: **The oxidation of platinum under wet conditions observed by electrochemical X - ray photoelectron spectroscopy.** *J Am Chem Soc* 2019, **141**:6537–6544.
 70. Favaro M, Drisdell WS, Marcus MA, Gregoire JM, Crumlin EJ, Haber JA, *et al.*: **An operando investigation of (Ni-Fe-Co-Ce)Ox system as highly efficient electrocatalyst for oxygen evolution reaction.** *ACS Catal* 2017, **7**:1248–1258.
 71. Friebe D, Viswanathan V, Miller DJ, Anniyev T, Ogasawara H, Larsen AH, *et al.*: **Balance of nanostructure and bimetallic interactions in Pt model fuel cell catalysts: in situ XAS and DFT study.** *J Am Chem Soc* 2012, **134**:9664–9671.
 72. Aziz EF, Zimina A, Freiwald M, Eisebitt S, Eberhardt W: **Molecular and electronic structure in NaCl electrolytes of varying concentration: identification of spectral fingerprints.** *J Chem Phys* 2006, **124**, 114502.
 73. Ohkubo T, Konishi T, Hattori Y, Kanoh H, Fujikawa T, Kaneko K: **Restricted hydration structures of Rb and Br ions confined in slit-shaped carbon nanospace.** *J Am Chem Soc* 2002, **124**: 11860–11861.
 74. Margarella AM, Perrine KA, Lewis T, Faubel M, Winter B, Hemminger JC: **Dissociation of sulfuric acid in aqueous solution: determination of the photoelectron spectral fingerprints of H₂SO₄, HSO₄⁻, and SO₄²⁻ in water.** *J Phys Chem C* 2013, **117**:8131–8137.
 75. Persson I, Klysubun W, Lundberg D: **A K-edge P XANES study of phosphorus compounds in solution.** *J Mol Struct* 2019, **1179**:608–611, <https://doi.org/10.1016/j.molstruc.2018.11.059>. Available from:.
 76. Axnanda S, Crumlin EJ, Mao B, Rani S, Chang R, Karlsson PG, *et al.*: **Using “tender” X-ray ambient pressure X-ray photoelectron spectroscopy as A direct probe of solid-liquid interface.** *Sci Rep* 2015, **5**, 09788.
 77. Velasco-velez JJ, Pfeifer V, Hävecker M, Weatherup RS, Arrigo R, Chuang C, *et al.*: **Photoelectron spectroscopy at the graphene – liquid interface reveals the electronic structure of an electrodeposited cobalt/graphene electrocatalyst.** *Angew Chem Int Ed* 2015, **54**:14554–14558.
 78. Lichterman MF, Richter MH, Hu S, Crumlin EJ, Axnanda S, Favaro M, *et al.*: **An electrochemical, microtopographical and ambient pressure X-ray photoelectron spectroscopic investigation of Si/TiO₂/Ni/electrolyte interfaces.** *J Electrochem Soc* 2016, **163**:H139–H146.
 79. Lucas CA, Thompson P, Gründer Y, Markovic NM: **The structure of the electrochemical double layer: Ag (111) in alkaline electrolyte.** *Electrochem Commun* 2011, **13**:1205–1208, <https://doi.org/10.1016/j.elecom.2011.08.043>. Available from:.
 80. Tanaka S, Tajiri H, Sakata O, Hoshi N, Nakamura M: **Interfacial structure of Pt(110) electrode during hydrogen evolution**

- reaction in alkaline solutions.** *J Phys Chem Lett* 2022, **13**: 8403–8408.
Resolves the position of interfacial Cs and water molecules during alkaline hydrogen evolution on Pt(110).
81. Nakamura M, Nakajima Y, Kato K, Sakata O, Hoshi N: **Surface oxidation of Au(111) electrode in alkaline media studied by using X-ray diffraction and infrared spectroscopy: effect of alkali metal cation on the alcohol oxidation reactions.** *J Phys Chem C* 2015, **119**:23586–23591.
 82. Liu Y, Kawaguchi T, Pierce MS, Komanicky V, You H: **Layering and ordering in electrochemical double layers.** *J Phys Chem Lett* 2018, **9**:1265–1271.
 83. Kawaguchi T, Rao RR, Lunger JR, Liu Y, Walko D, Karapetrova EA, *et al.*: **Stern layers on RuO₂(100) and (110) in electrolyte: surface X-ray scattering studies.** *J Electroanal Chem* 2020, **875**, 114228, <https://doi.org/10.1016/j.jelechem.2020.114228>. Available from:.
 84. Vlieg E: *ROD Software page*. 2019. Available from: https://www.esrf.fr/computing/scientific/joint_projects/ANA-ROD/index.htm.
 85. Monteiro MCO, Dattila F, Hagedoorn B, García-Muelas R, López N, Koper MTM: **Absence of CO₂ electroreduction on copper, gold and silver electrodes without metal cations in solution.** *Nat Catal* 2021, **4**:654–662.
 86. Malkani AS, Li J, Oliveira NJ, He M, Chang X, Xu B, *et al.*: **Understanding the electric and nonelectric field components of the cation effect on the electrochemical CO reduction reaction.** *Sci Adv* 2020, **6**, eabd2569.